Multiaxial Fatigue

Professor Darrell F. Socie

Department of Mechanical Science and Engineering

University of Illinois at Urbana-Champaign

© 2001-2011 Darrell Socie, All Rights Reserved

Contact Information

Darrell Socie
Mechanical Science and Engineering
1206 West Green
Urbana, Illinois 61801
USA

d-socie@uiuc.edu
Tel: 217 333 7630
Fax: 217 333 5634

 © 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Outline

- State of Stress (Chapter 1)
- Fatigue Mechanisms (Chapter 3)
- Stress Based Models (Chapter 5)
- Strain Based Models (Chapter 6)
- Fracture Mechanics Models (Chapter 7)
- Nonproportional Loading (Chapter 8)
- Notches (Chapter 9)

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

State of Stress

- Stress components
- Common states of stress
- Shear stresses

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress Components

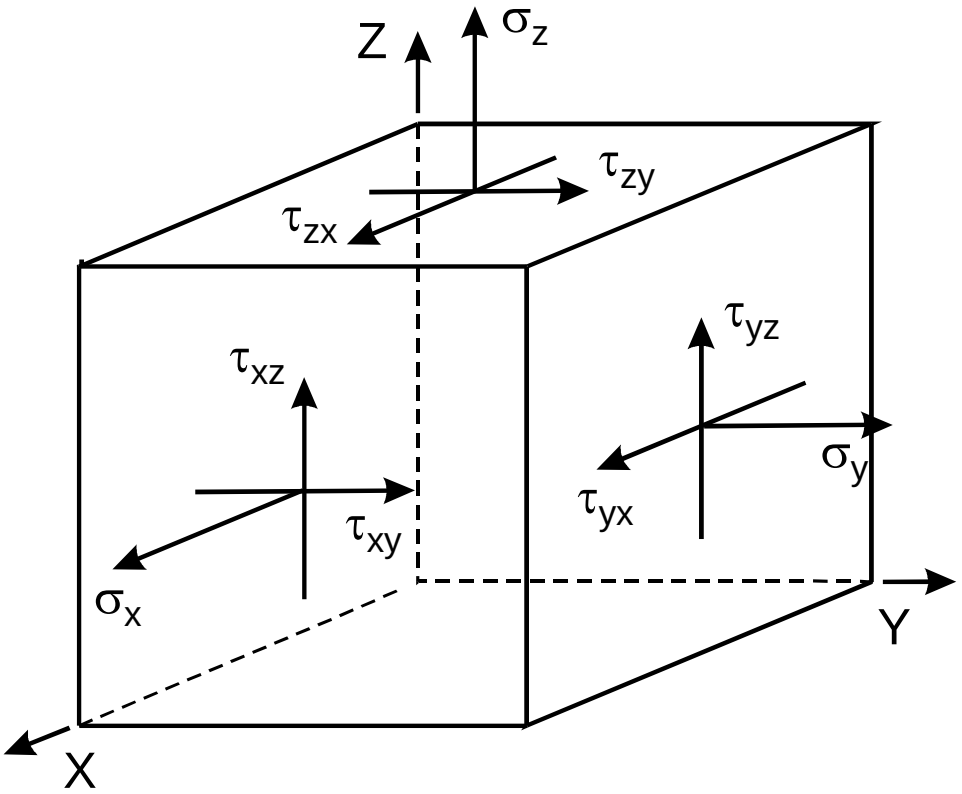

Six stresses and six strains

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stresses Acting on a Plane

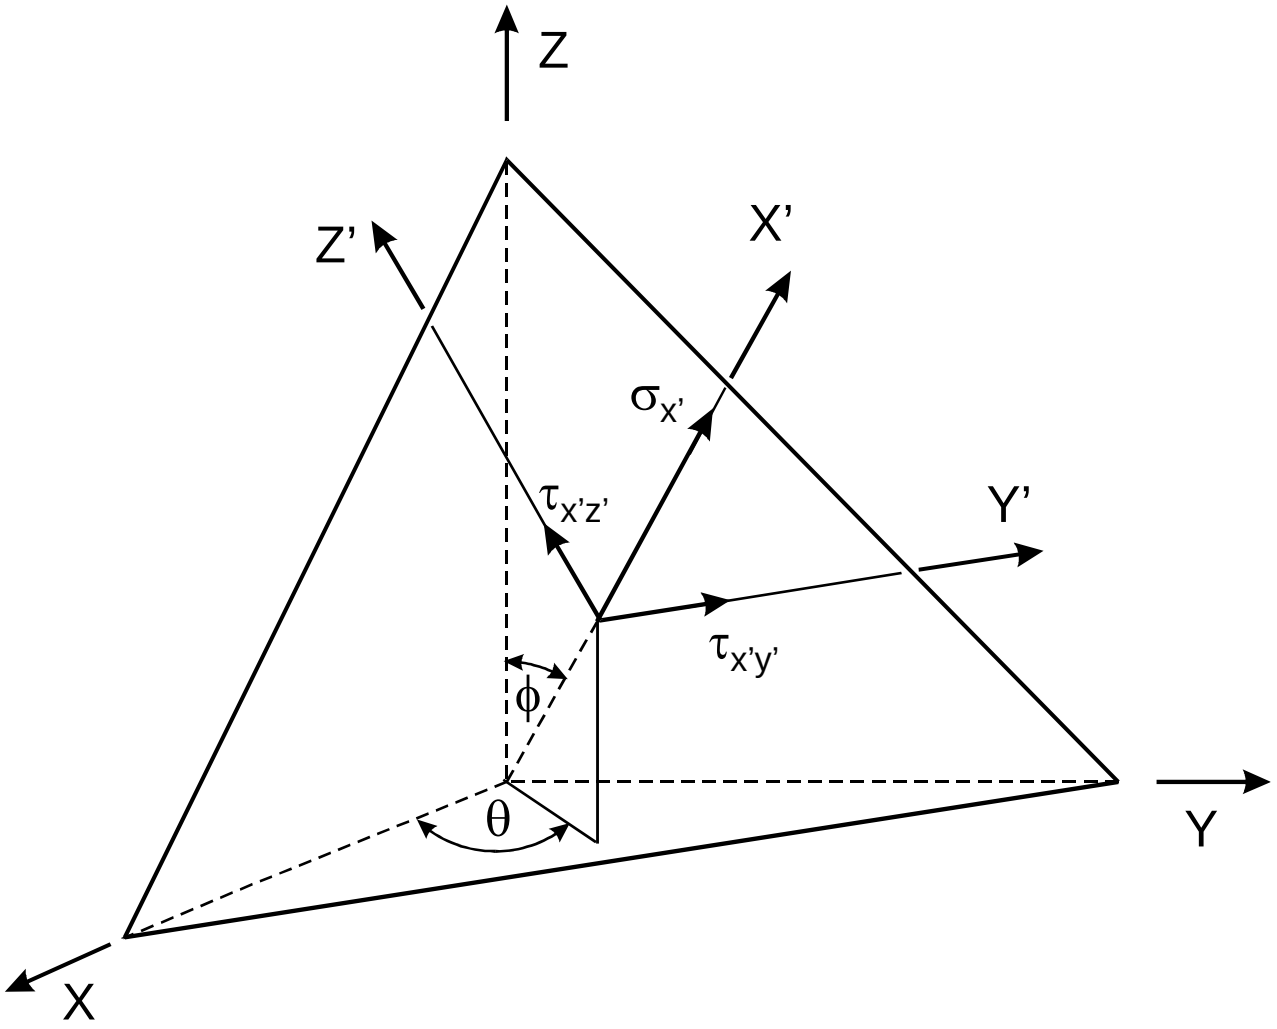

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Principal Stresses

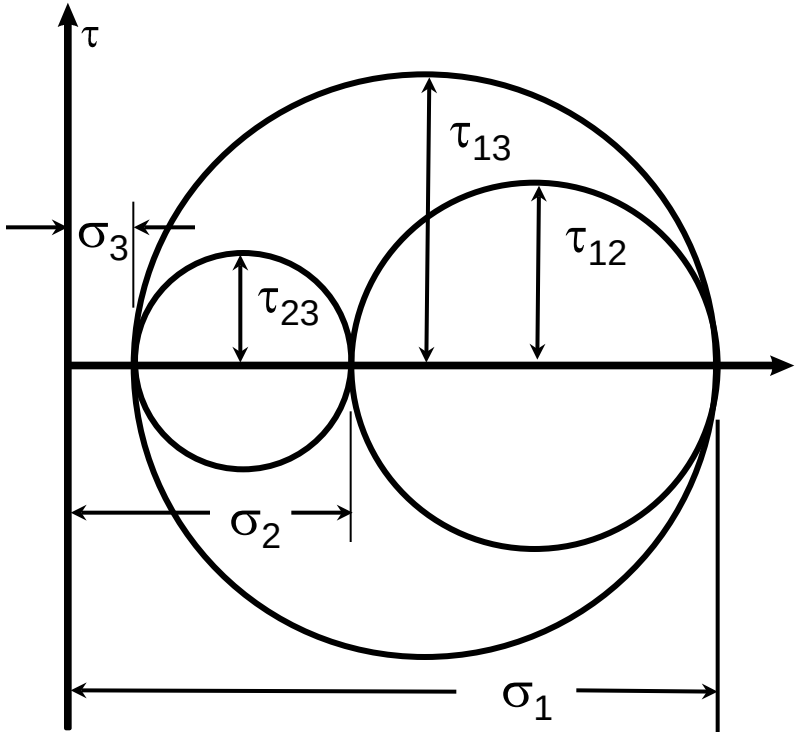

$$\sigma^3 - \sigma^2(\sigma_X + \sigma_Y + \sigma_Z) + \sigma(\sigma_X\sigma_Y + \sigma_Y\sigma_Z\sigma_X\sigma_Z - \tau^2_{XY} - \tau^2_{YZ} - \tau^2_{XZ}) - (\sigma_X\sigma_Y\sigma_Z + 2\tau_{XY}\tau_{YZ}\tau_{XZ} - \sigma_X\tau^2_{YZ} - \sigma_Y\tau^2_{ZX} - \sigma_Z\tau^2_{XY}) = 0$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress and Strain Distributions

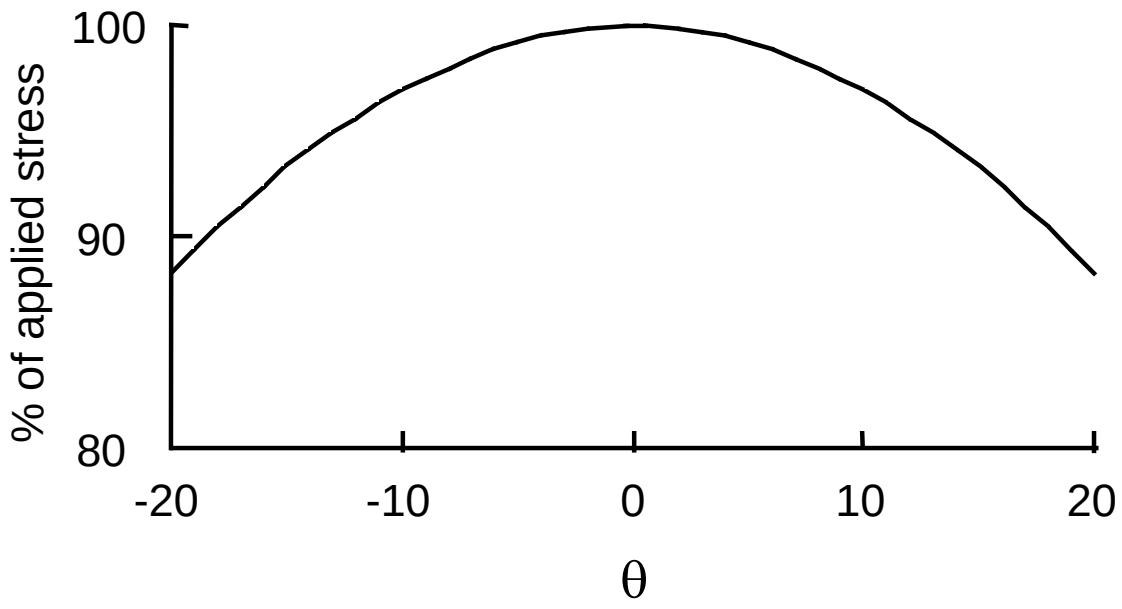

Stresses are nearly the same over a 10° range of angles

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Tension

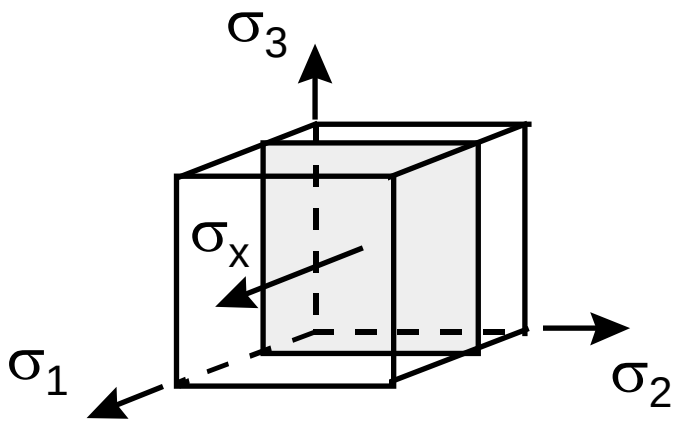

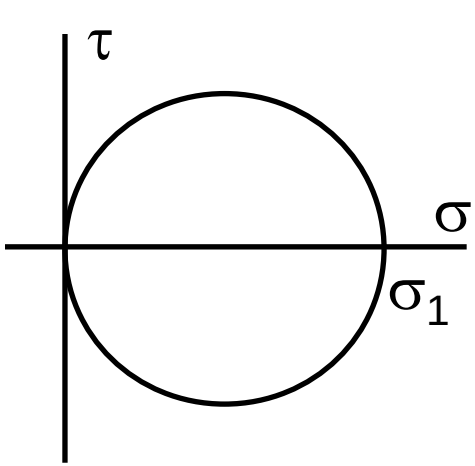

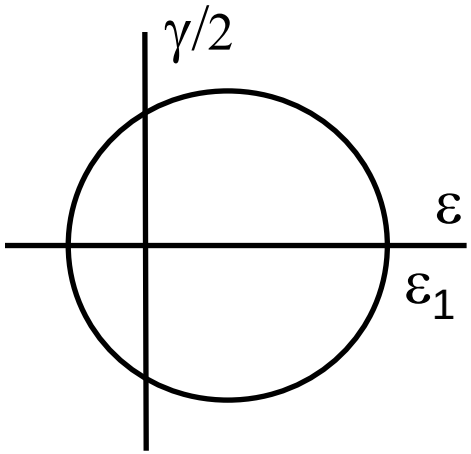

$\sigma_2 = \sigma_3 = 0$

$\varepsilon_2 = \varepsilon_3 = -\nu\varepsilon_1$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Torsion

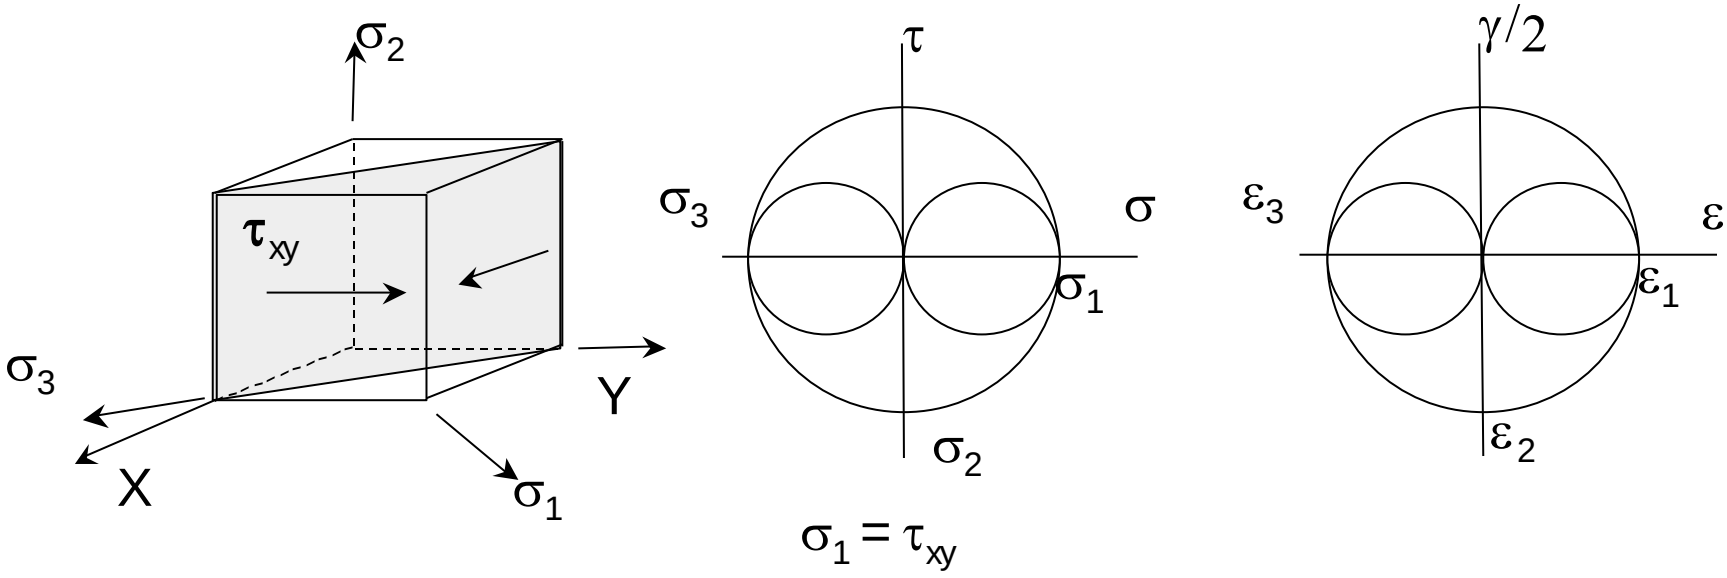

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Biaxial Tension

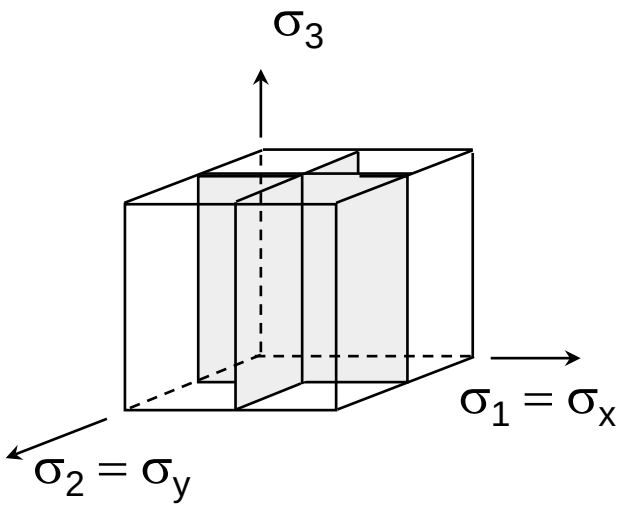

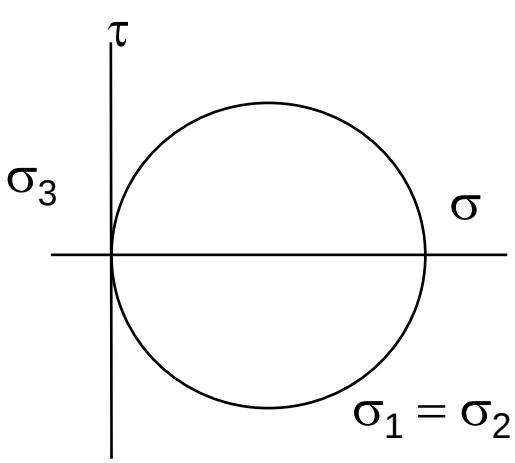

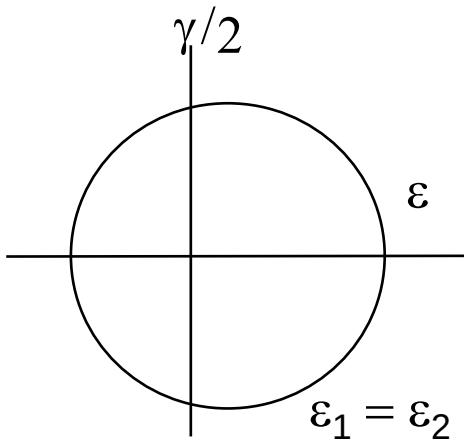

$$\varepsilon_3 = -\frac{2\nu}{1-\nu}\varepsilon$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Shear Stresses

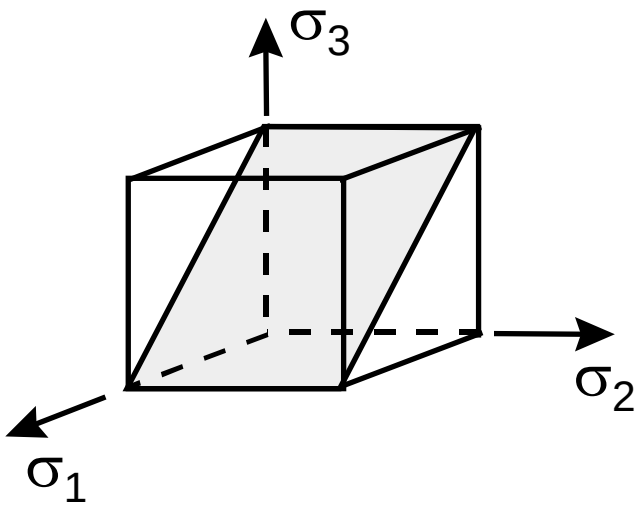

Maximum shear stress

$$\tau_{13} = \frac{|\sigma_1 - \sigma_3|}{2}$$

Mises: $\bar{\sigma} = \frac{3}{\sqrt{2}}\tau_{oct}$

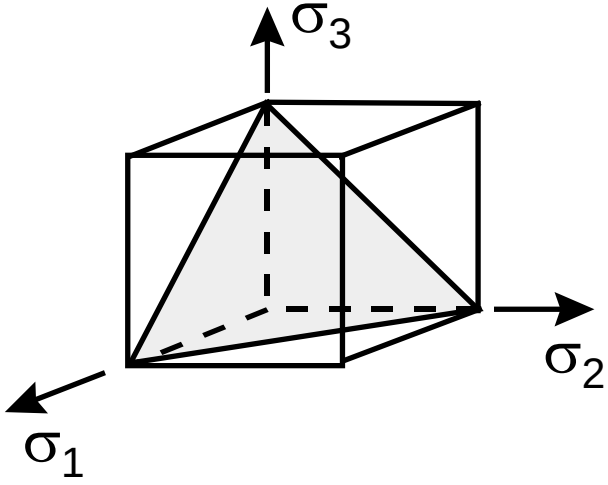

Octahedral shear stress

$$\tau_{oct} = \frac{1}{3}\sqrt{(\sigma_1-\sigma_3)^2+(\sigma_1-\sigma_2)^2+(\sigma_2-\sigma_3)^2}$$

$$\tau_{oct} = \frac{3}{2\sqrt{2}}\tau_{13} = 0.94\,\tau_{13}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

State of Stress Summary

- Stresses acting on a plane
- Principal stress
- Maximum shear stress
- Octahedral shear stress

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatigue Mechanisms

- Crack nucleation
- Fracture modes
- Crack growth
- State of stress effects

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Crack Nucleation

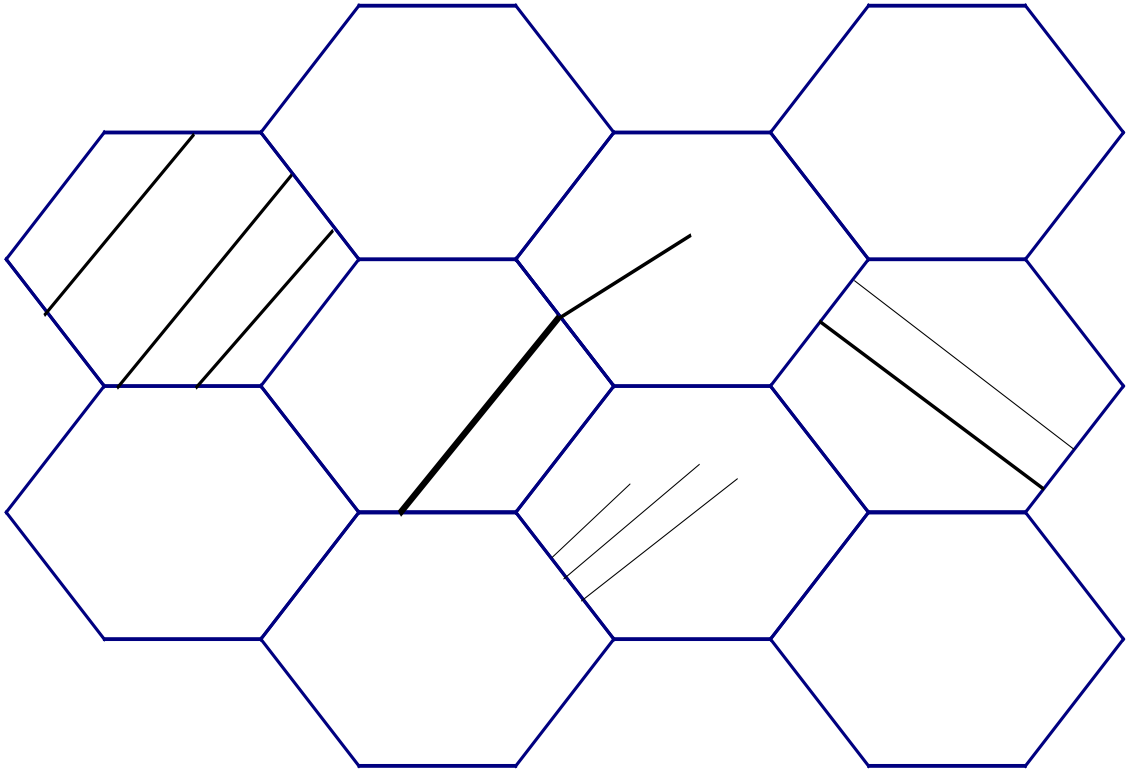

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Slip Bands

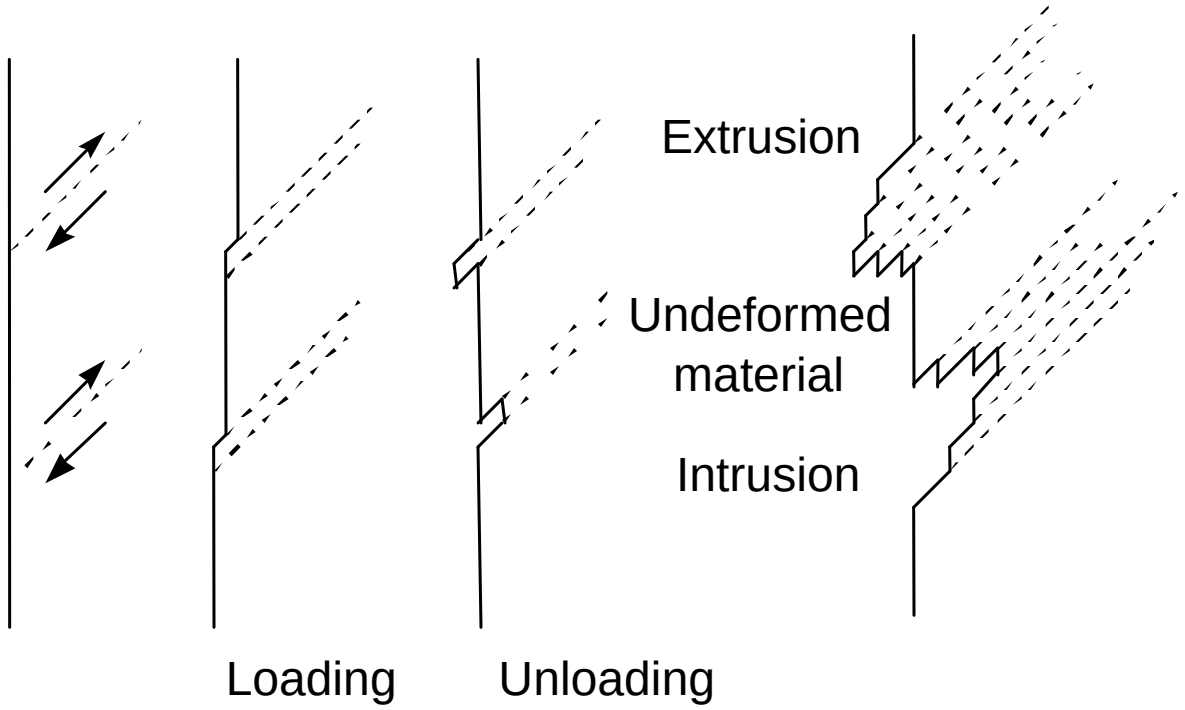

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Slip Bands

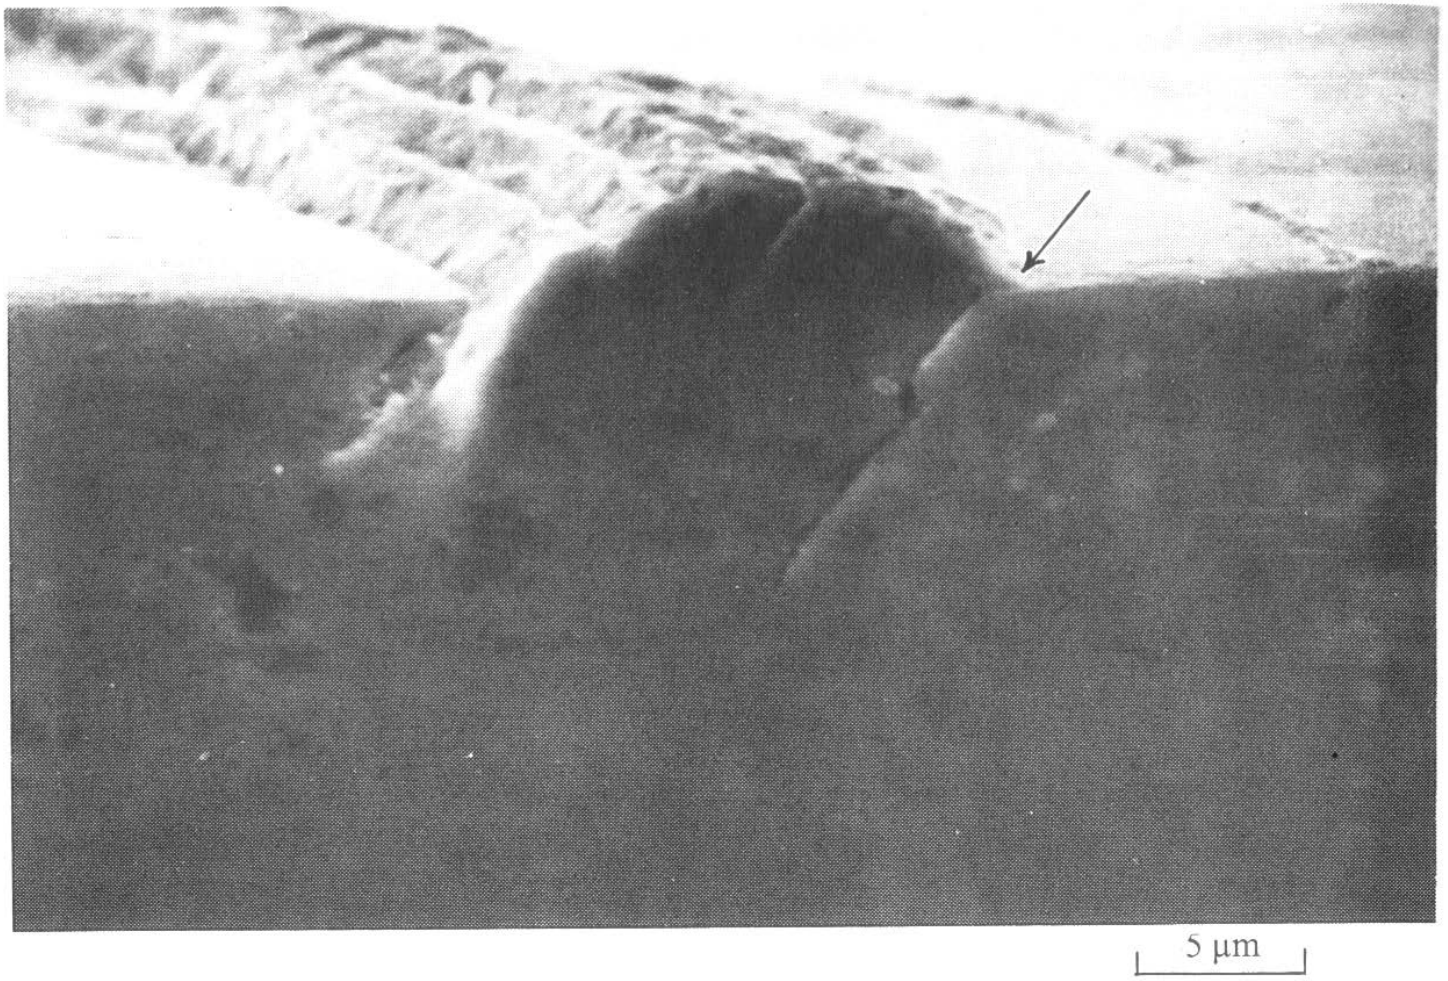

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode I, Mode II, and Mode III

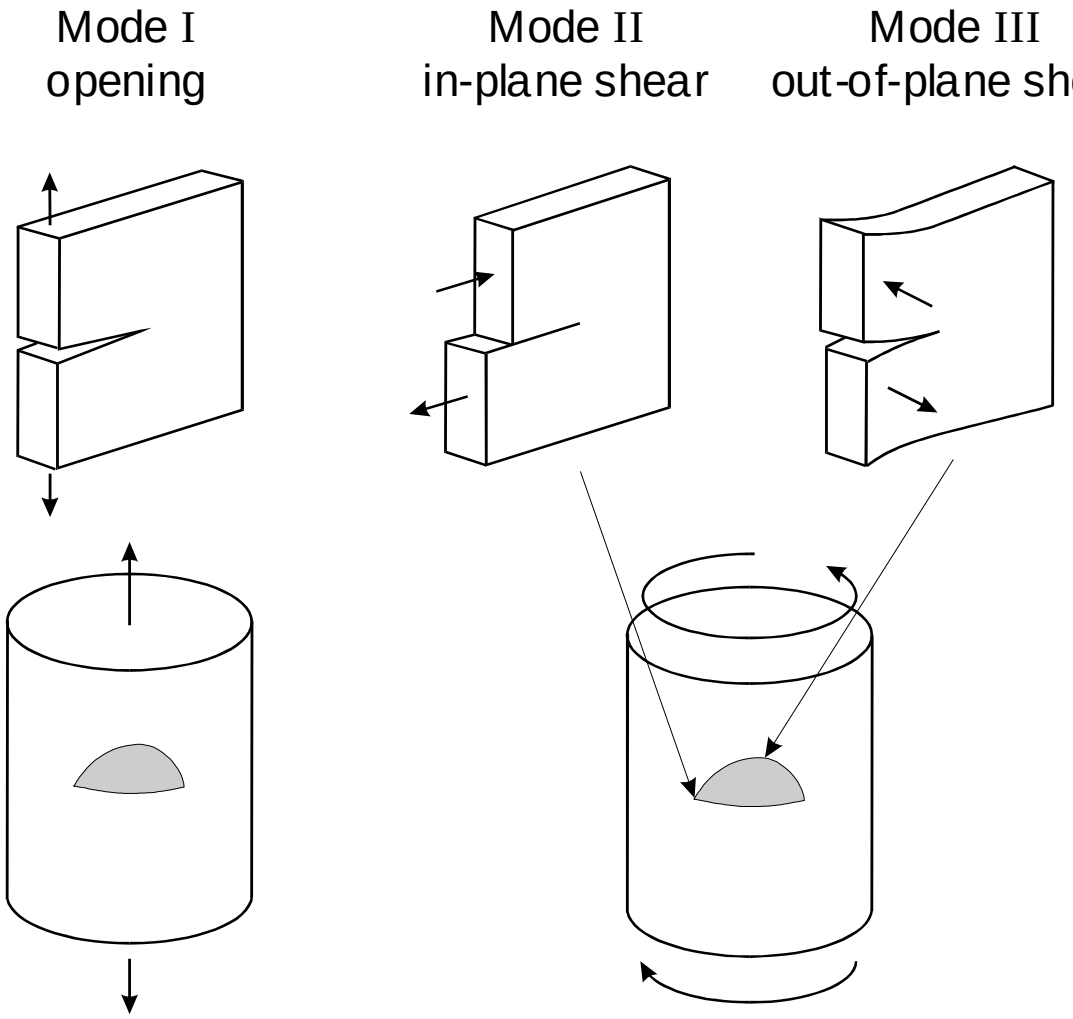

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stage I and Stage II

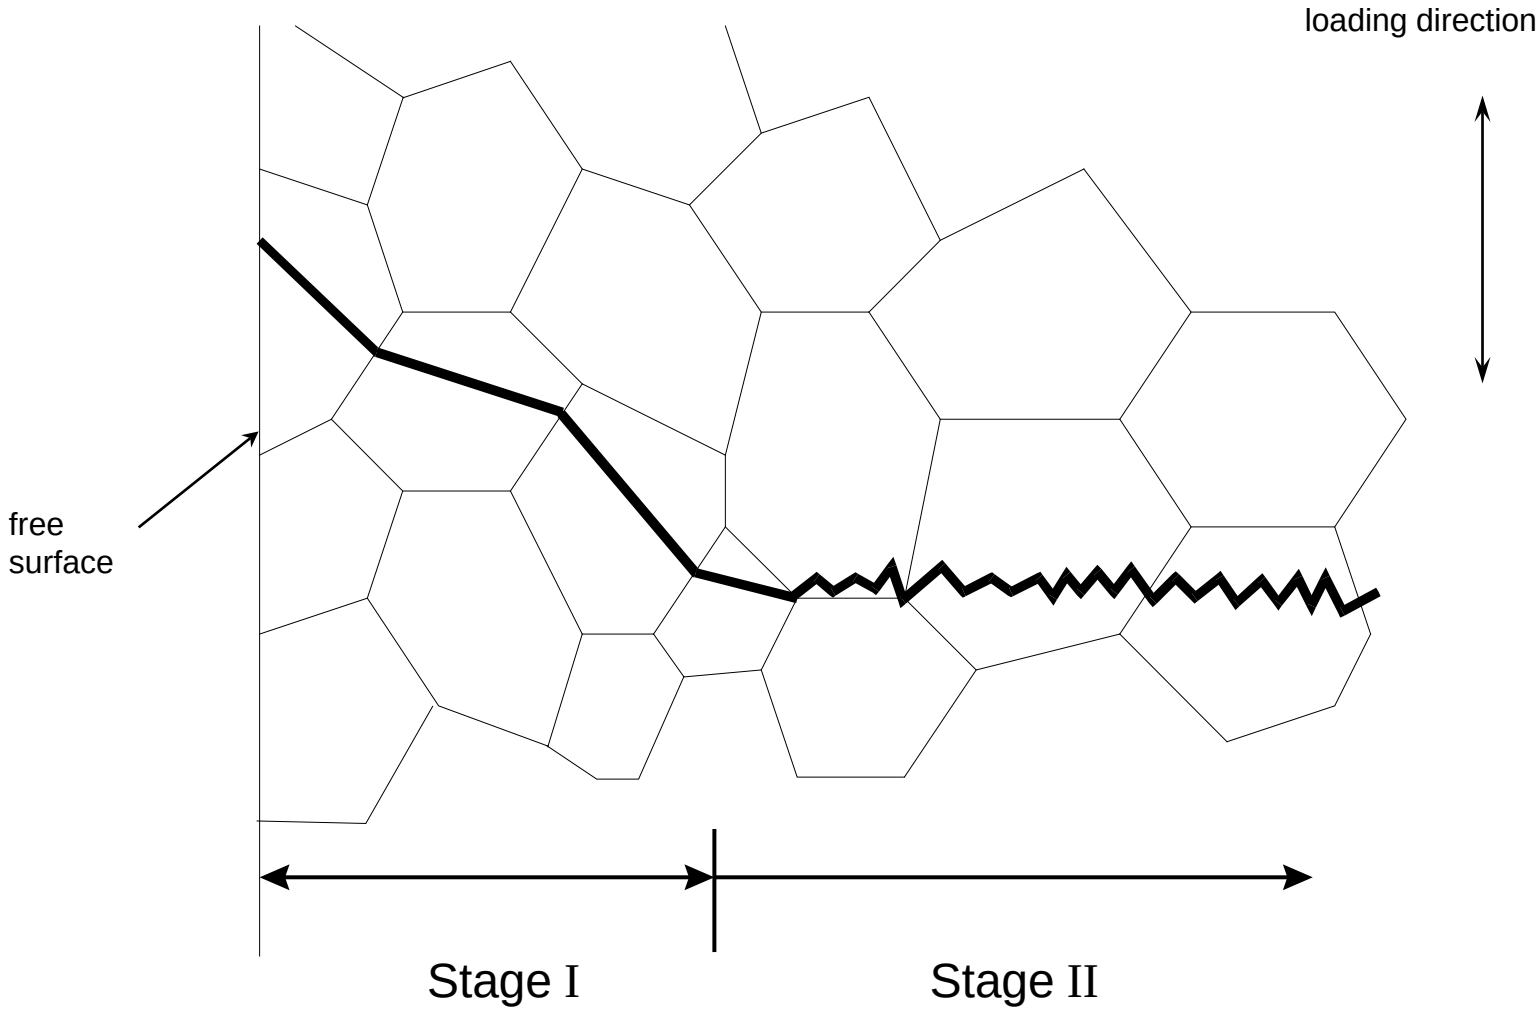

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Case A and Case B

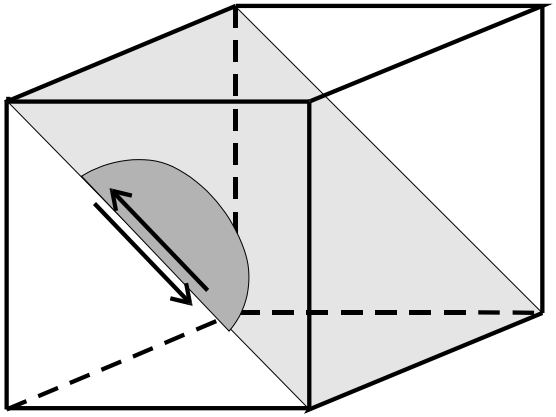

Case A

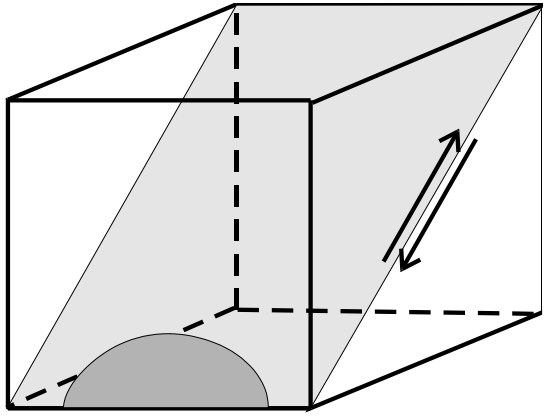

Case B

Growth along the surface

Growth into the surface

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode I Growth

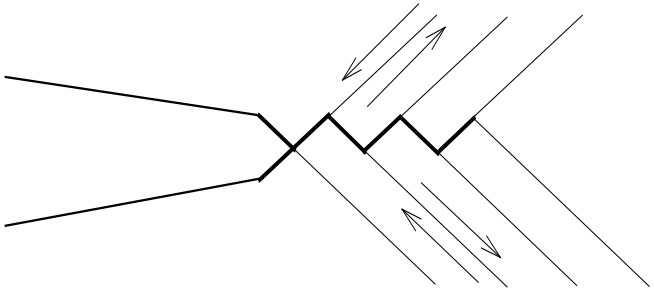

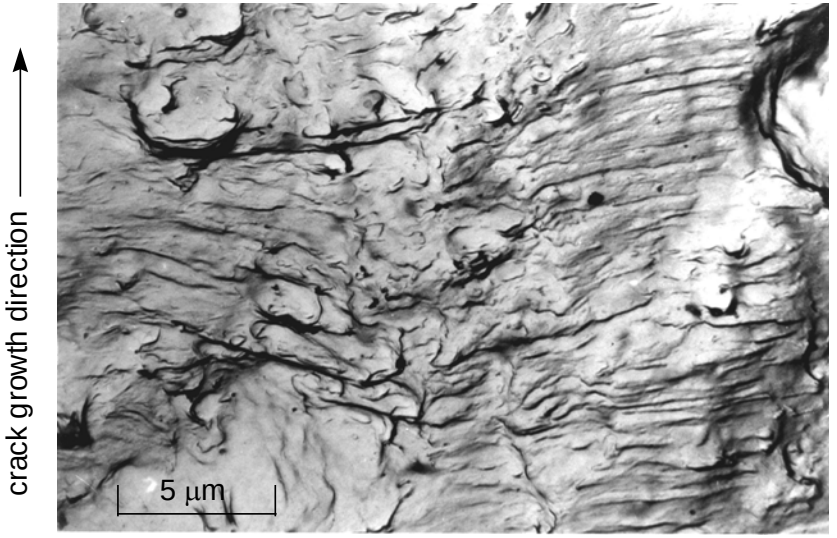

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode II Growth

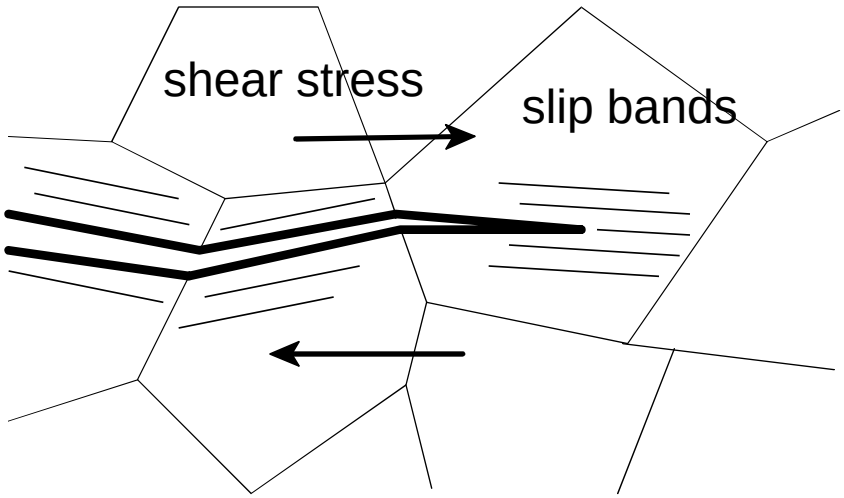

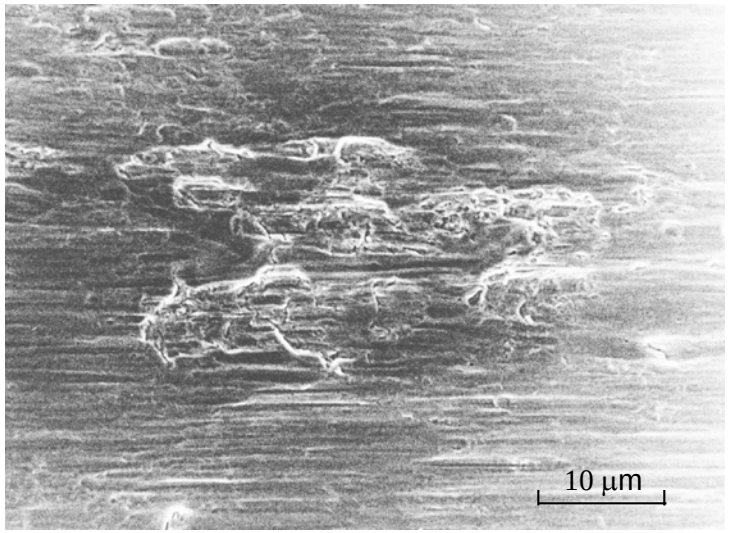

crack growth direction

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

304 Stainless Steel - Torsion

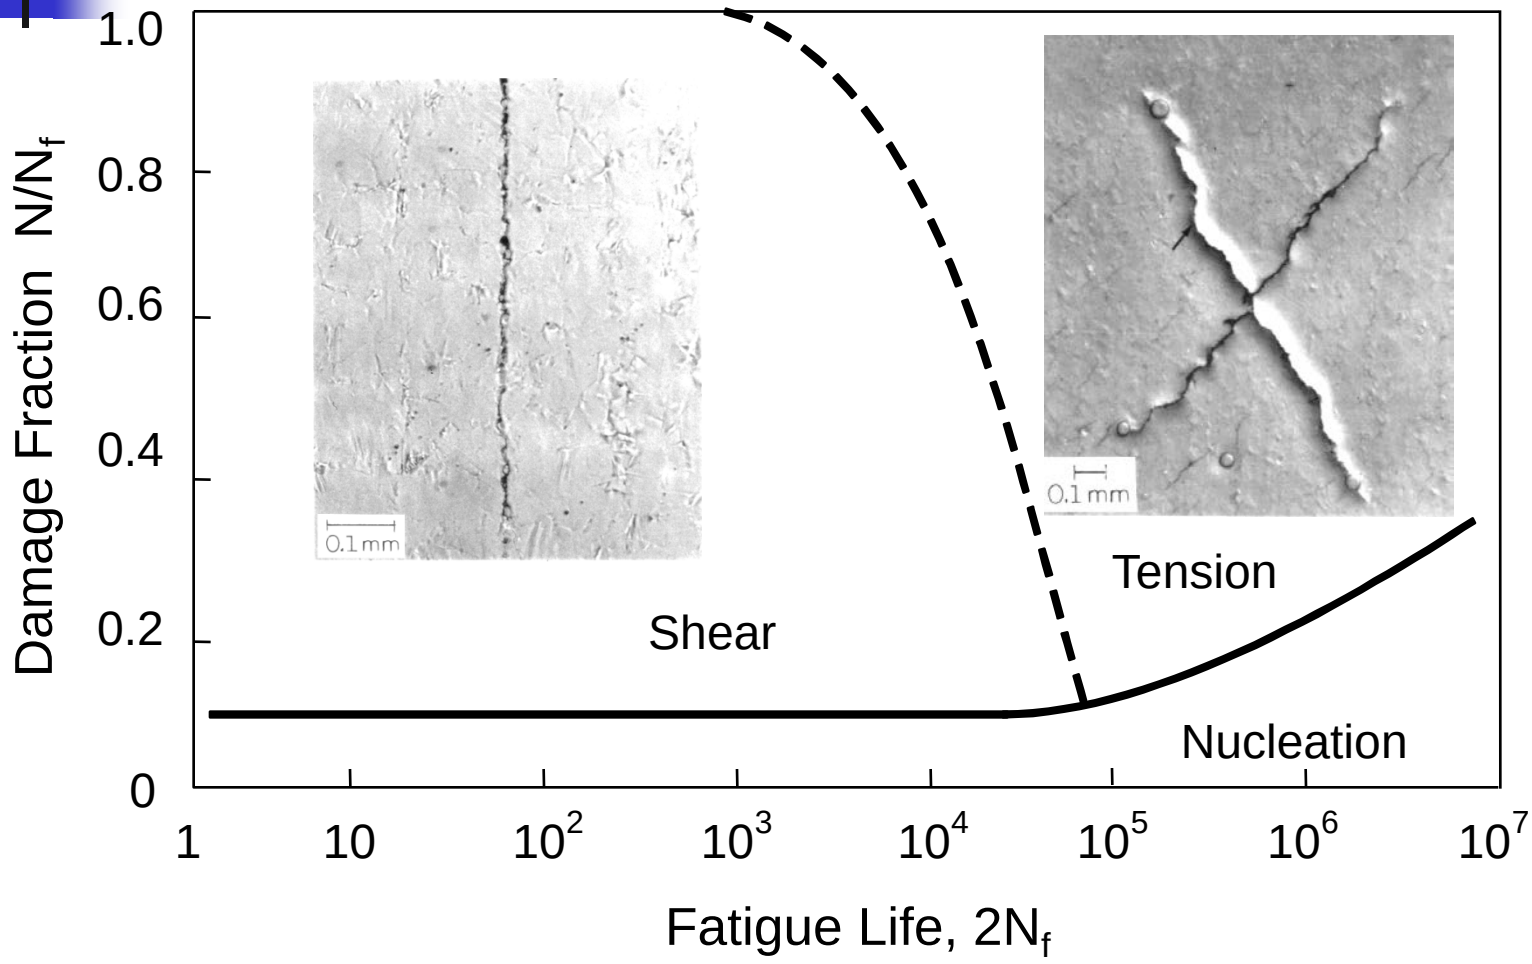

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

304 Stainless Steel - Tension

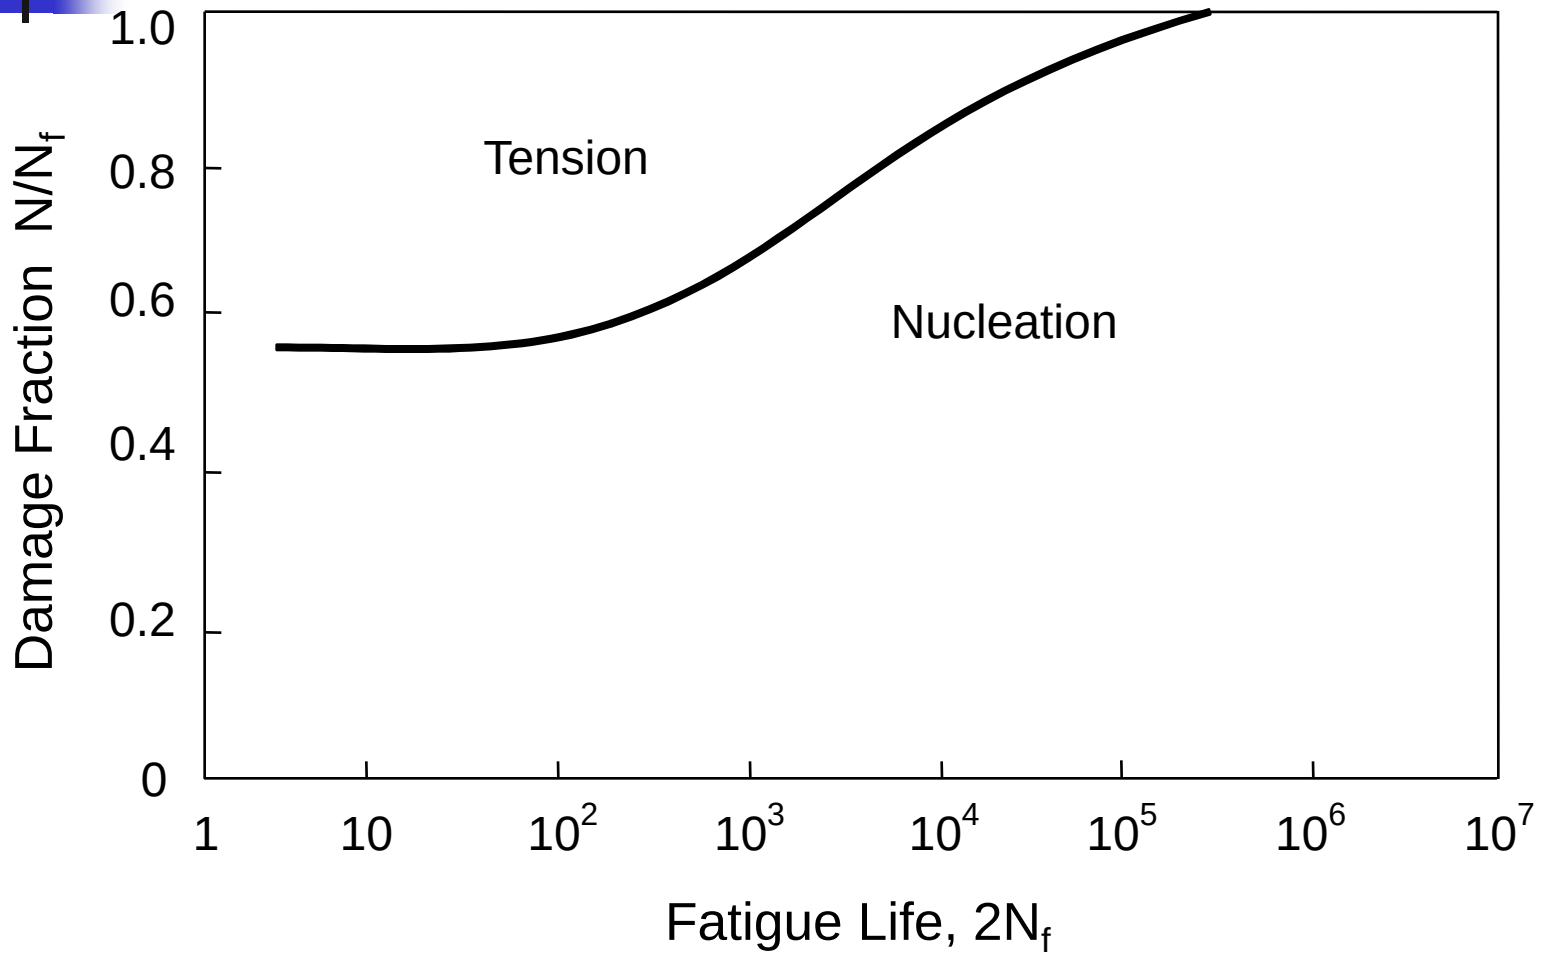

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Inconel 718 - Torsion

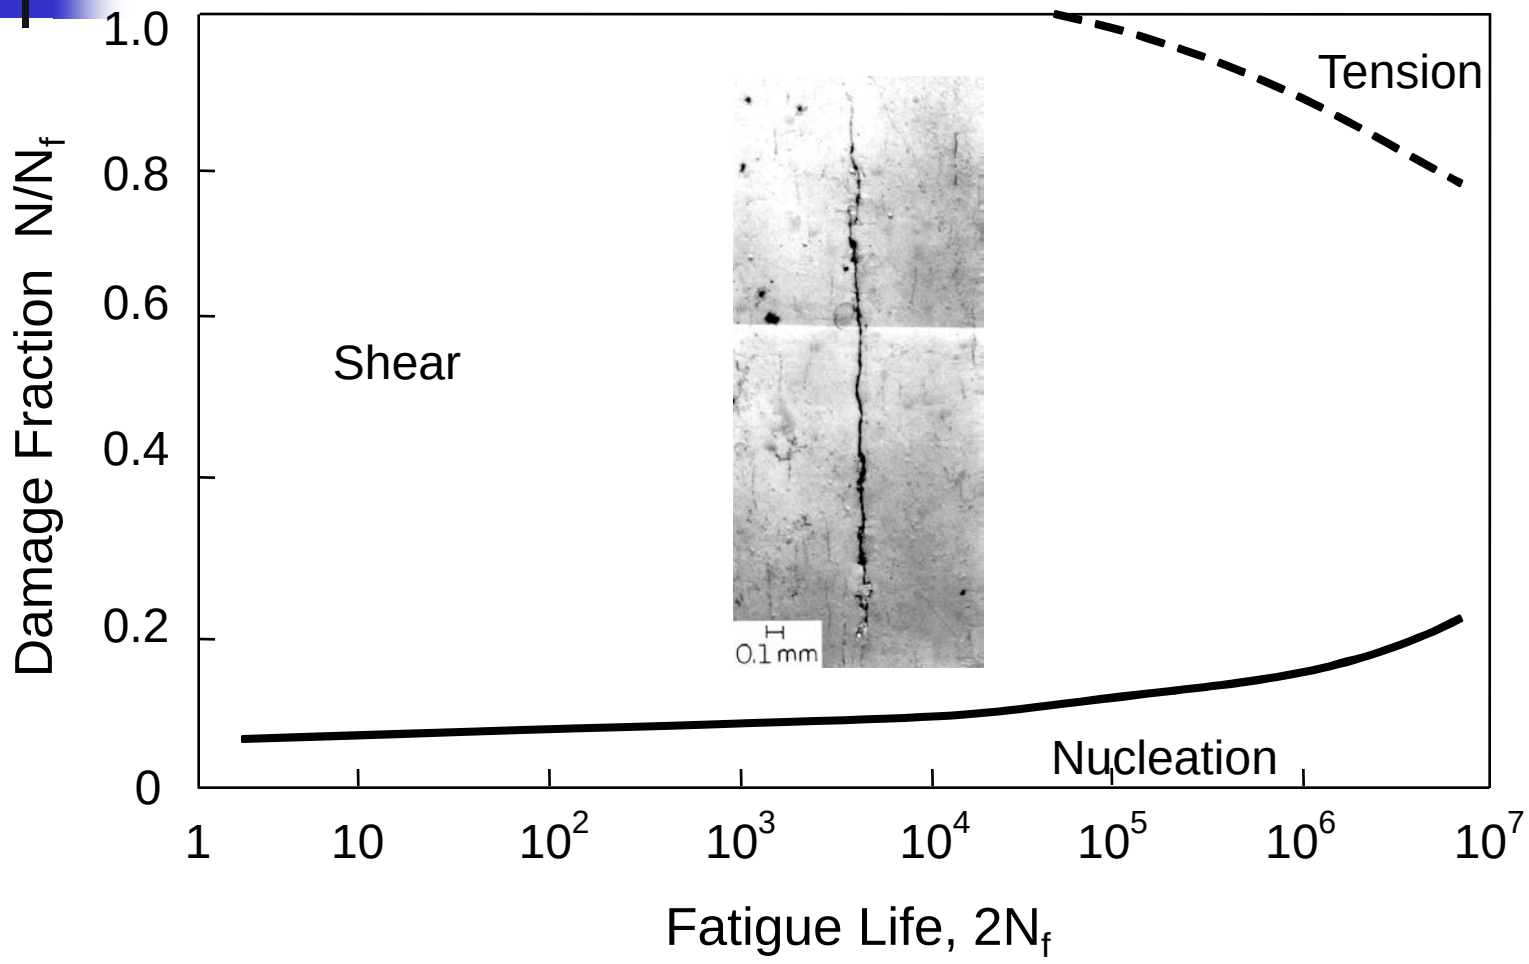

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Inconel 718 - Tension

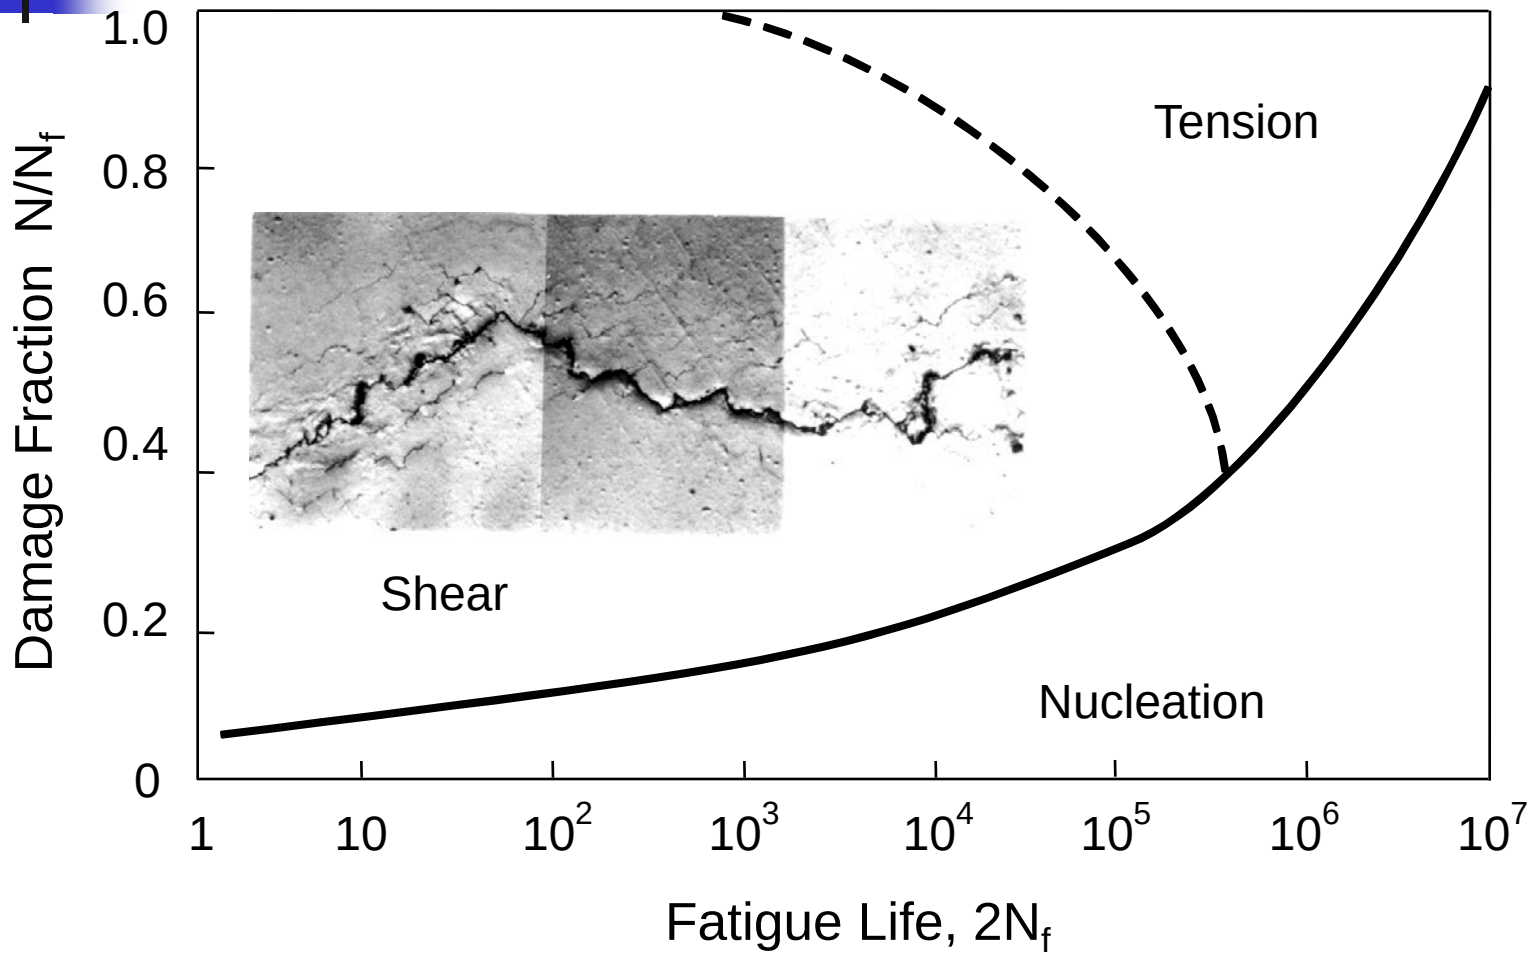

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

1045 Steel - Torsion

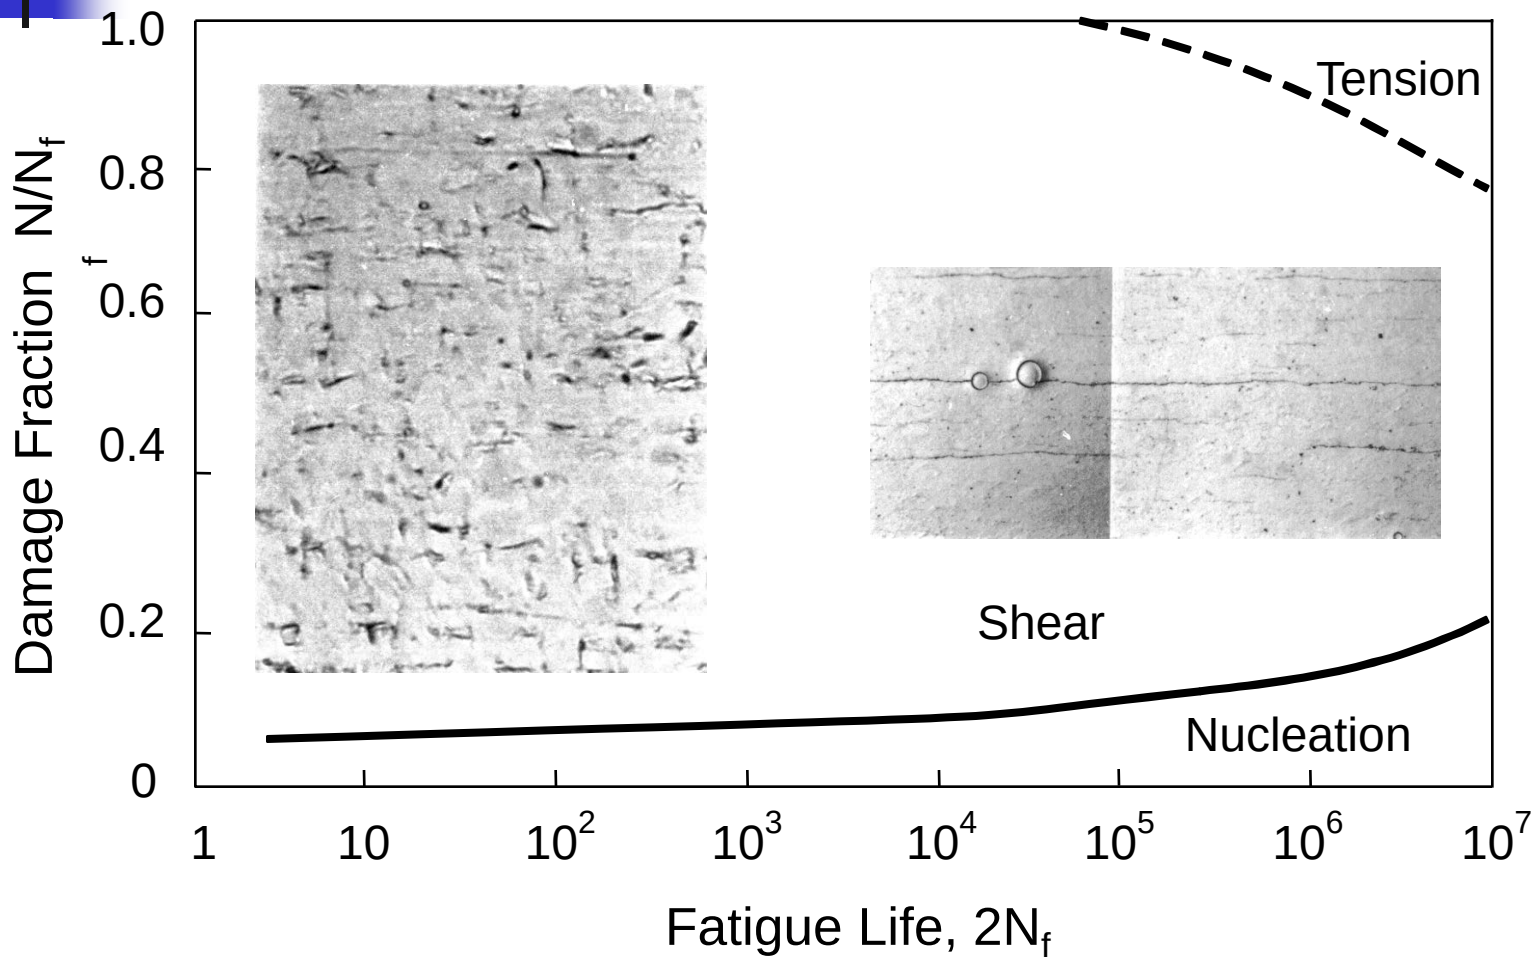

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

1045 Steel - Tension

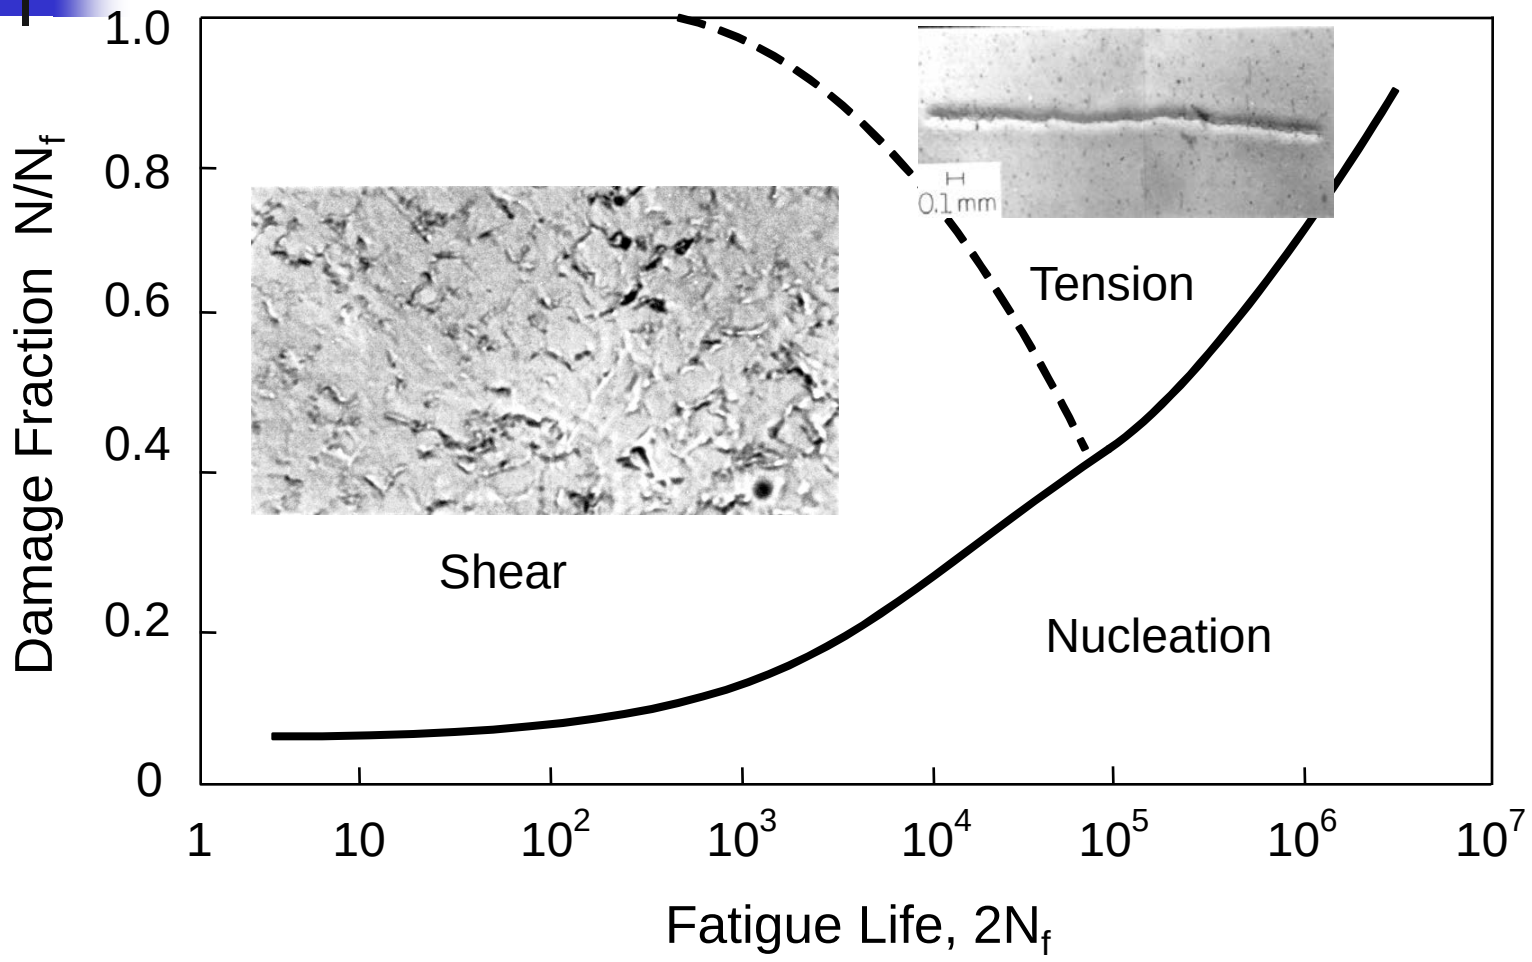

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatigue Mechanisms Summary

- Fatigue cracks nucleate in shear
- Fatigue cracks grow in either shear or tension depending on material and state of stress

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress Based Models

- Sines
- Findley
- Dang Van

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Bending Torsion Correlation

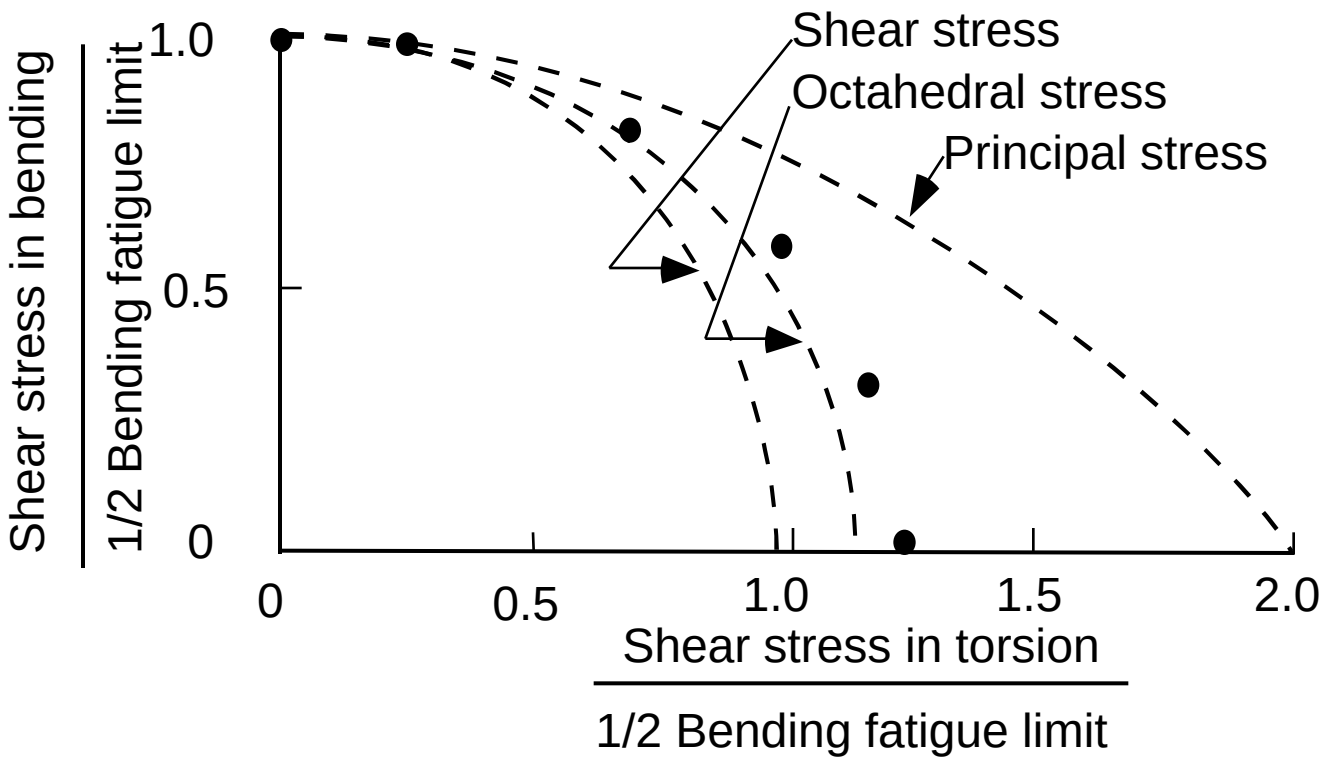

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Test Results

- Cyclic tension with static tension
- Cyclic torsion with static torsion
- Cyclic tension with static torsion
- Cyclic torsion with static tension

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Tension with Static Tension

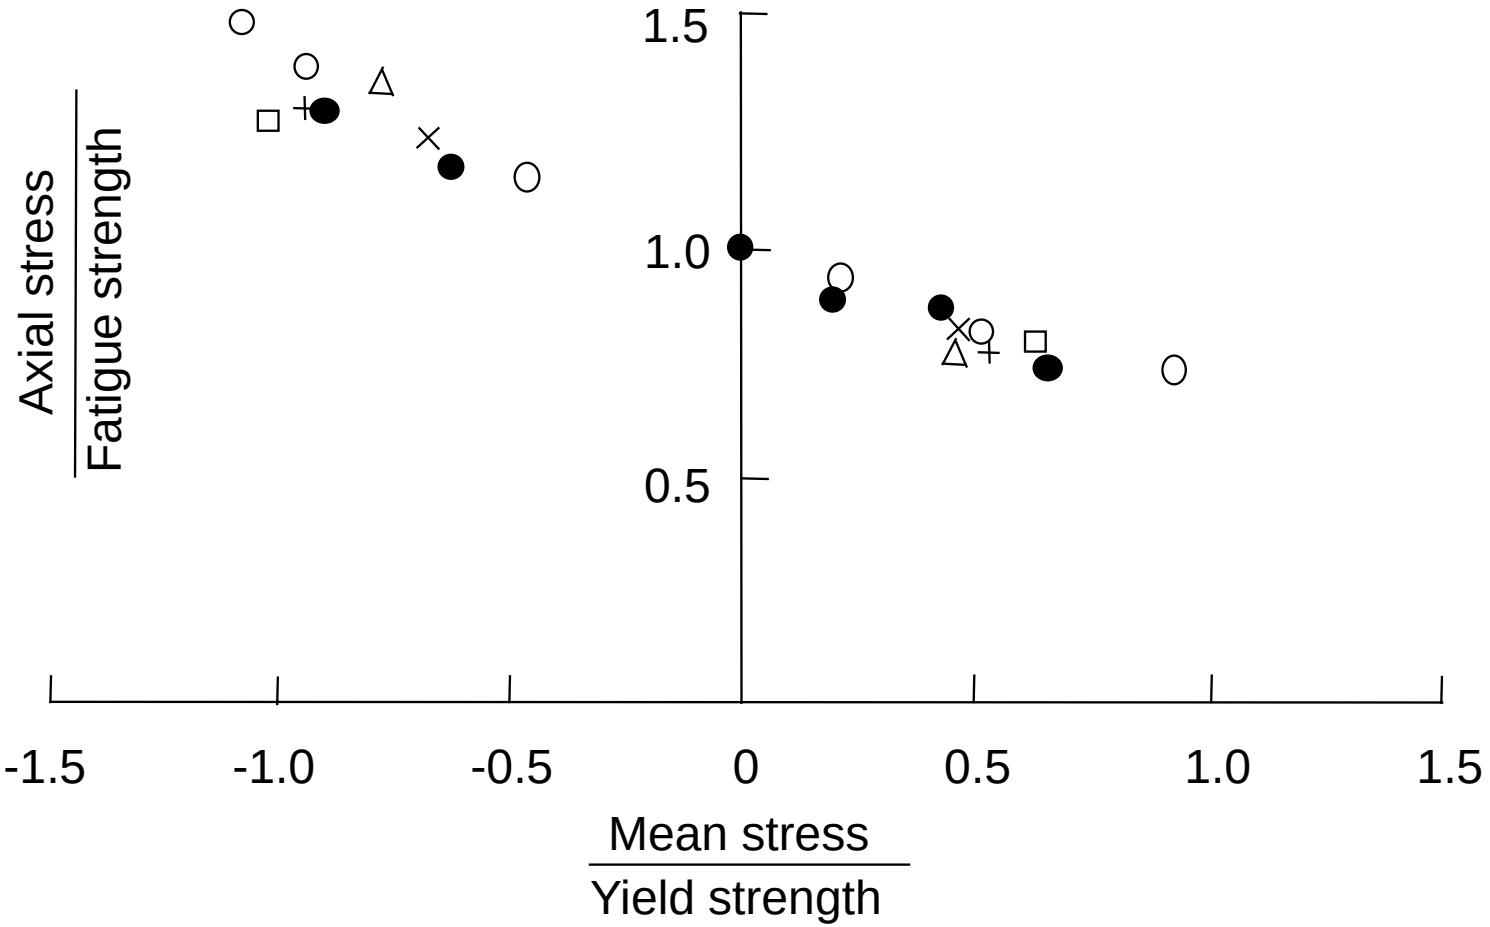

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Torsion with Static Torsion

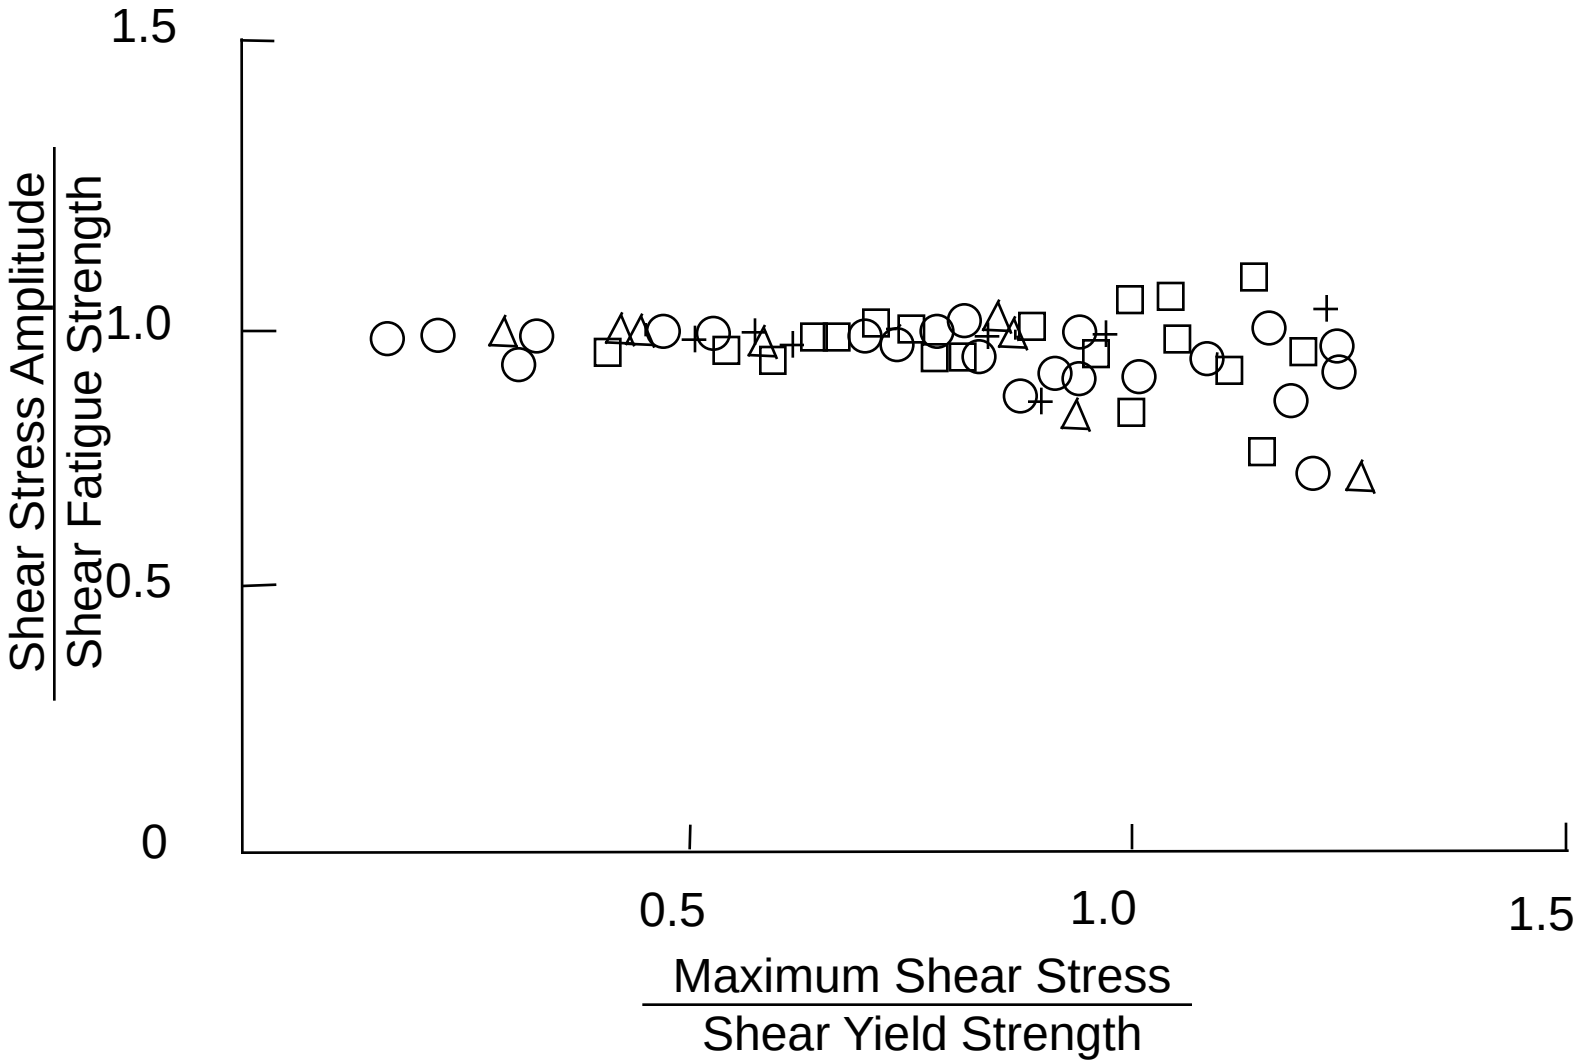

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Tension with Static Torsion

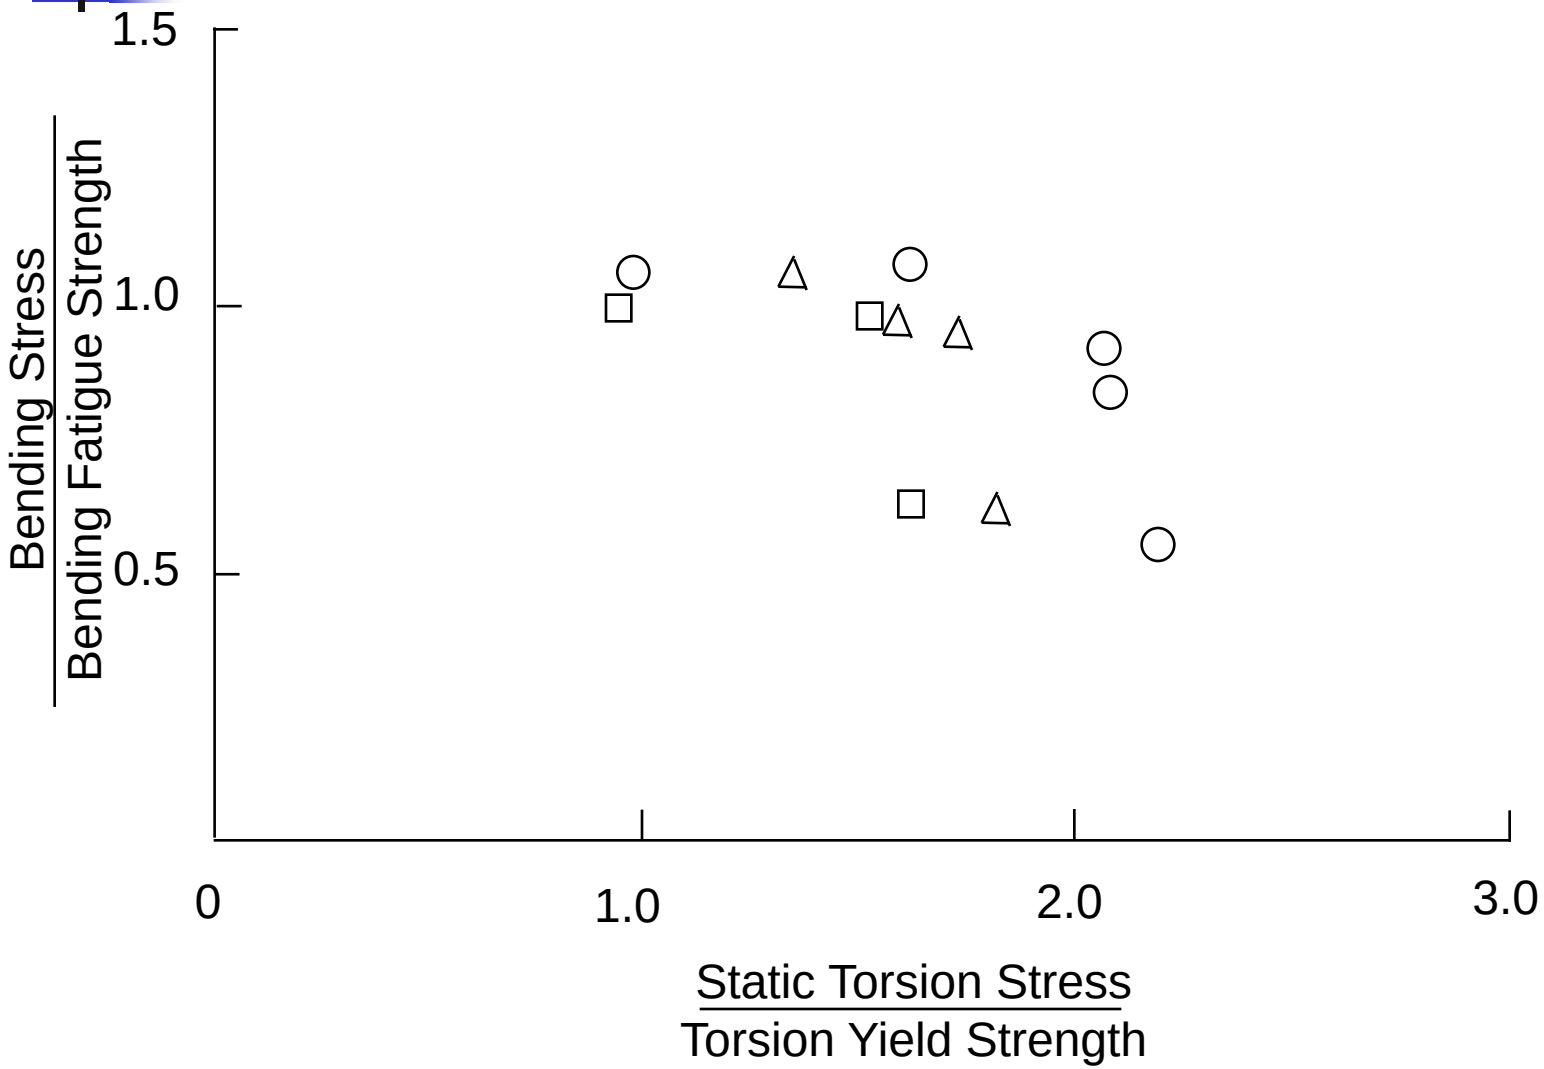

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Torsion with Static Tension

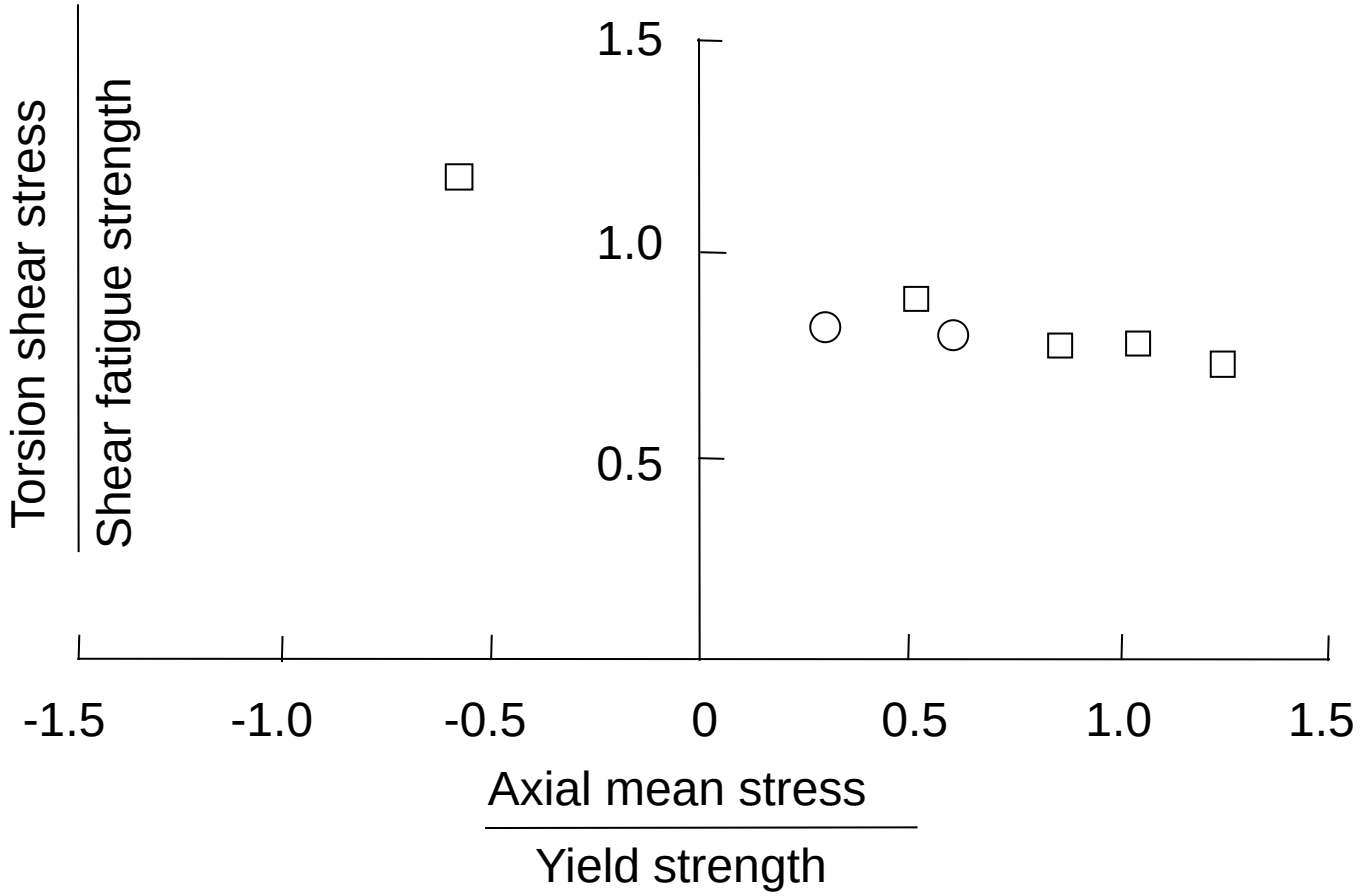

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Conclusions

- Tension mean stress affects both tension and torsion
- Torsion mean stress does not affect tension or torsion

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Sines

$$\frac{\Delta\tau_{oct}}{2} + \alpha(3\sigma_h) = \beta$$

$$\frac{1}{6}\sqrt{(\Delta\sigma_x - \Delta\sigma_y)^2 + (\Delta\sigma_x - \Delta\sigma_z)^2 + (\Delta\sigma_y - \Delta\sigma_z)^2 + 6(\Delta\tau_{xy}^2 + \Delta\tau_{xz}^2 + \Delta\tau_{yz}^2)} +$$

$$\alpha(\sigma_x^{mean} + \sigma_y^{mean} + \sigma_z^{mean}) = \beta$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Findley

$$\left(\frac{\Delta\tau}{2} + k\sigma_n\right)_{max} = f$$

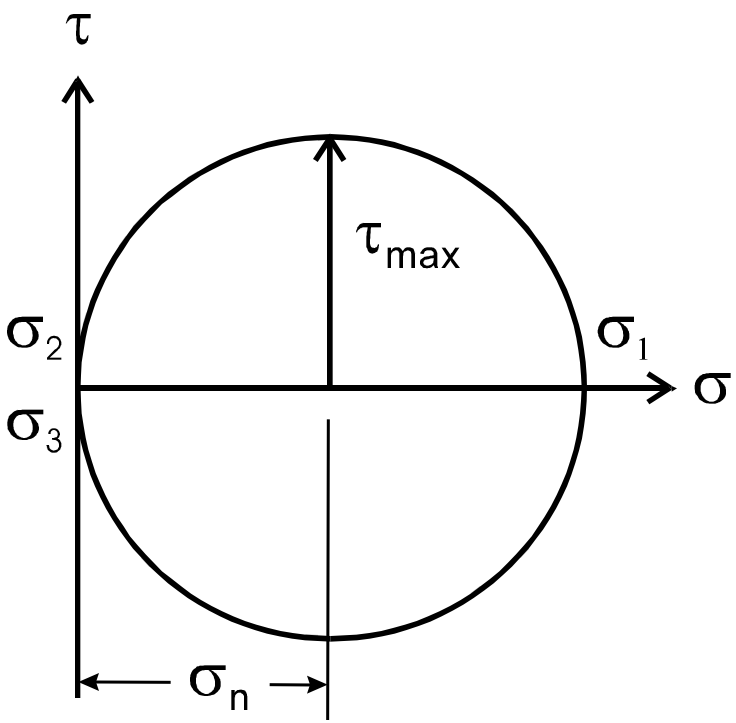

tension

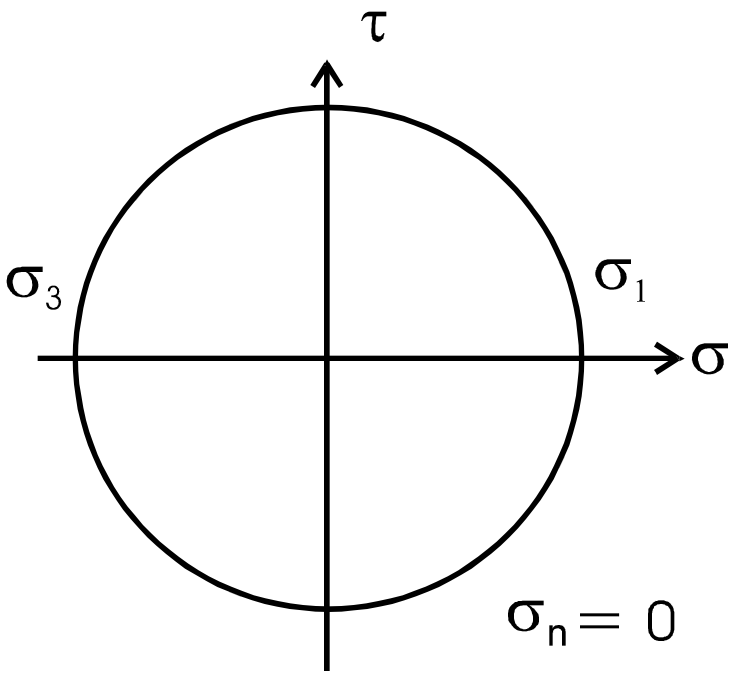

torsion

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Bending Torsion Correlation

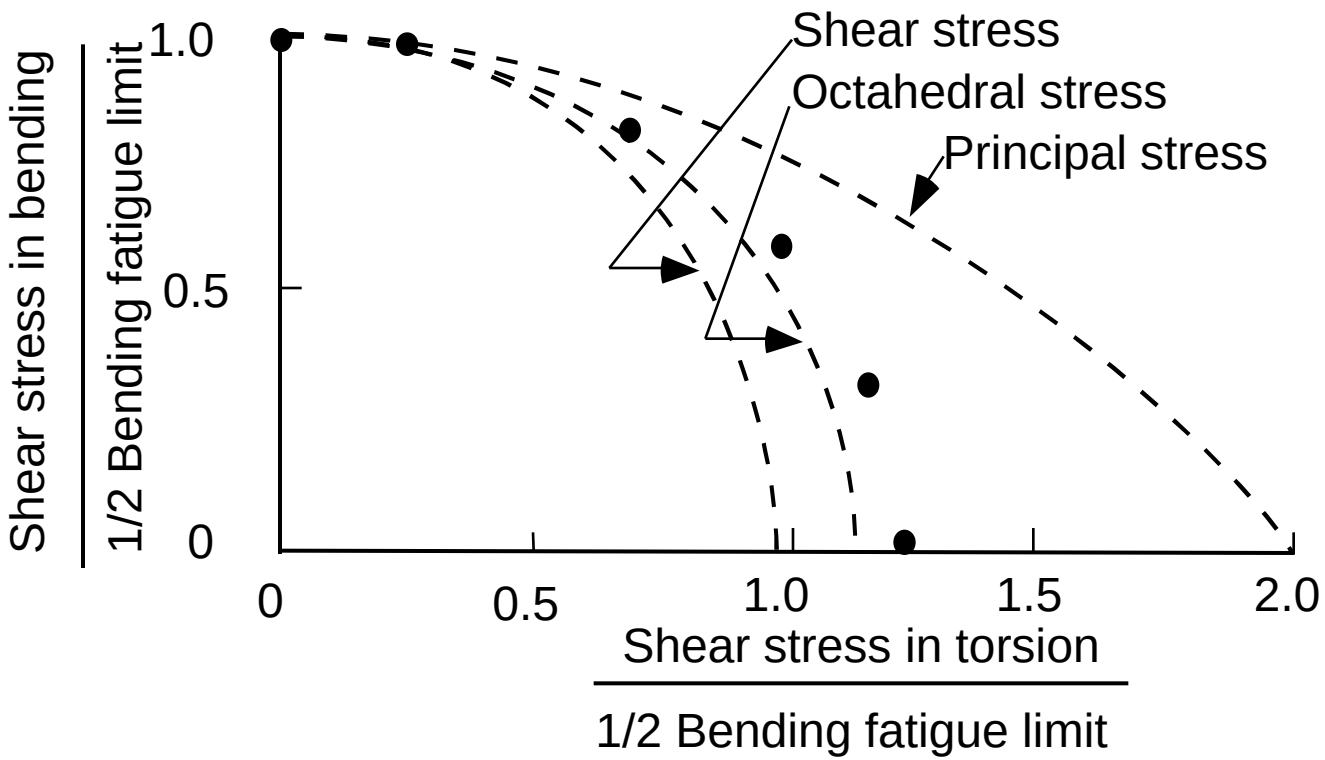

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Dang Van

$$\tau(t) + a\sigma_h(t) = b$$

$\Sigma_{ij}(M,t)$ $E_{ij}(M,t)$

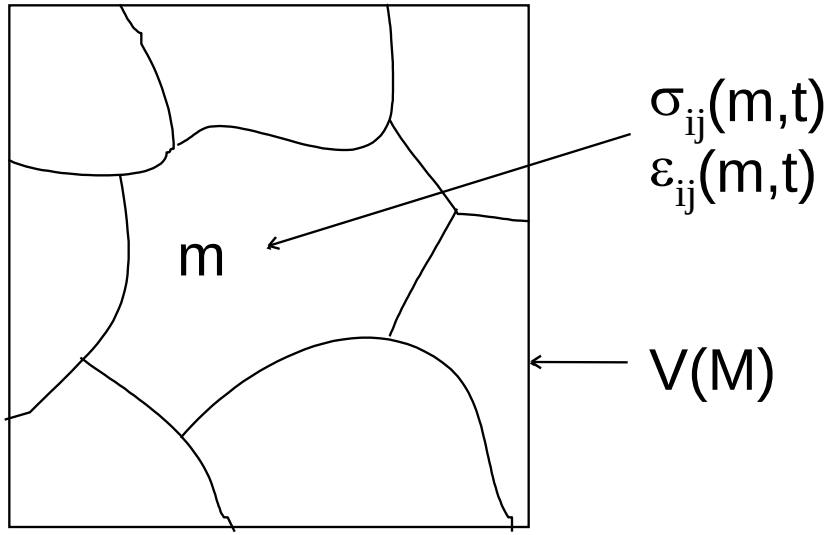

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Dang Van (continued)

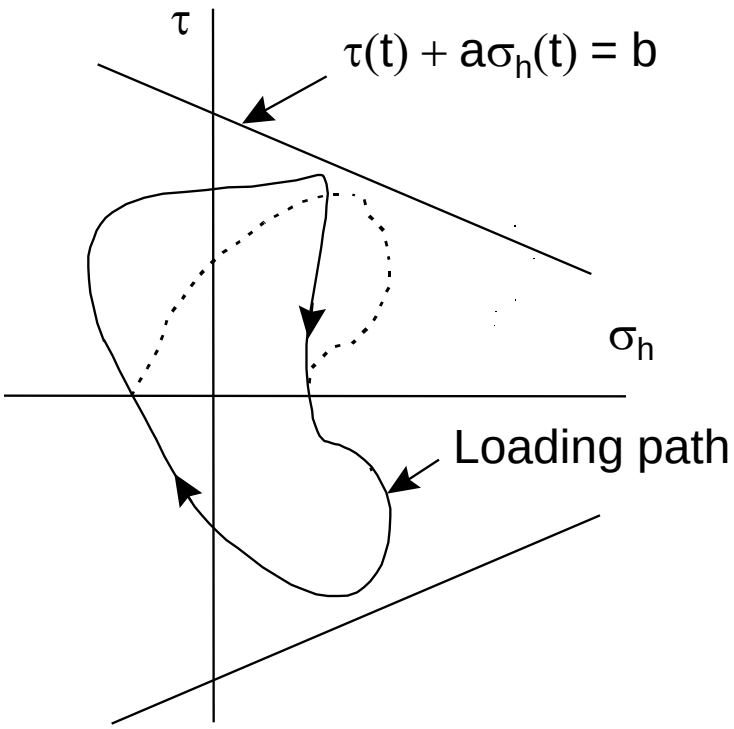

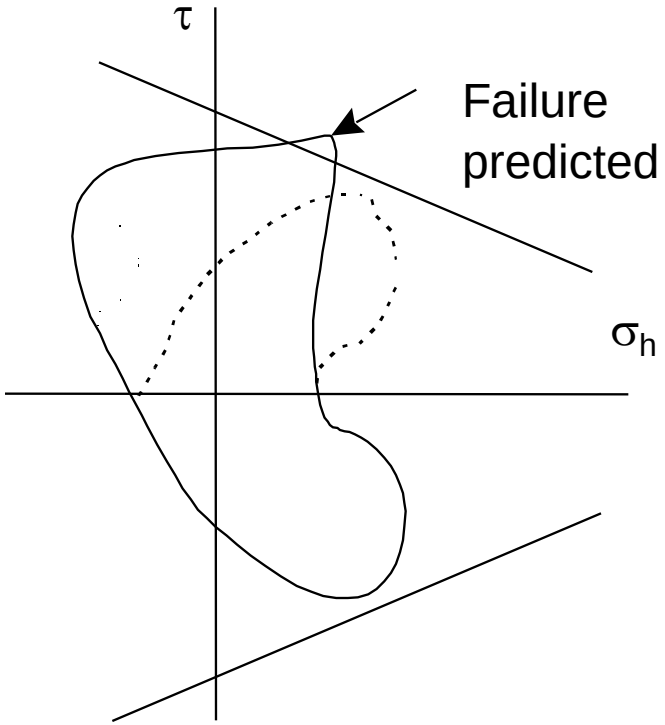

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress Based Models Summary

Sines: $$\frac{\Delta\tau_{oct}}{2} + \alpha(3\sigma_h) = \beta$$

Findley: $$\left(\frac{\Delta\tau}{2} + k\sigma_n\right)_{max} = f$$

Dang Van: $$\tau(t) + a\sigma_h(t) = b$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Strain Based Models

- Plastic Work
- Brown and Miller
- Fatemi and Socie
- Smith Watson and Topper
- Liu

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Octahedral Shear Strain

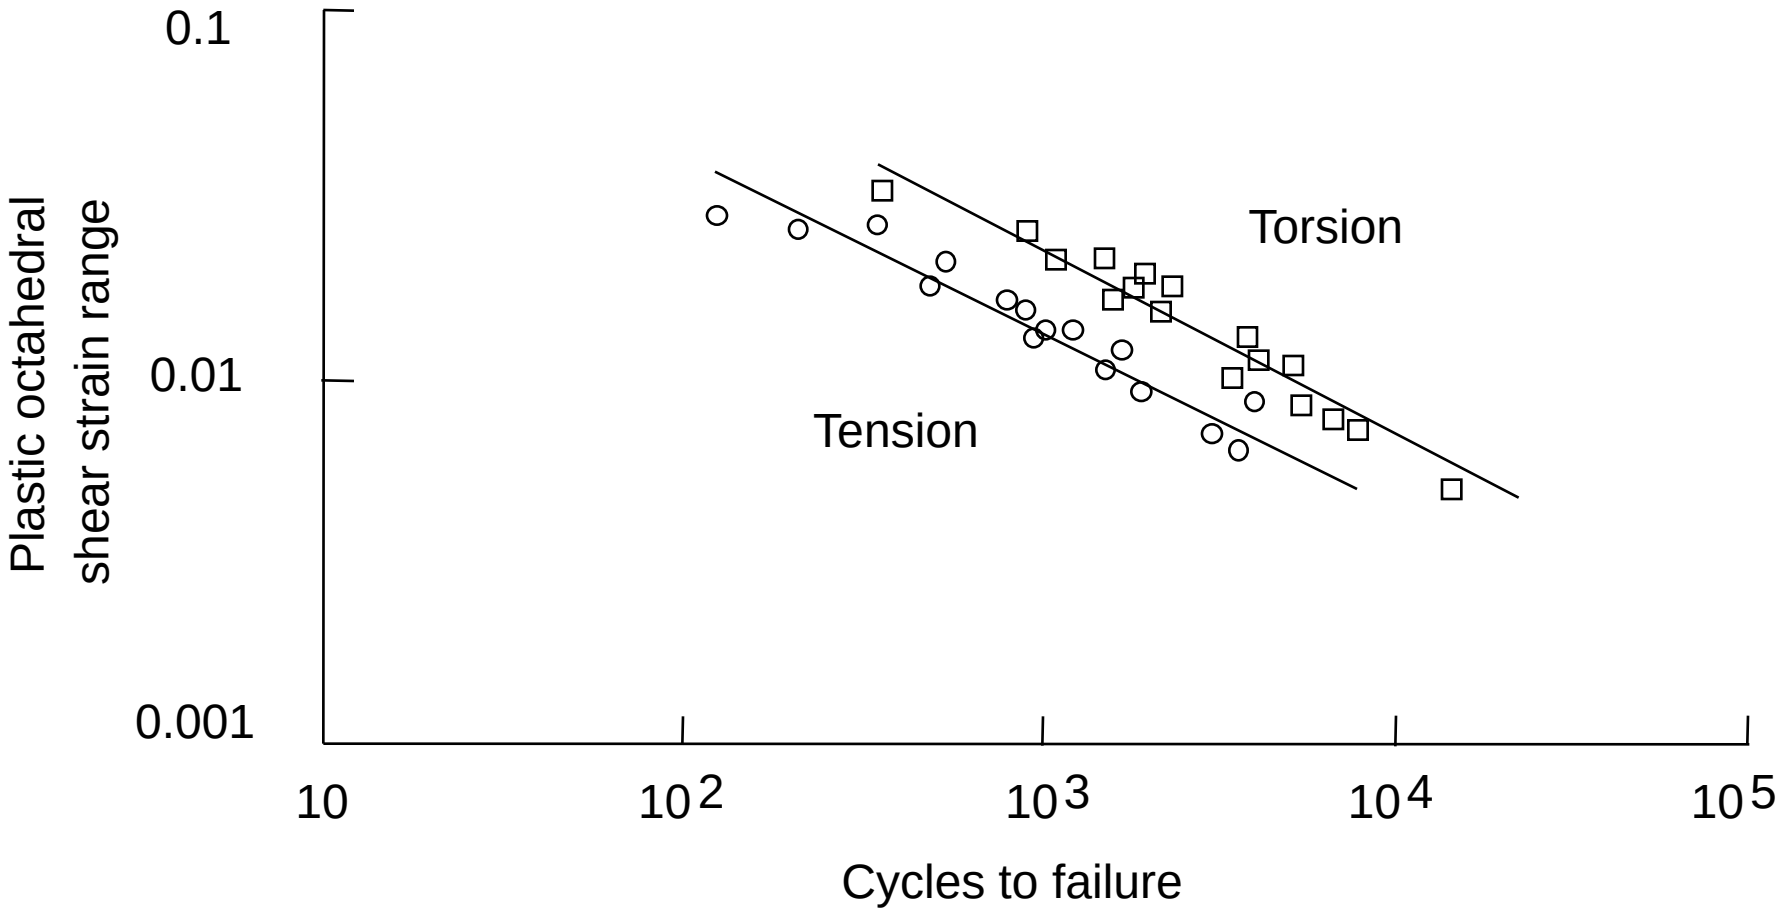

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Plastic Work

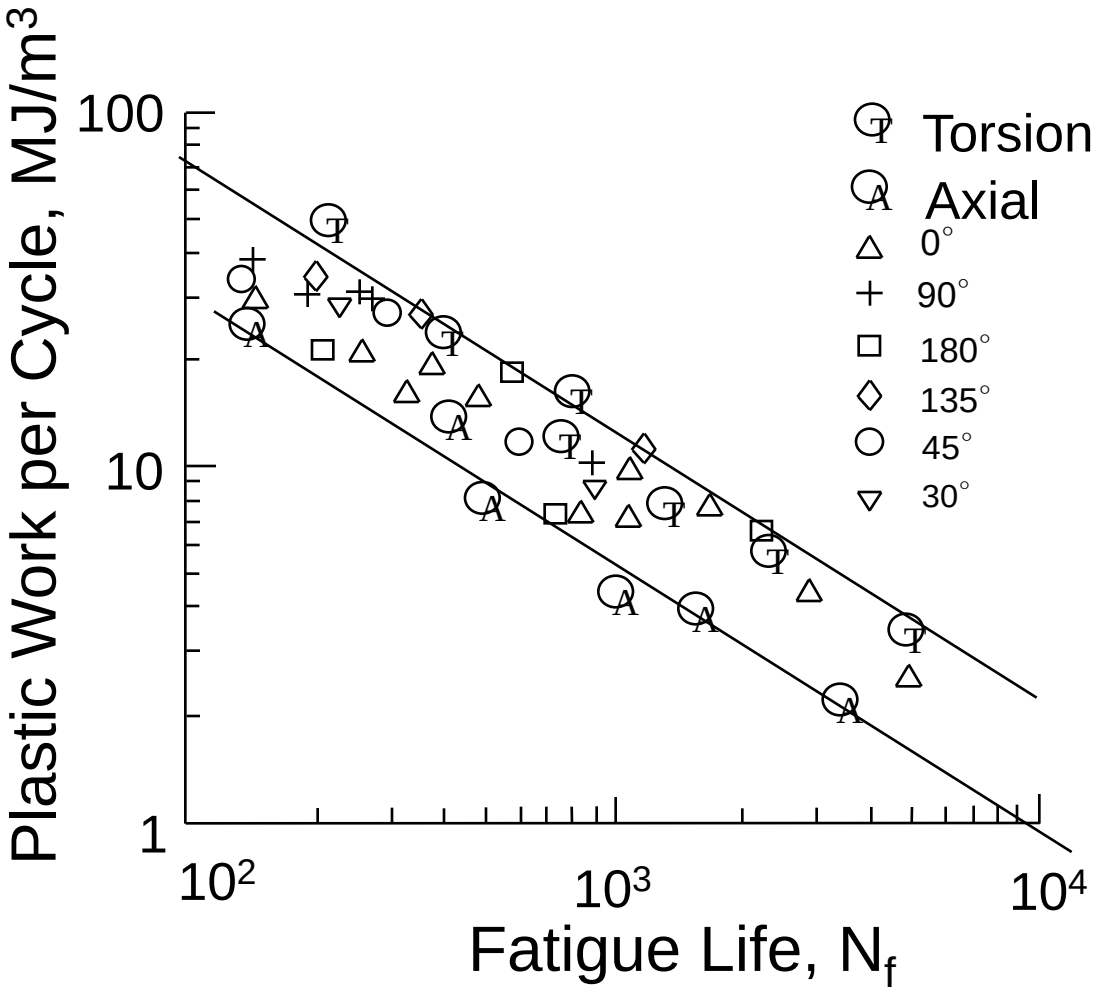

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Brown and Miller

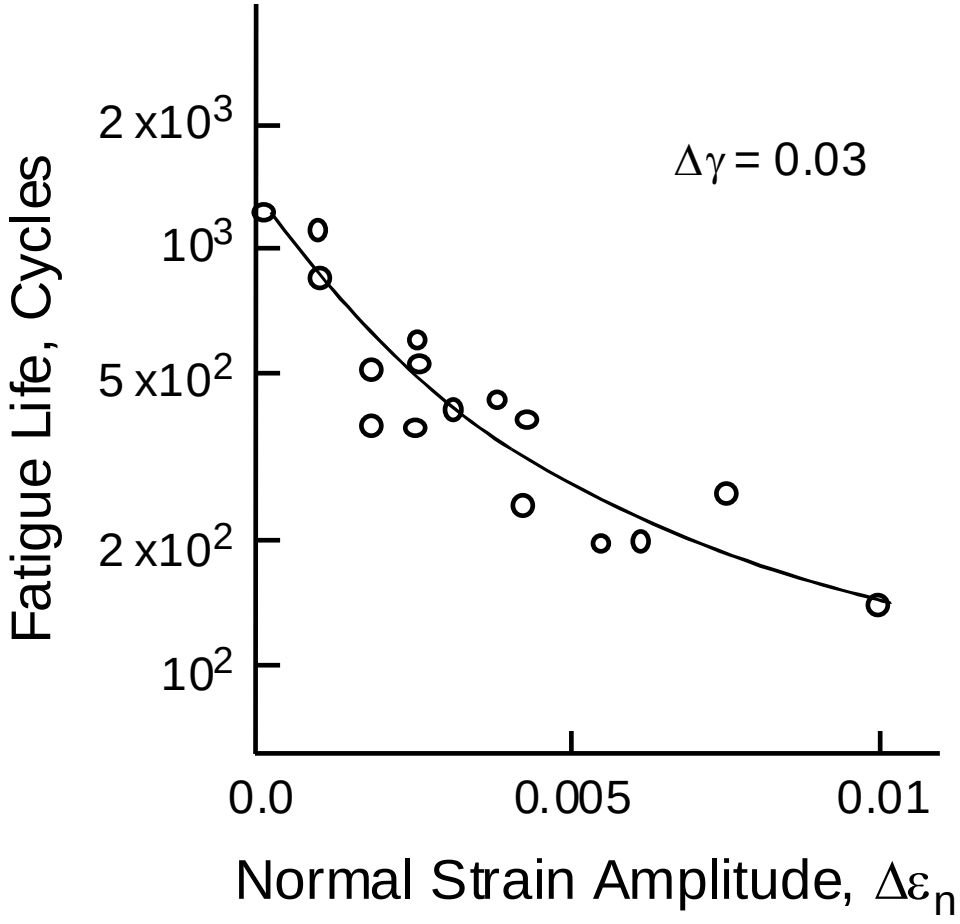

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Case A and B

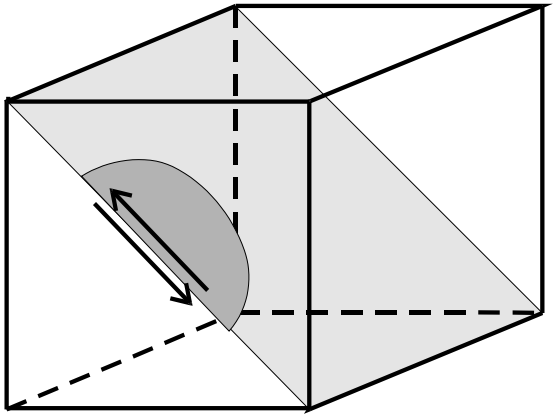

Case A

Growth along the surface

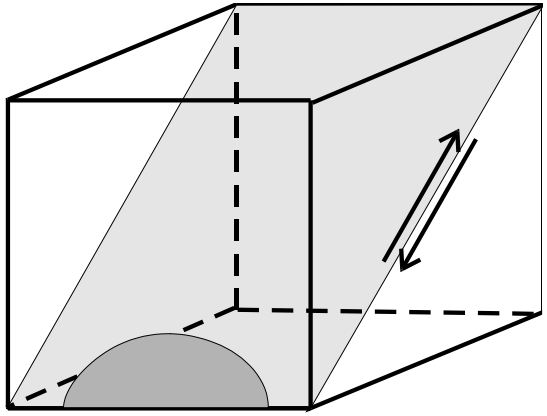

Case B

Growth into the surface

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Brown and Miller (continued)

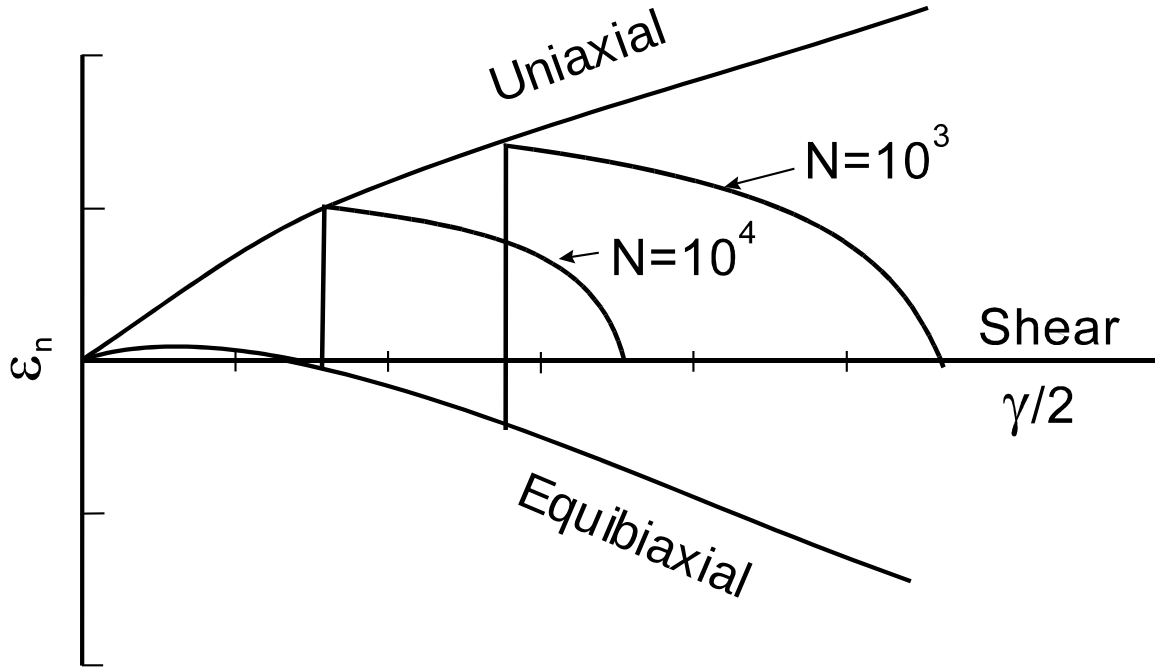

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Brown and Miller (continued)

$$\Delta\hat{\gamma} = \left(\Delta\gamma_{max}^{\alpha} + S\Delta\varepsilon_n^{\alpha}\right)^{\frac{1}{\alpha}}$$

$$\frac{\Delta\gamma_{max}}{2} + S\Delta\varepsilon_n = A\frac{\sigma_f^{'} - 2\sigma_{n,mean}}{E}(2N_f)^b + B\varepsilon_f^{'}(2N_f)^c$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatemi and Socie

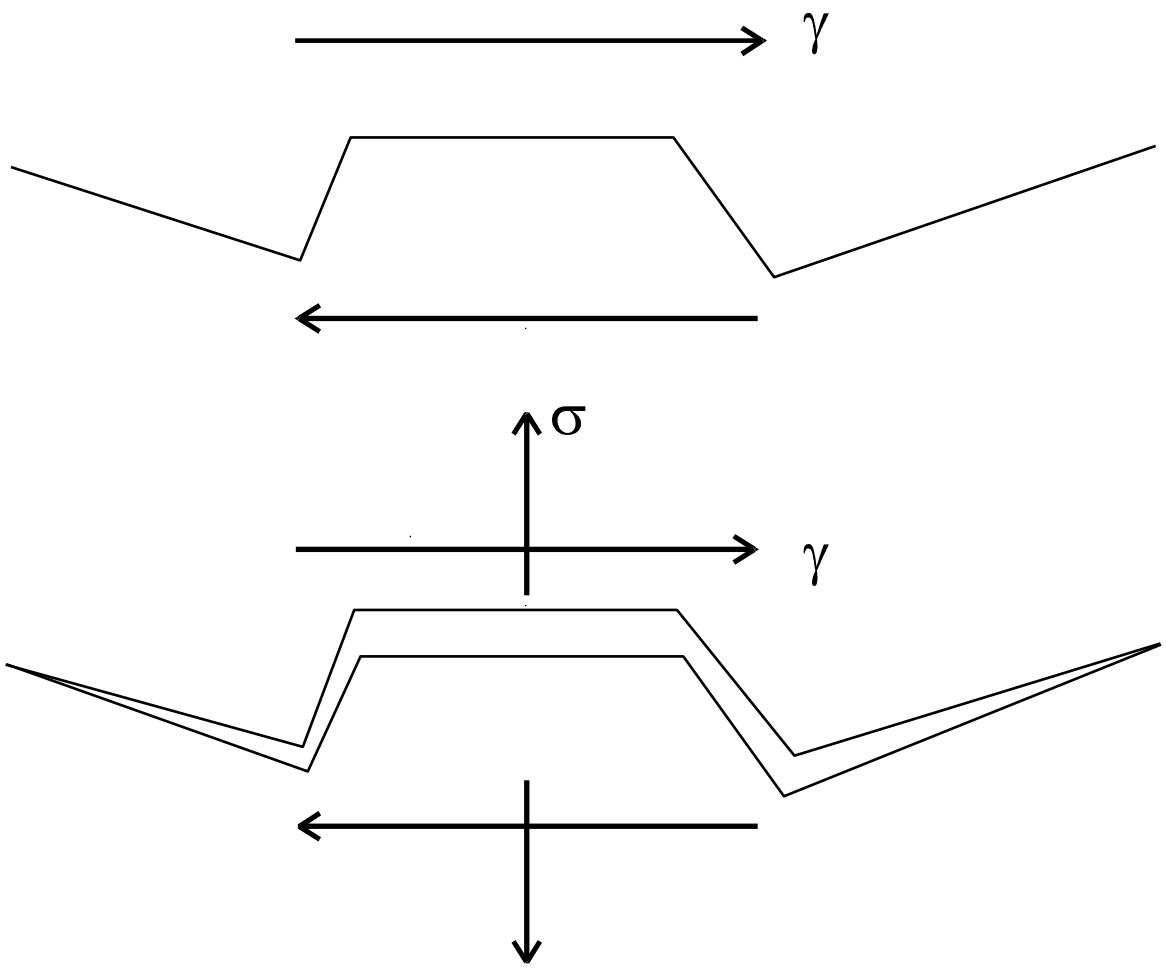

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Loading Histories

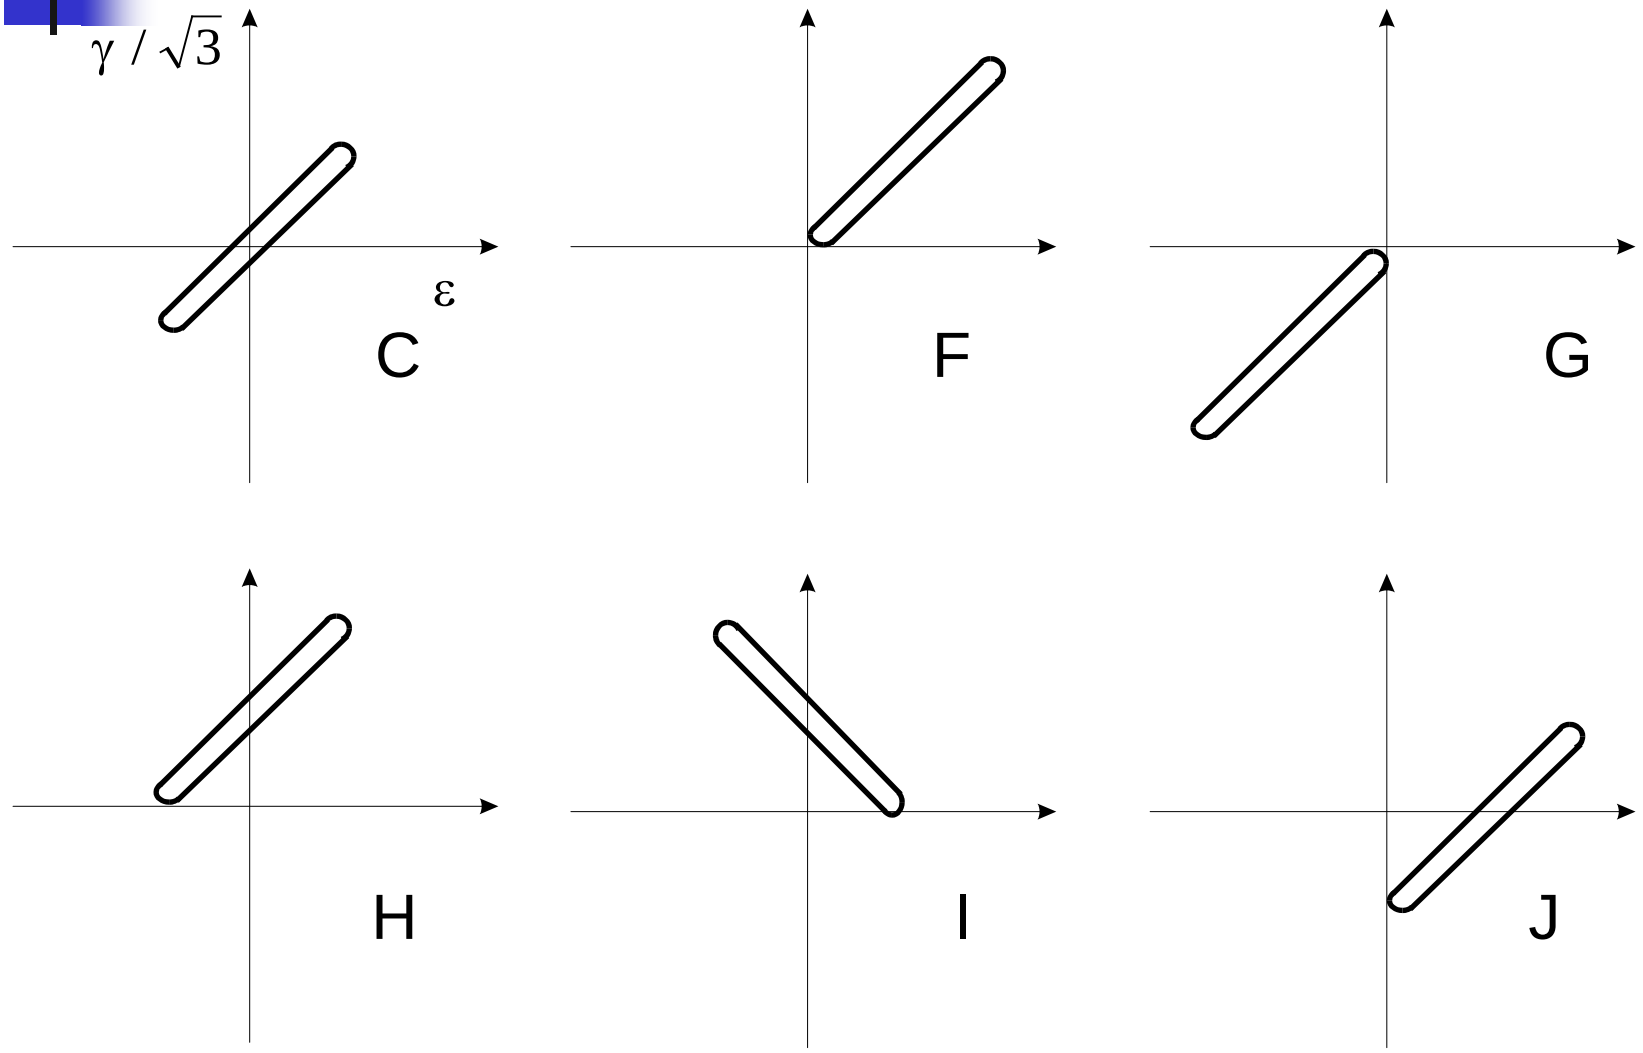

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Crack Length Observations

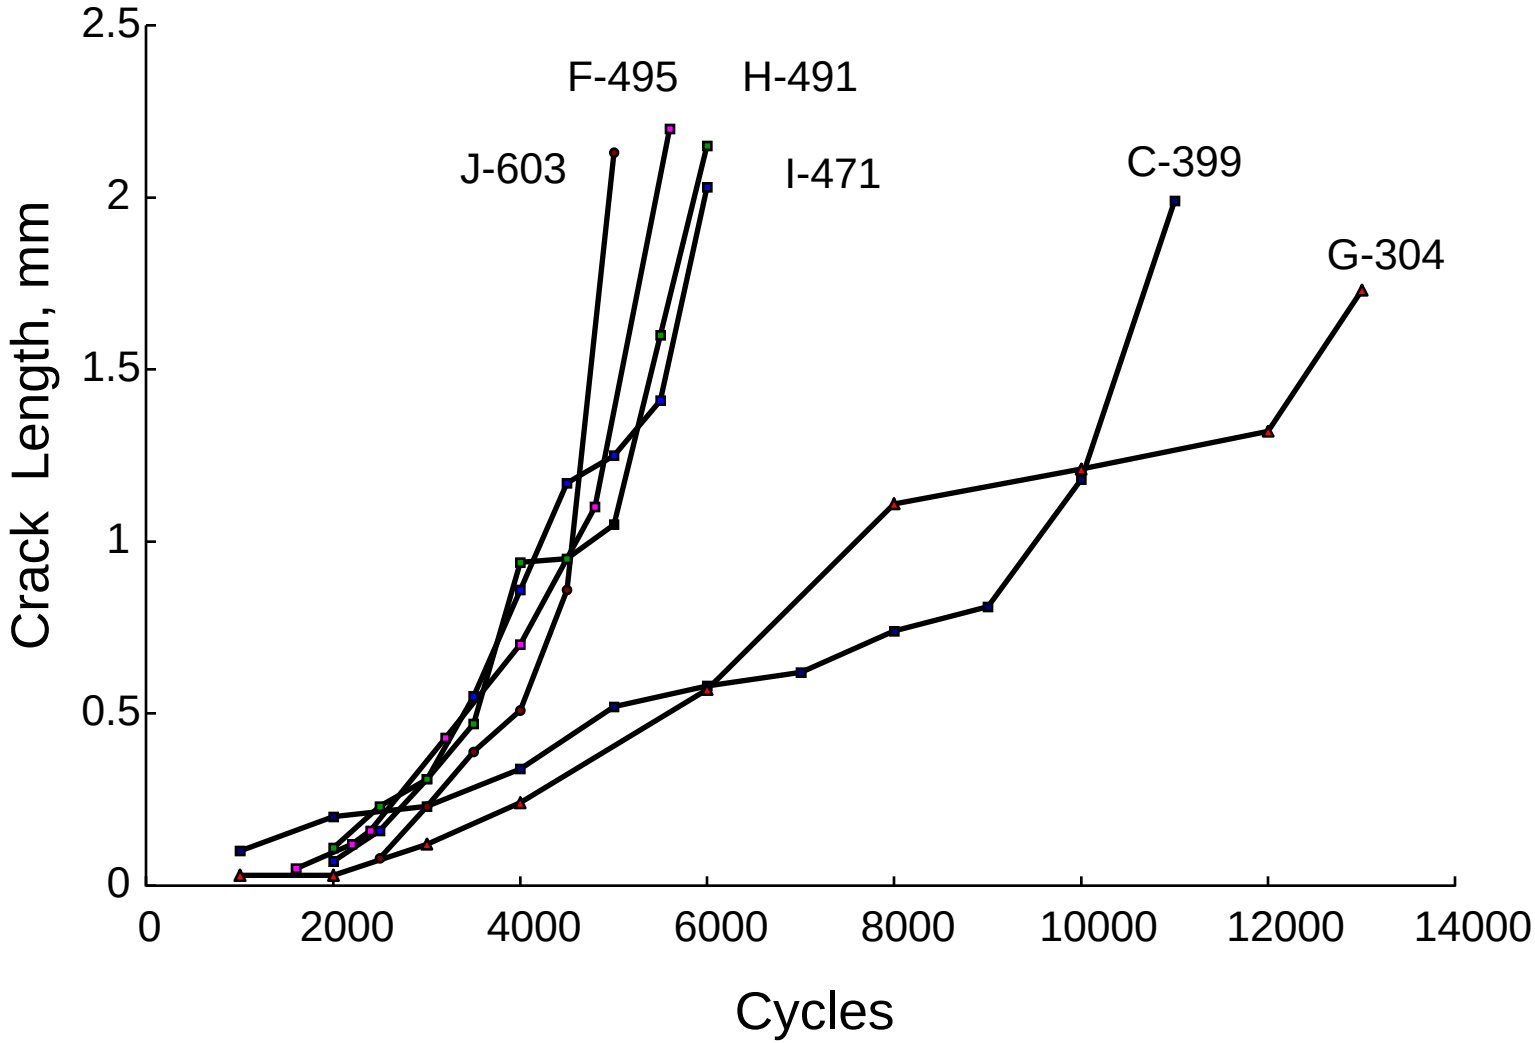

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatemi and Socie

$$\frac{\Delta\gamma}{2}\left(1+k\frac{\sigma_{n,max}}{\sigma_y}\right)=\frac{\tau_f^{'}}{G}(2N_f)^{bo}+\gamma_f^{'}(2N_f)^{co}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Smith Watson Topper

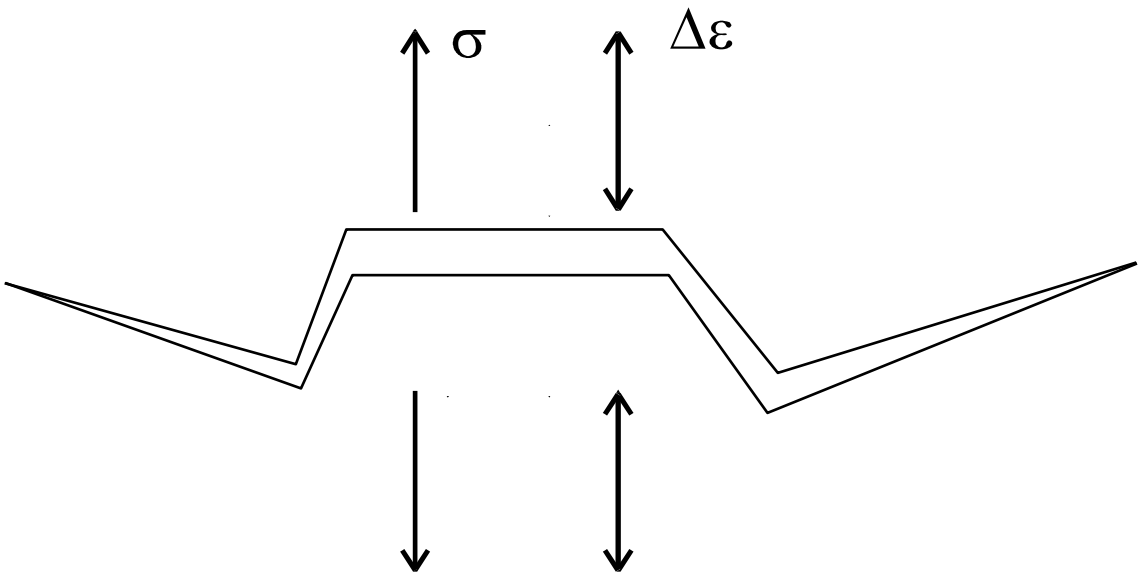

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

SWT

$$\sigma_n \frac{\Delta\varepsilon_1}{2} = \frac{\sigma_f^{'2}}{E}(2N_f)^{2b} + \sigma_f^{'}\varepsilon_f^{'}(2N_f)^{b+c}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Liu

Virtual strain energy for both mode I and mode II cracking

$$\Delta W_I = (\Delta\sigma_n \, \Delta\varepsilon_n)_{max} + (\Delta\tau \, \Delta\gamma)$$

$$\Delta W_I = 4\sigma_f' \varepsilon_f' (2N_f)^{b+c} + \frac{4\sigma_f'^2}{E}(2N_f)^{2b}$$

$$\Delta W_{II} = (\Delta\sigma_n \, \Delta\varepsilon_n) + (\Delta\tau \, \Delta\gamma)_{max}$$

$$\Delta W_{II} = 4\tau_f' \gamma_f' (2N_f)^{bo+co} + \frac{4\tau_f'^2}{G}(2N_f)^{2bo}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Torsion

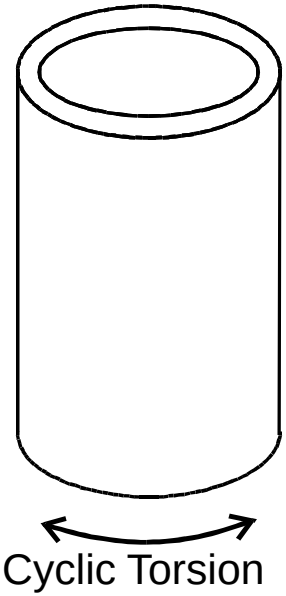

Cyclic Torsion

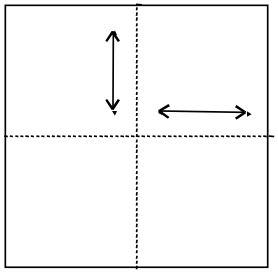

Cyclic Shear Strain

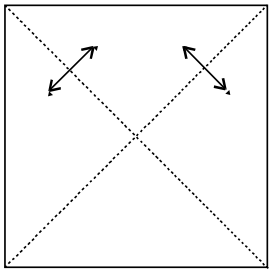

Cyclic Tensile Strain

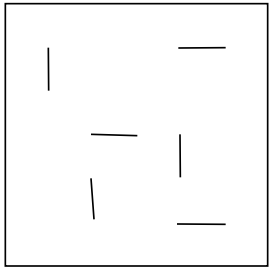

Shear Damage

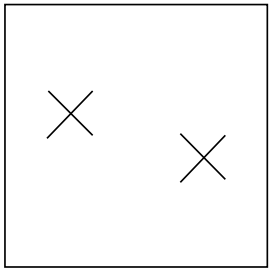

Tensile Damage

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Torsion with Static Tension

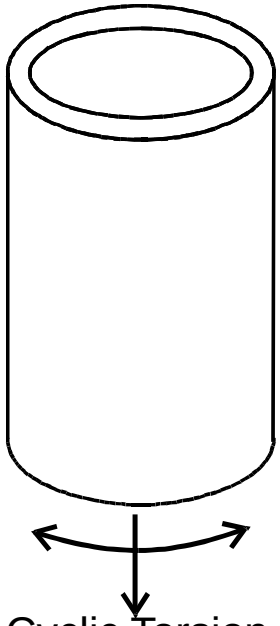

Cyclic Torsion
Static Tension

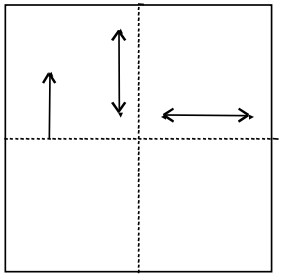

Cyclic Shear Strain

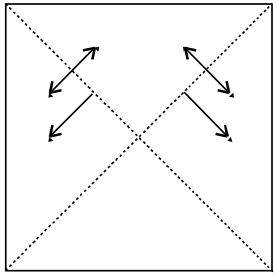

Cyclic Tensile Strain

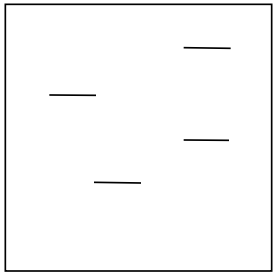

Shear Damage

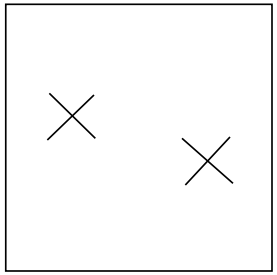

Tensile Damage

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Torsion with Compression

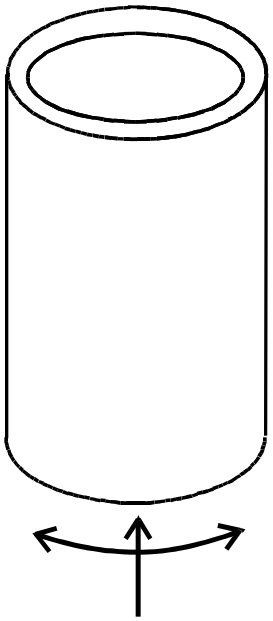

Cyclic Torsion
Static Compression

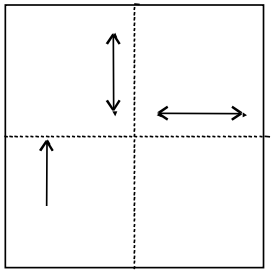

Cyclic Shear Strain

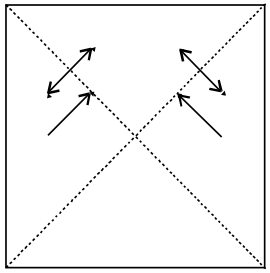

Cyclic Tensile Strain

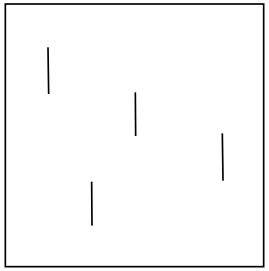

Shear Damage

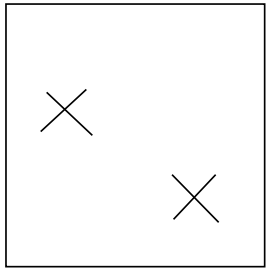

Tensile Damage

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Torsion with Tension and Compression

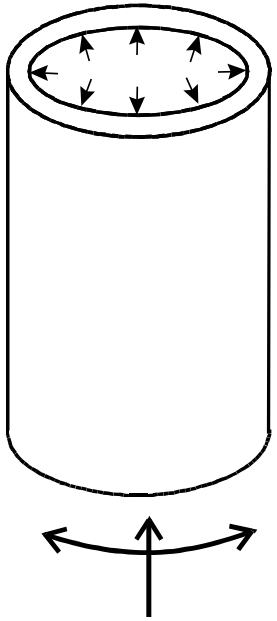

Cyclic Torsion
Static Compression
Hoop Tension

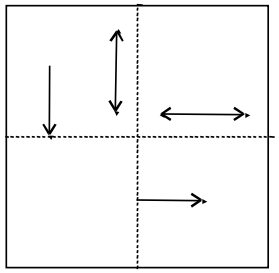

Cyclic Shear Strain

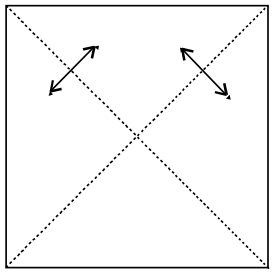

Cyclic Tensile Strain

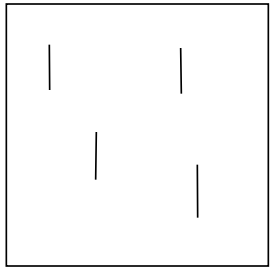

Shear Damage

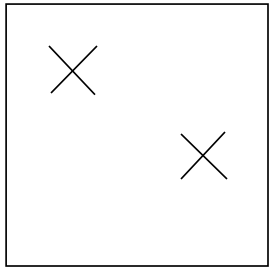

Tensile Damage

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Test Results

Load Case	$\Delta\gamma/2$	σ_{hoop} MPa	σ_{axial} MPa	N_f
Torsion	0.0054	0	0	45,200
with tension	0.0054	0	450	10,300
with compression	0.0054	0	-500	50,000
with tension and compression	0.0054	450	-500	11,200

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

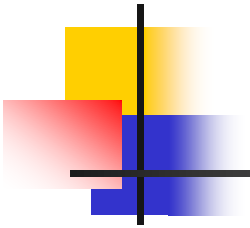

Conclusions

- All critical plane models correctly predict these results
- Hydrostatic stress models can not predict these results

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Loading History

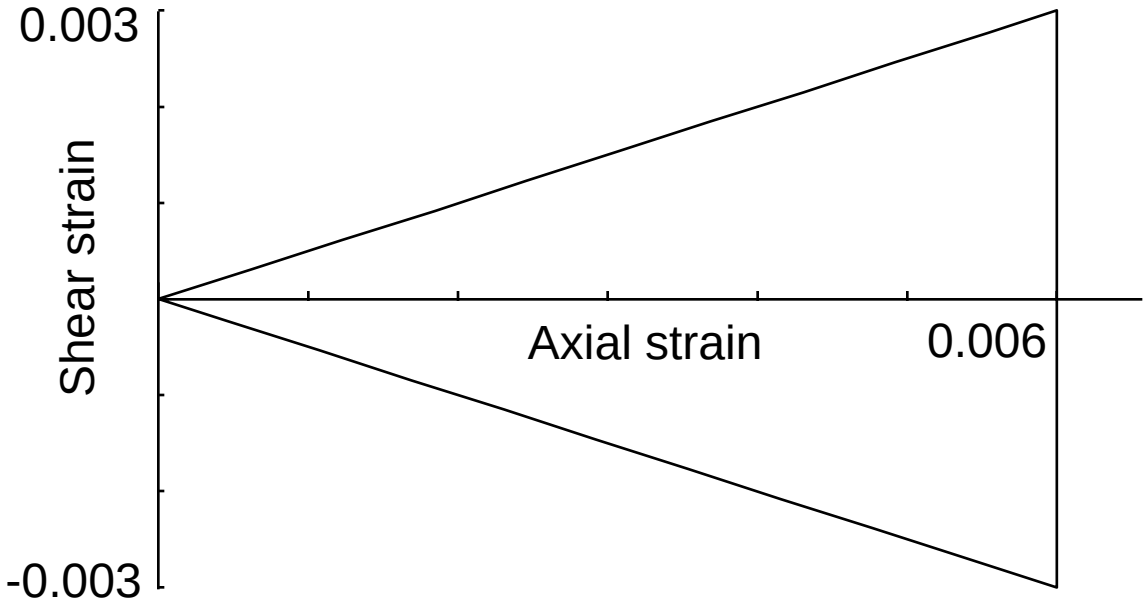

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Model Comparison

Summary of calculated fatigue lives

Model	Equation	Life
Epsilon	6.5	14,060
Garud	6.7	5,210
Ellyin	6.17	4,450
Brown-Miller	6.22	3,980
SWT	6.24	9,930
Liu I	6.41	4,280
Liu II	6.42	5,420
Chu	6.37	3,040
Gamma		26,775
Fatemi-Socie	6.23	10,350
Glinka	6.39	33,220

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Strain Based Models Summary

- Two separate models are needed, one for tensile growth and one for shear growth
- Cyclic plasticity governs stress and strain ranges
- Mean stress effects are a result of crack closure on the critical plane

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Separate Tensile and Shear Models

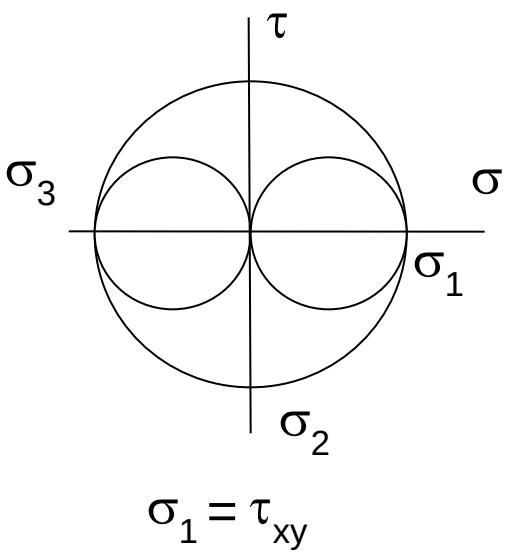

$\sigma_1 = \tau_{xy}$

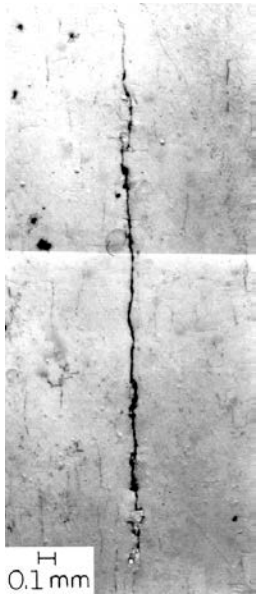

Inconel

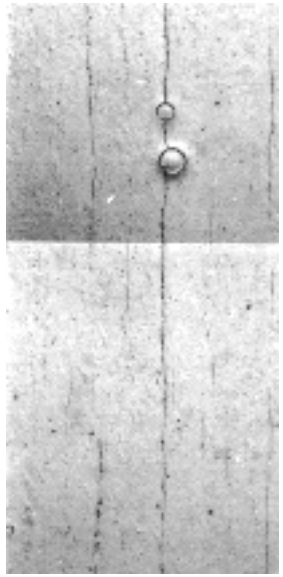

1045 steel

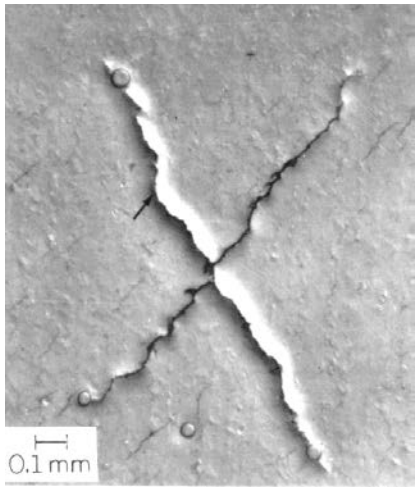

stainless steel

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Cyclic Plasticity

$\Delta\varepsilon$

$\Delta\gamma$

$\Delta\varepsilon^p$

$\Delta\gamma^p$

$\Delta\varepsilon\Delta\sigma$

$\Delta\gamma\Delta\tau$

$\Delta\varepsilon^p\Delta\sigma$

$\Delta\gamma^p\Delta\tau$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mean Stresses

$$\Delta\varepsilon_{eq} = \frac{\sigma_f' - \sigma_{mean}}{E}(2N_f)^b + \varepsilon_f'(2N_f)^c$$

$$\frac{\Delta\gamma_{max}}{2} + S\Delta\varepsilon_n = (1.3 + 0.7S)\frac{\sigma_f' - 2\sigma_n}{E}(2N_f)^b + (1.5 + 0.5S)\varepsilon_f'(2N_f)^c$$

$$\frac{\Delta\gamma}{2}\left(1 + k\frac{\sigma_{n,max}}{\sigma_y}\right) = \frac{\tau_f'}{G}(2N_f)^{bo} + \gamma_f'(2N_f)^{co}$$

$$\sigma_n\frac{\Delta\varepsilon_1}{2} = \frac{\sigma_f'^2}{E}(2N_f)^{2b} + \sigma_f'\varepsilon_f'(2N_f)^{b+c}$$

$$\Delta W_I = \left[(\Delta\sigma_n\Delta\varepsilon_n)_{max} + (\Delta\tau\Delta\gamma)\right]\left(\frac{2}{1-R}\right)$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fracture Mechanics Models

- Mode I growth
- Torsion
- Mode II growth
- Mode III growth

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode I, Mode II, and Mode III

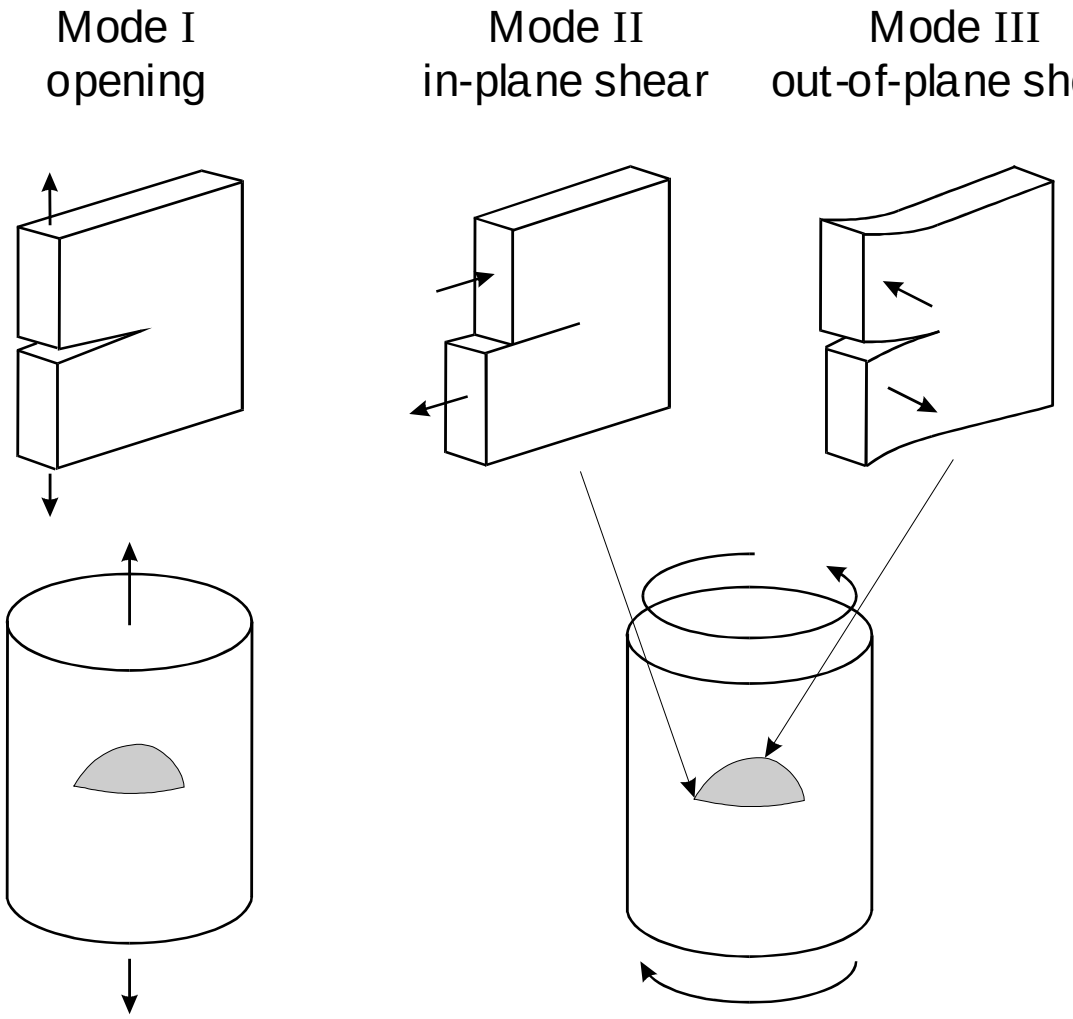

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode I and Mode II Surface Cracks

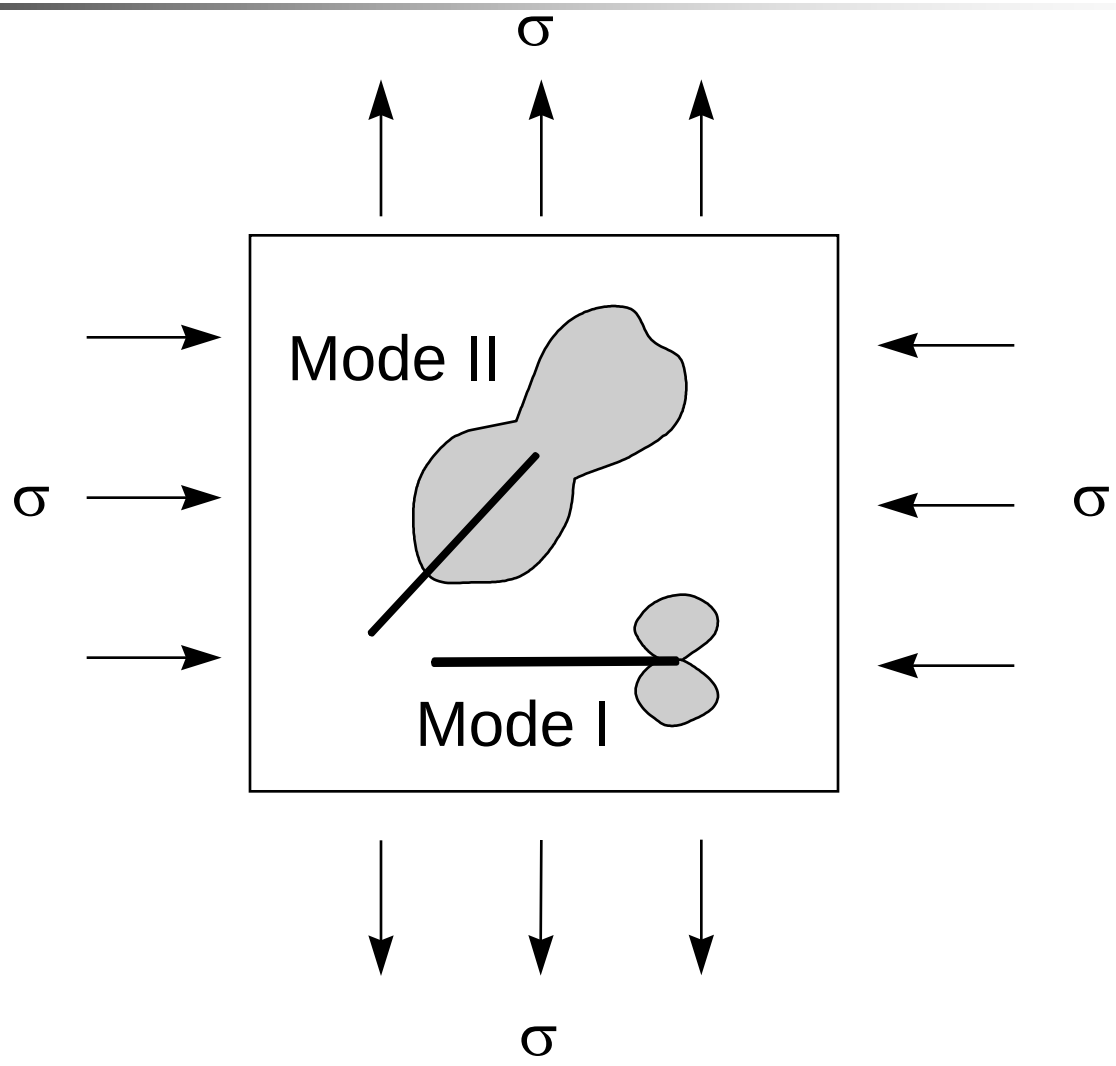

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Biaxial Mode I Growth

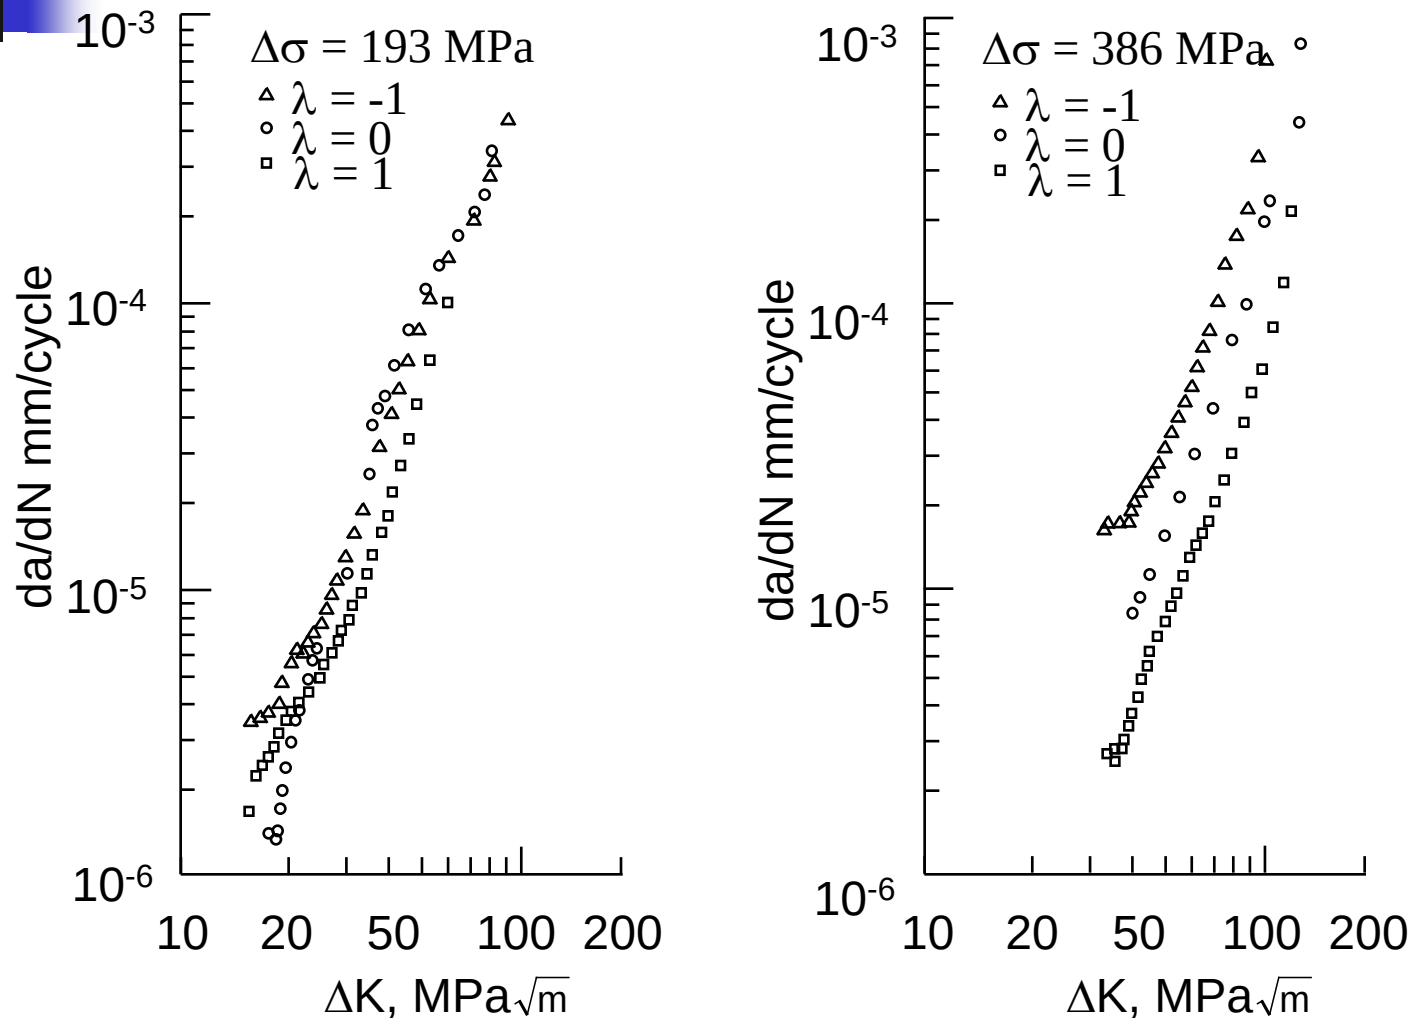

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Surface Cracks in Torsion

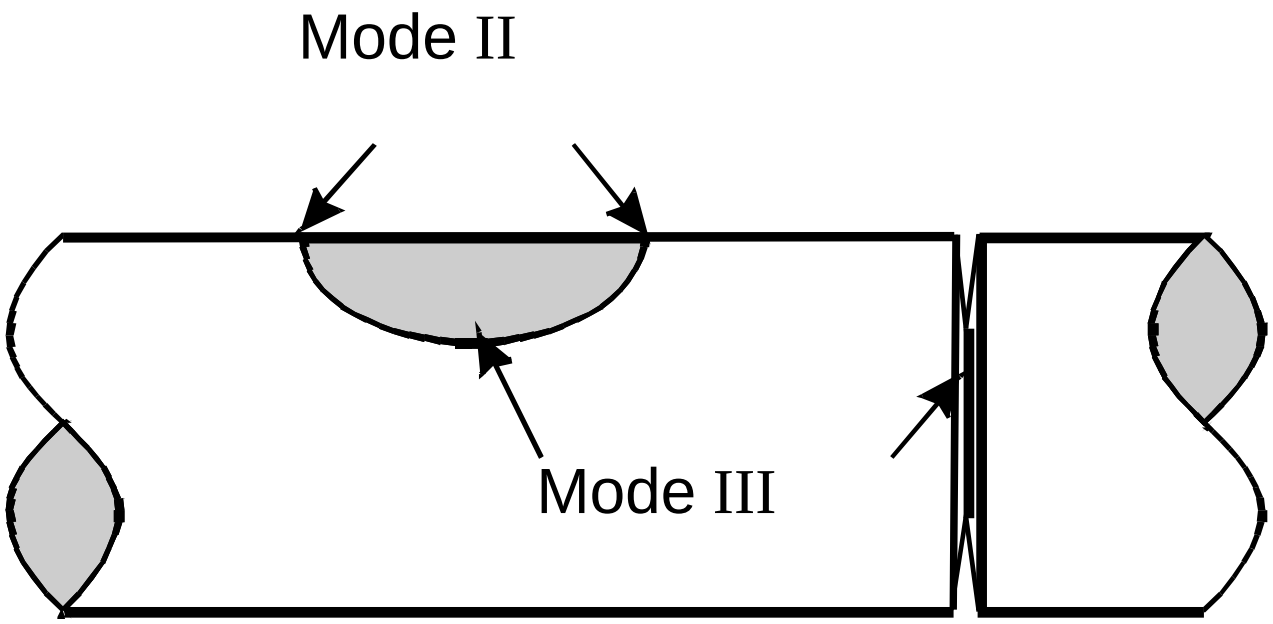

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Failure Modes in Torsion

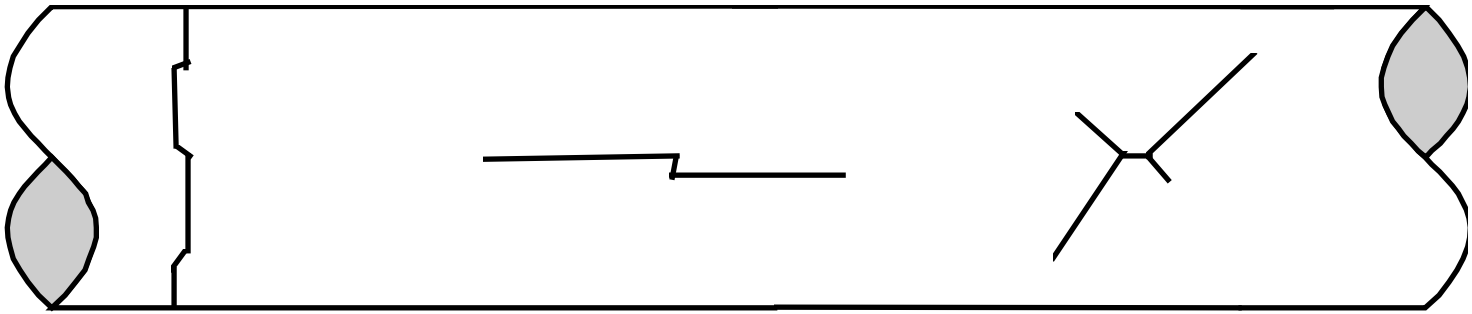

Transverse Longitudinal Spiral

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fracture Mechanism Map

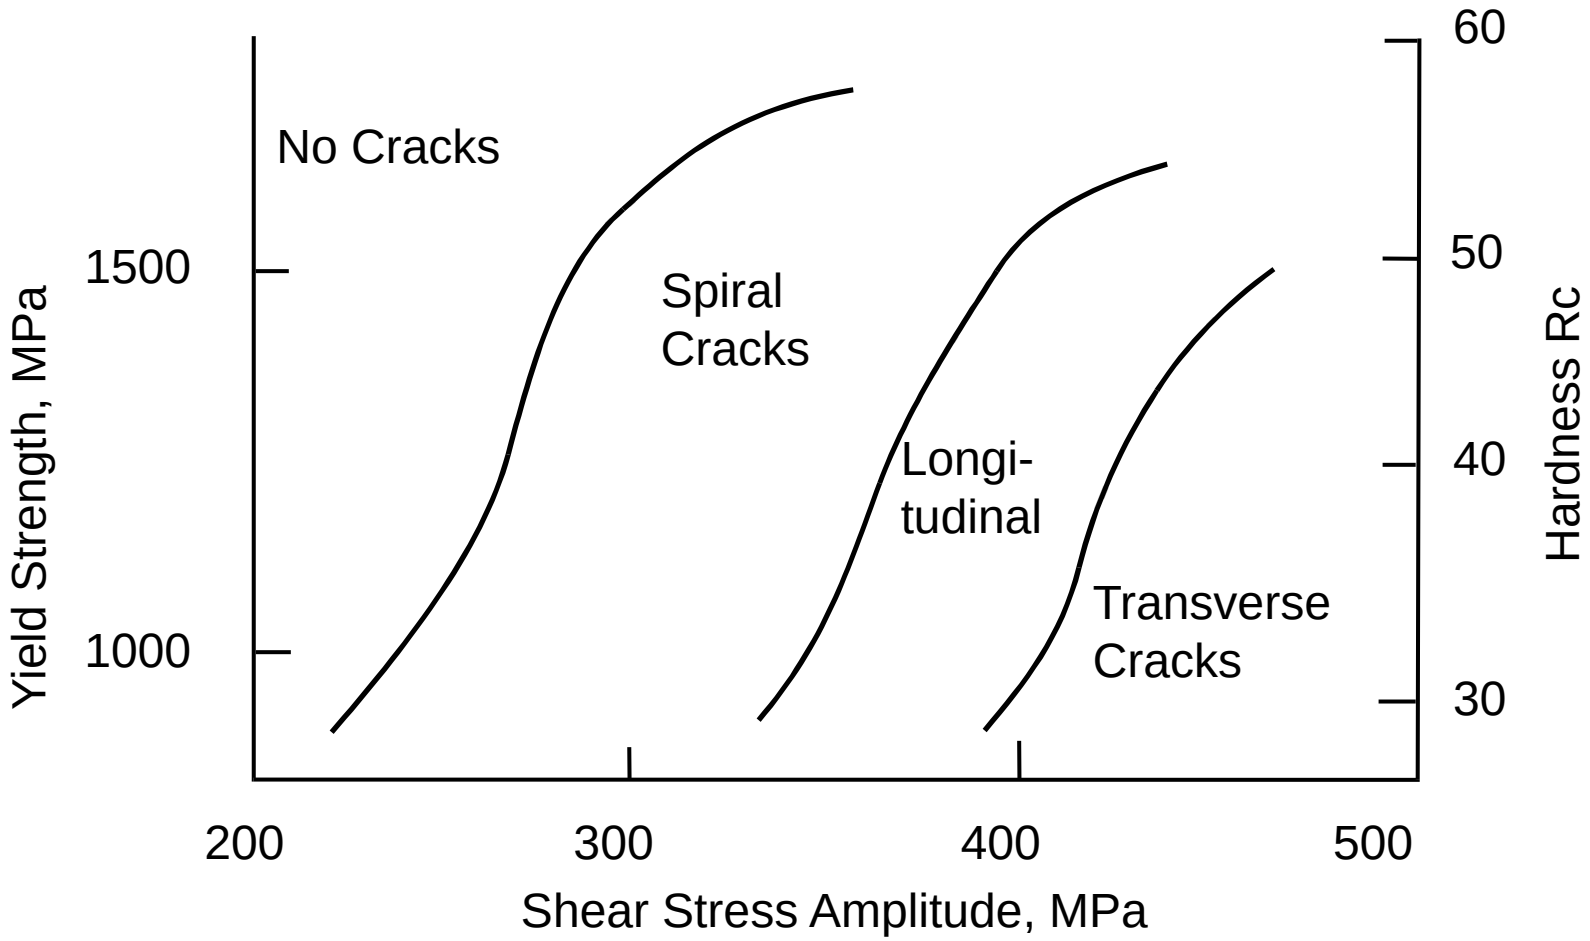

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode I and Mode III Growth

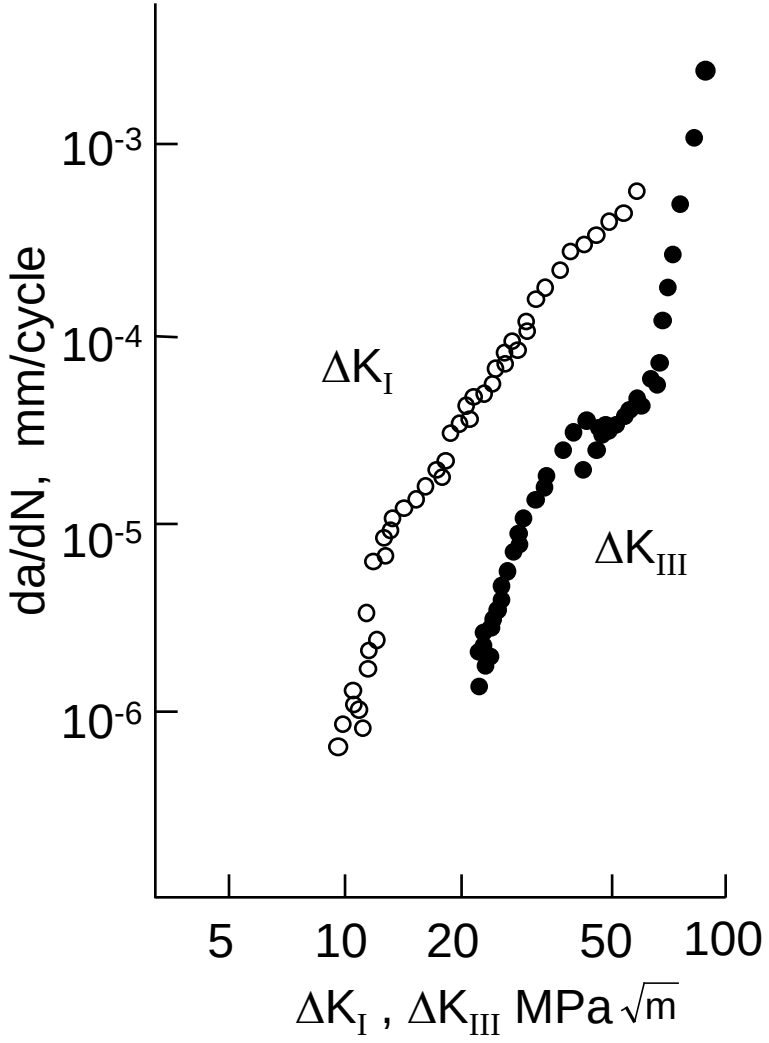

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode I and Mode II Growth

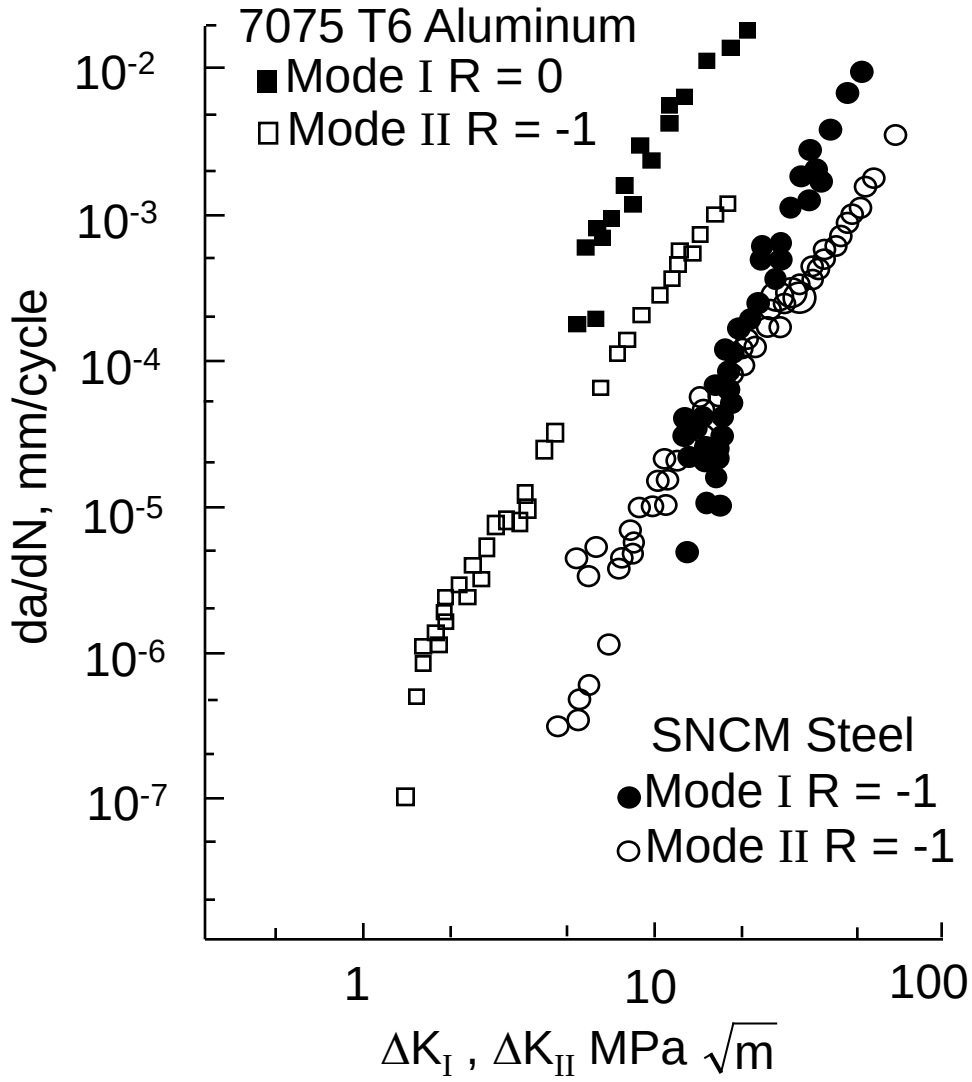

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fracture Mechanics Models

$$\frac{da}{dN} = C\left(\Delta K_{eq}\right)^m$$

$$\Delta K_{eq} = \left[\Delta K_I^4 + 8\Delta K_{II}^4 + 8\Delta K_{III}^4 / (1-\nu)\right]^{0.25}$$

$$\Delta K_{eq} = \left[\Delta K_I^2 + \Delta K_{II}^2 + (1+\nu)\Delta K_{III}^2\right]^{0.5}$$

$$\Delta K_{eq} = \left[\Delta K_I^2 + \Delta K_I \Delta K_{II} + \Delta K_{II}^2\right]^{0.5}$$

$$\Delta K_{eq}(\varepsilon) = \left[(F_{II}\frac{E}{2(1+\nu)}\Delta\gamma)^2 + (F_I E \Delta\varepsilon)^2 \right]^{0.5} \sqrt{\pi a}$$

$$\Delta K_{eq}(\varepsilon) = FG\Delta\gamma\left(1 + k\frac{\sigma_{n,max}}{\sigma_{ys}}\right)\sqrt{\pi a}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fracture Surfaces

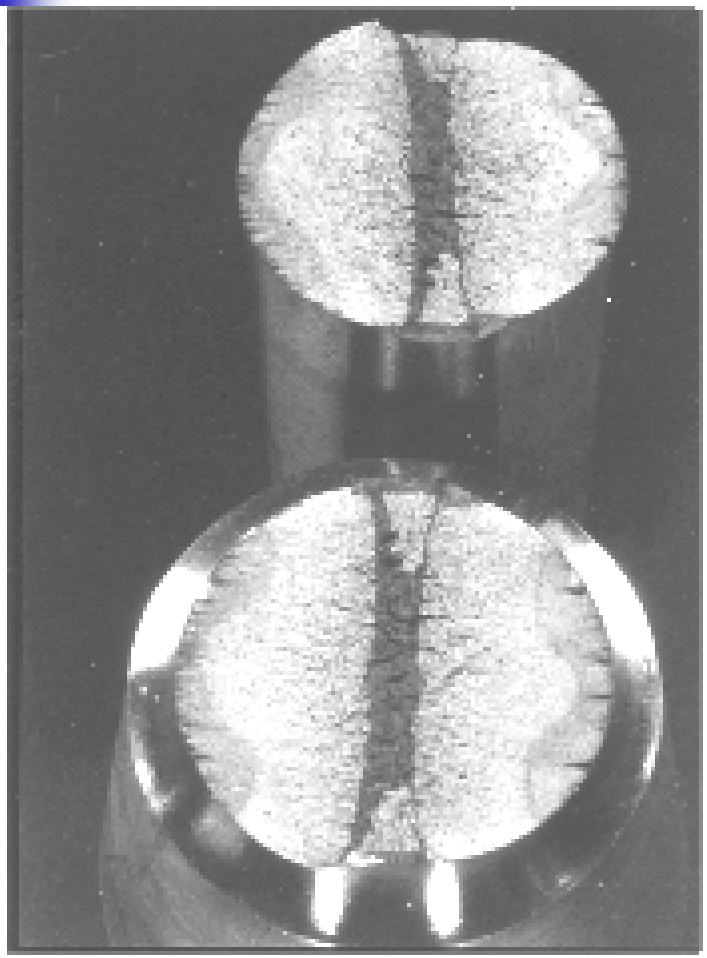

Bending

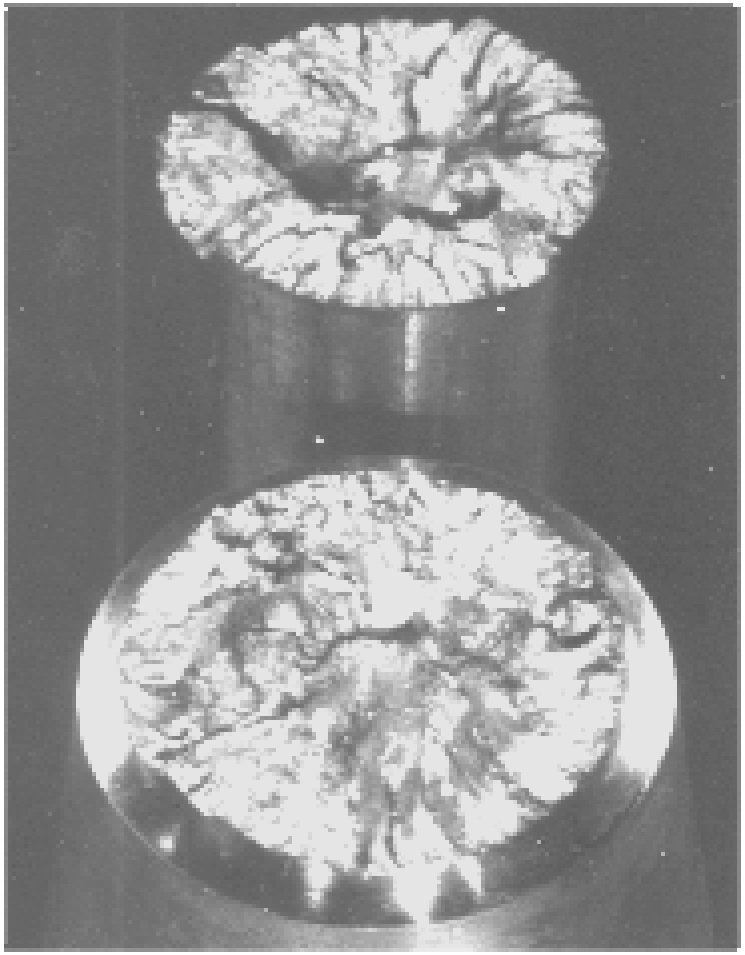

Torsion

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Mode III Growth

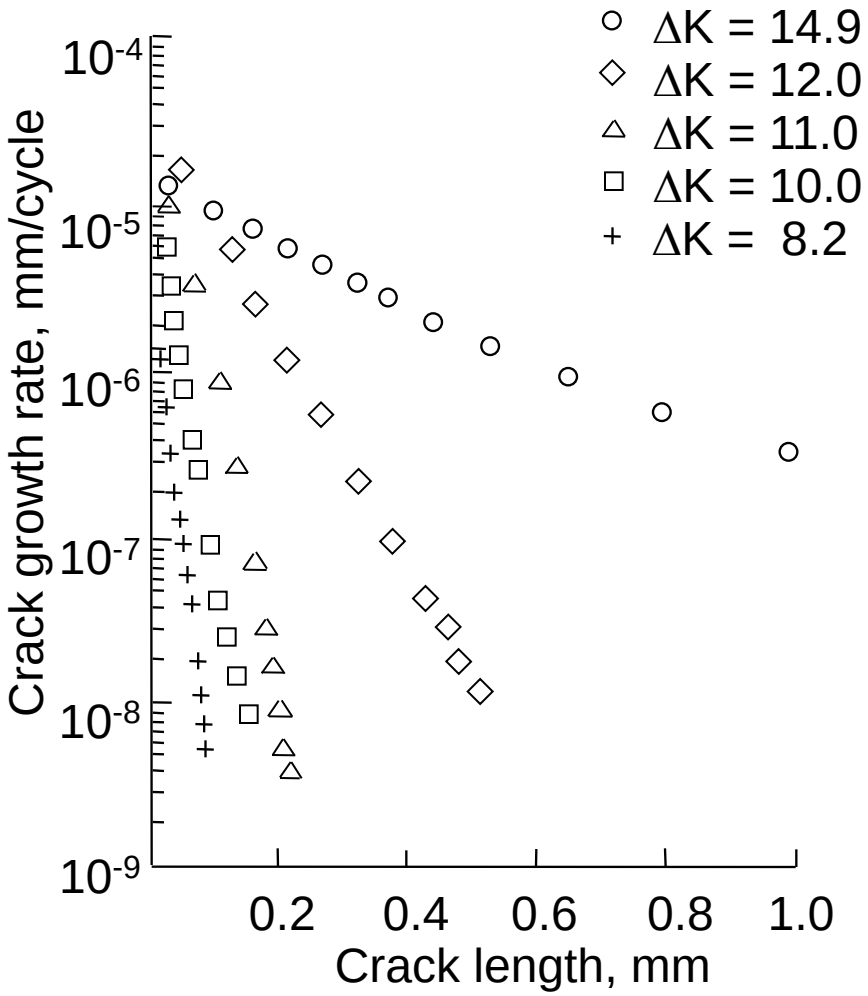

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fracture Mechanics Models Summary

- Multiaxial loading has little effect in Mode I
- Crack closure makes Mode II and Mode III calculations difficult

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Nonproportional Loading

- In and Out-of-phase loading
- Nonproportional cyclic hardening
- Variable amplitude

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

In and Out-of-Phase Loading

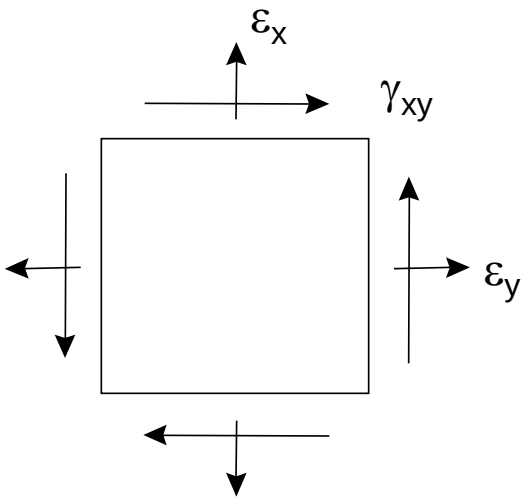

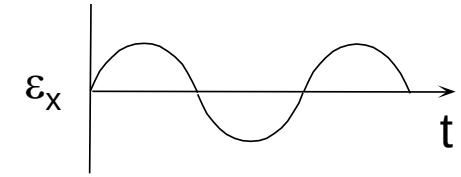

$$\varepsilon_x = \varepsilon_o \sin(\omega t)$$

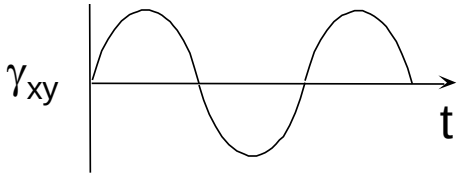

$$\gamma_{xy} = (1+\nu)\varepsilon_o \sin(\omega t)$$

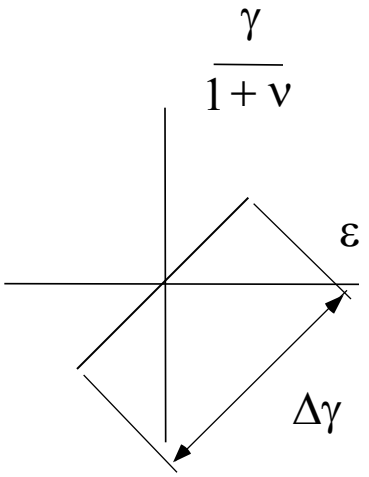

In-phase

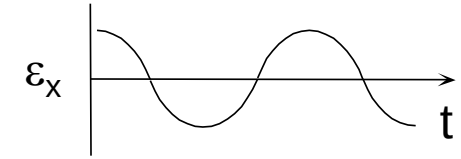

$$\varepsilon_x = \varepsilon_o \cos(\omega t)$$

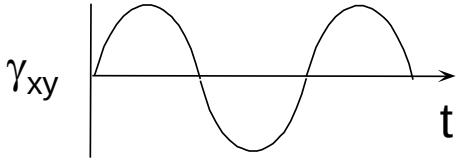

$$\gamma_{xy} = (1+\nu)\varepsilon_o \sin(\omega t)$$

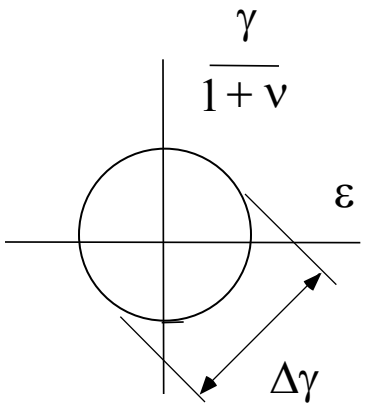

Out-of-phase

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

In-Phase and Out-of-Phase

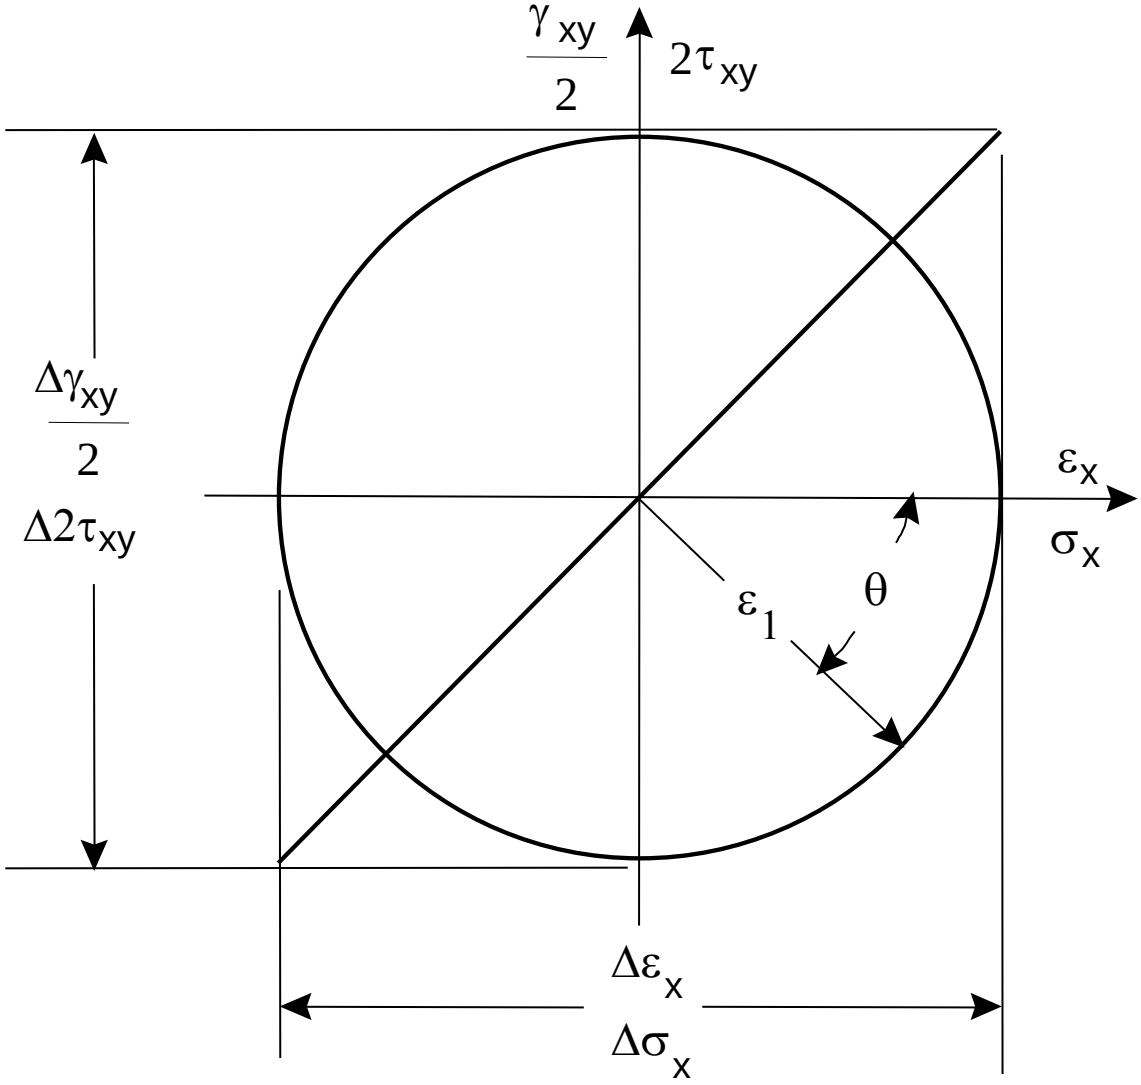

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Loading Histories

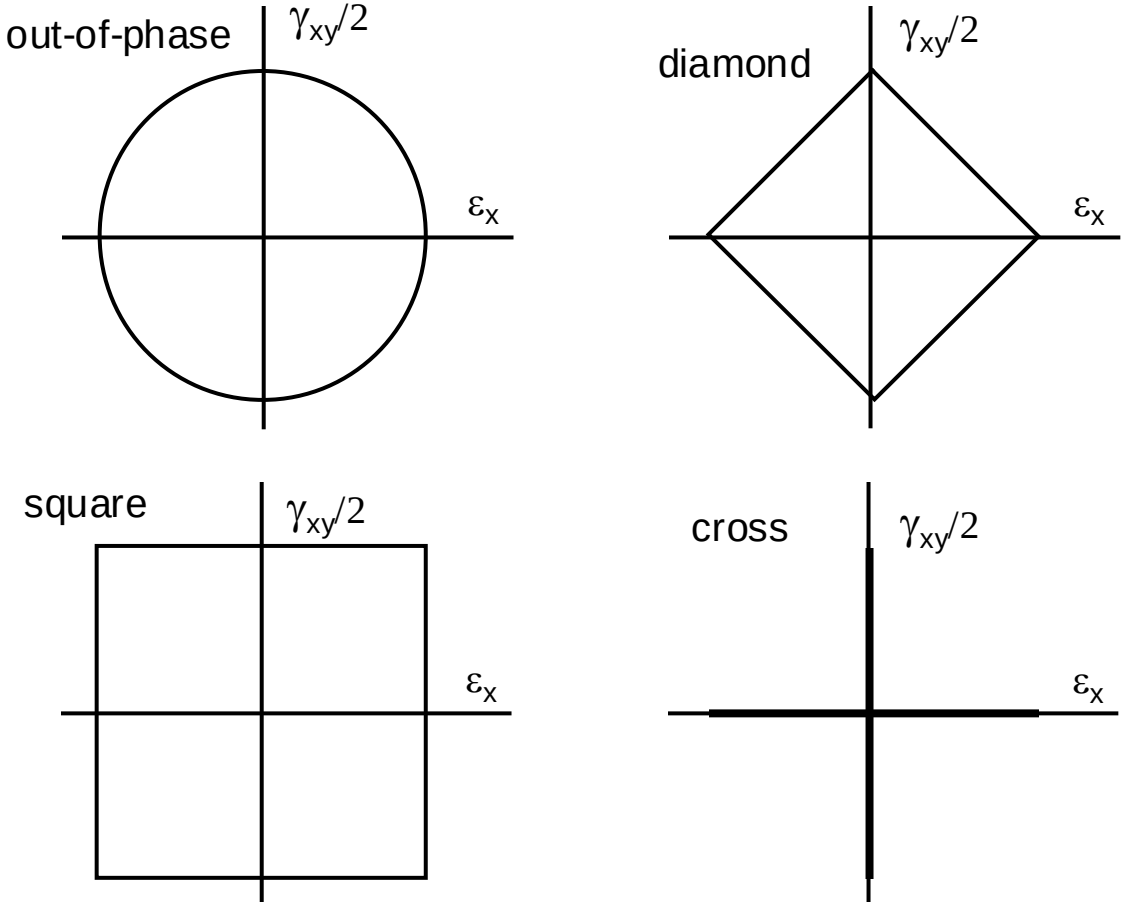

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Loading Histories

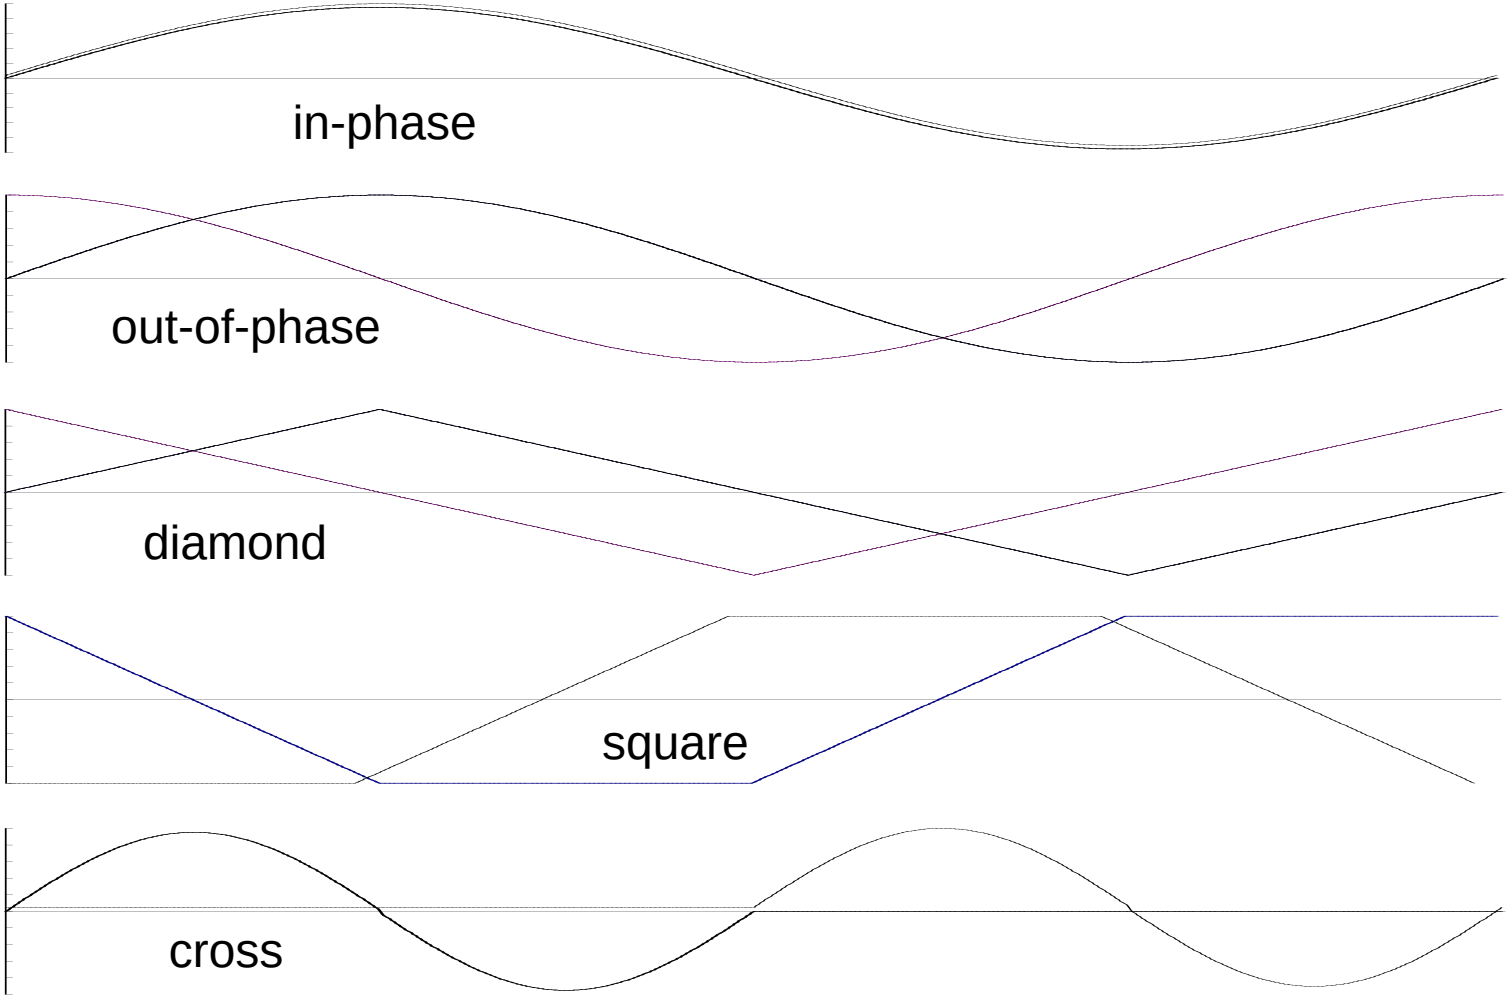

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Findley Model Results

	$\Delta\tau/2$ MPa	$\sigma_{n,max}$ MPa	$\Delta\tau/2 + 0.3\ \sigma_{n,max}$	N/N_{ip}
in-phase	353	250	428	1.0
90° out-of-phase	250	500	400	2.0
diamond	250	500	400	2.0
square	353	603	534	0.11
cross - tension cycle	250	250	325	16
cross - torsion cycle	250	0	250	216

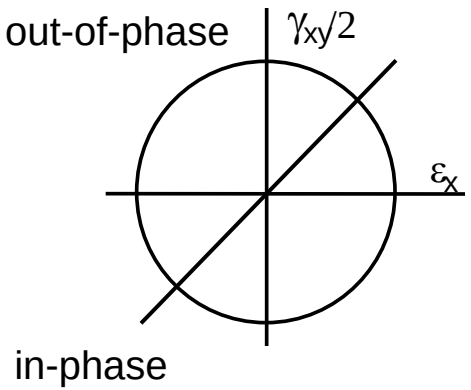

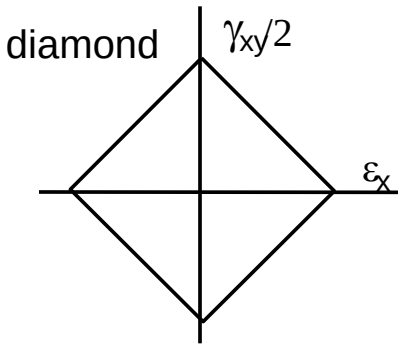

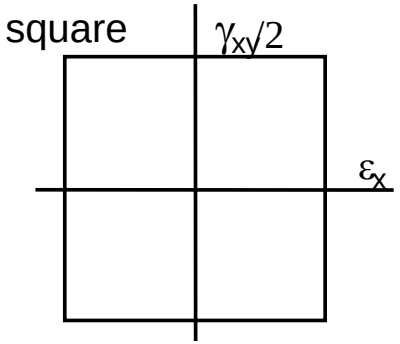

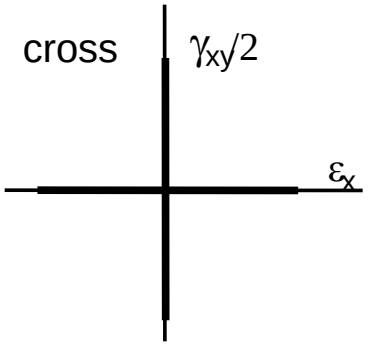

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Nonproportional Hardening

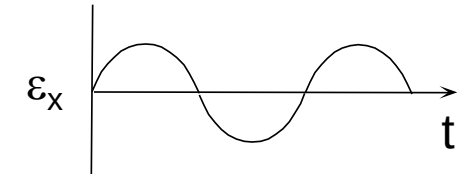

$$\varepsilon_x = \varepsilon_o \sin(\omega t)$$

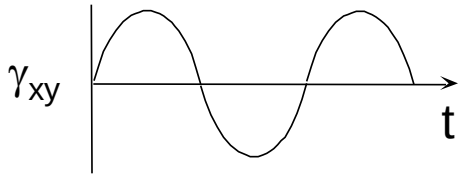

$$\gamma_{xy} = (1+\nu)\varepsilon_o \sin(\omega t)$$

In-phase

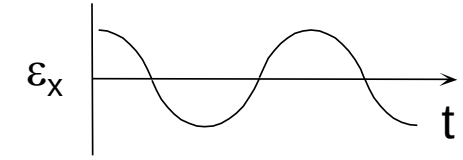

$$\varepsilon_x = \varepsilon_o \cos(\omega t)$$

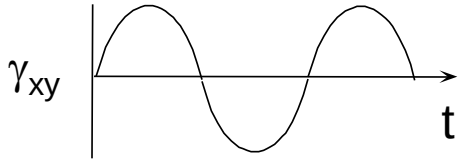

$$\gamma_{xy} = (1+\nu)\varepsilon_o \sin(\omega t)$$

Out-of-phase

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

In-Phase

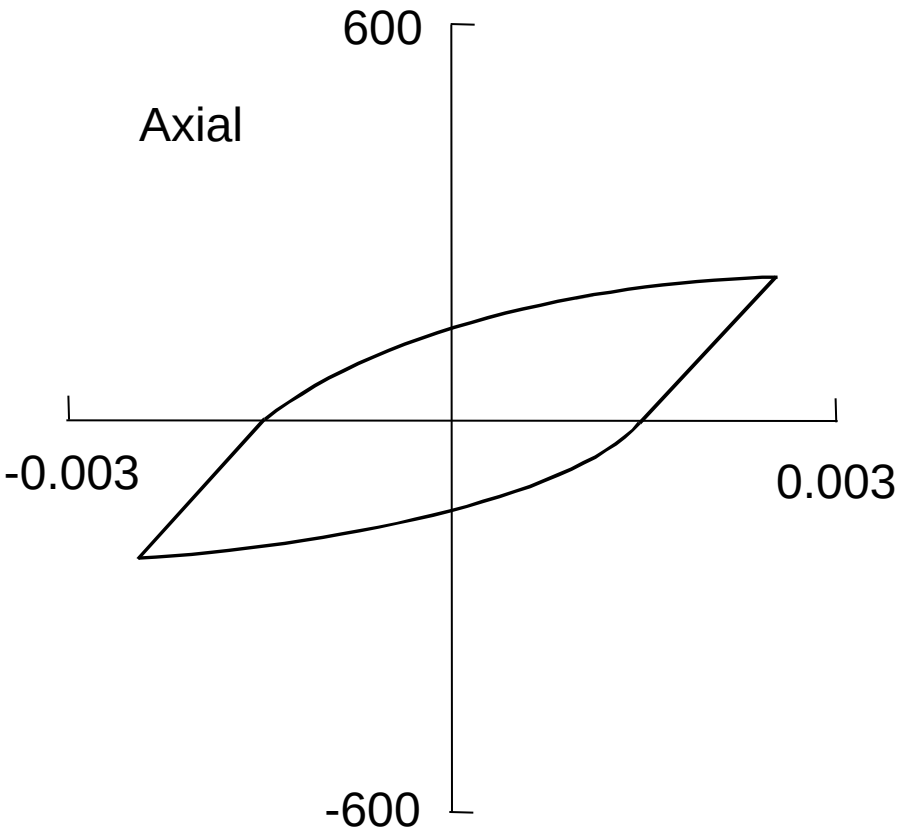

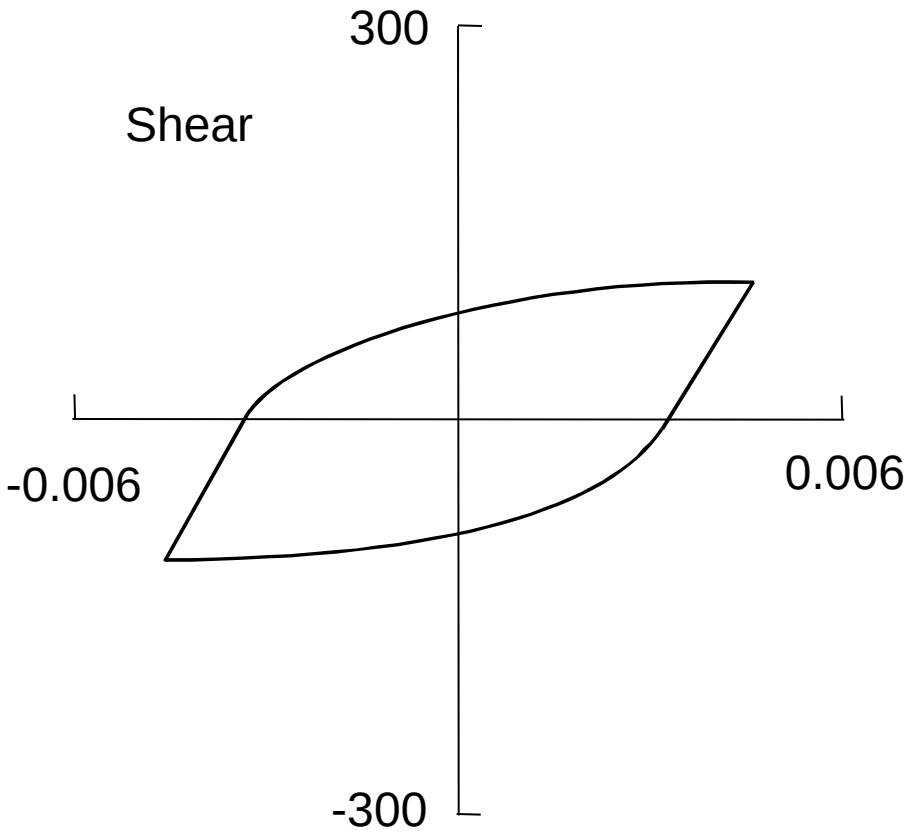

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

90° Out-of-Phase

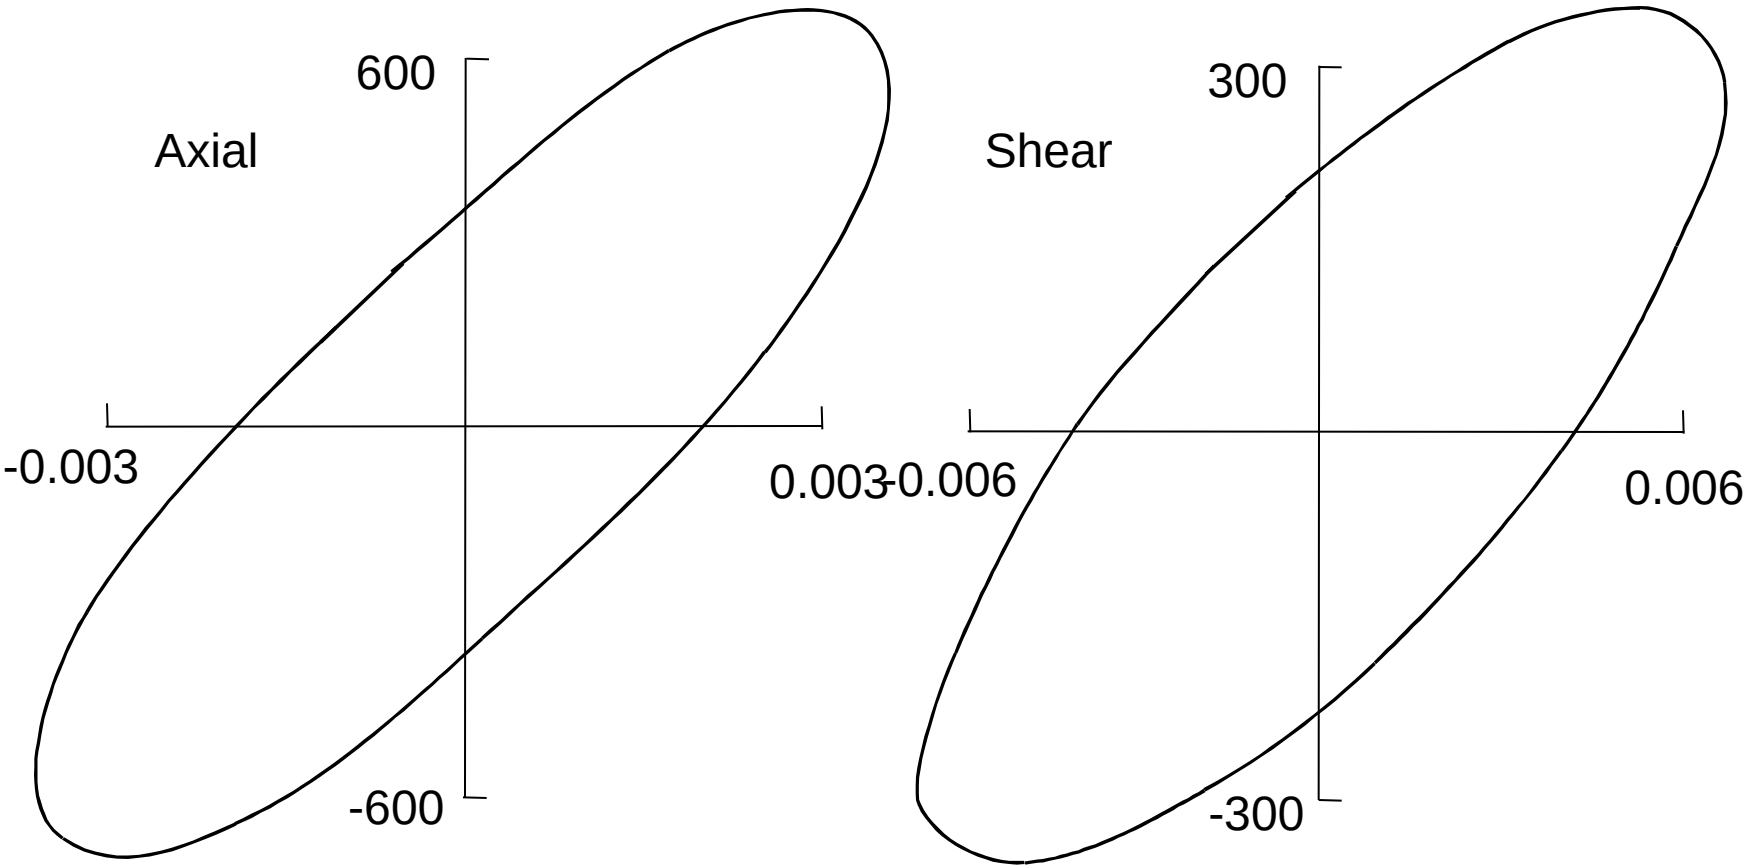

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Critical Plane

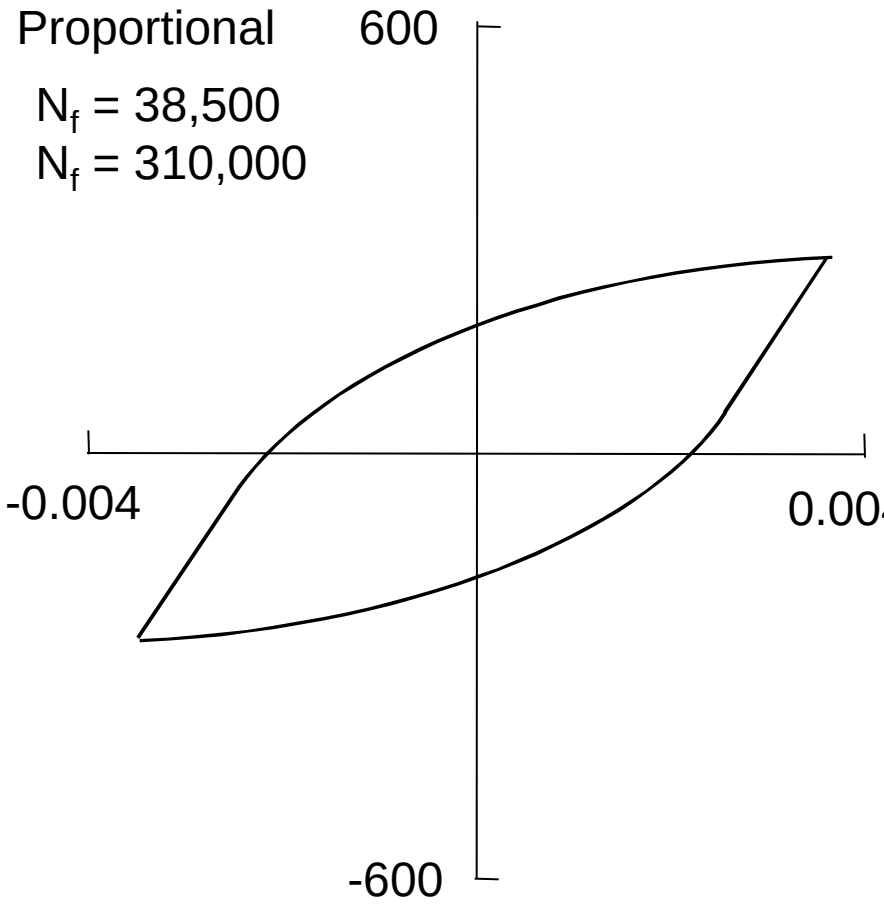

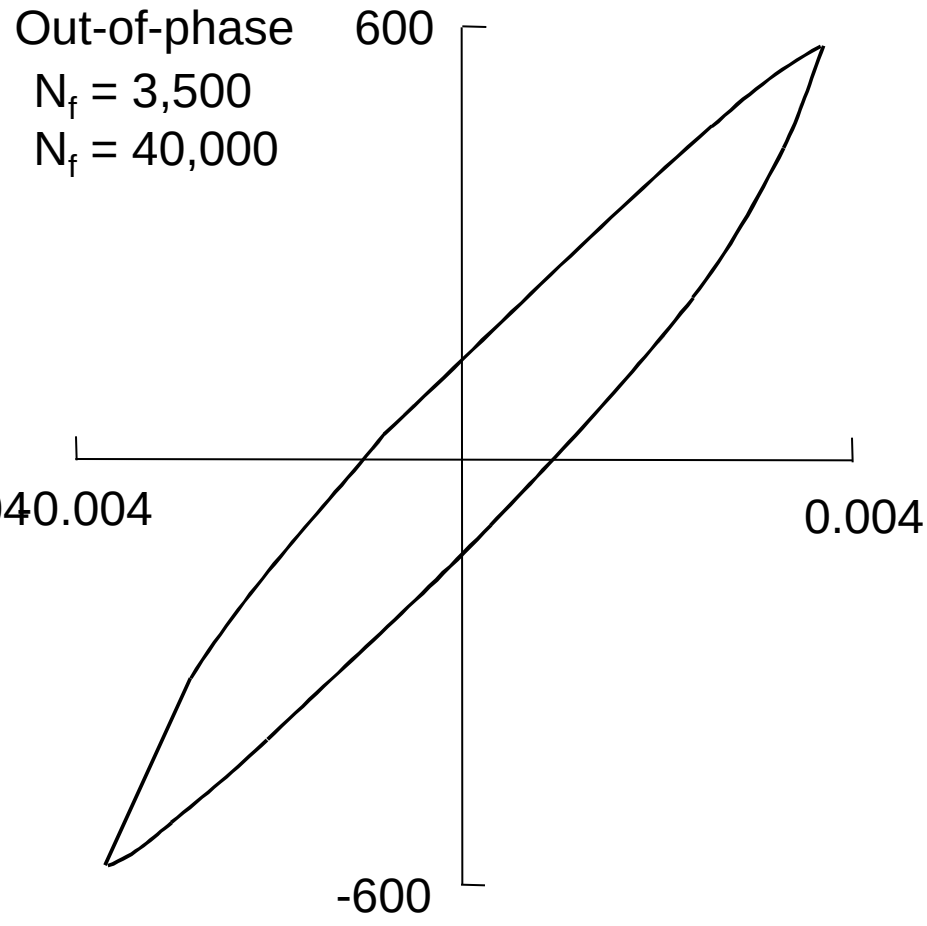

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Loading Histories

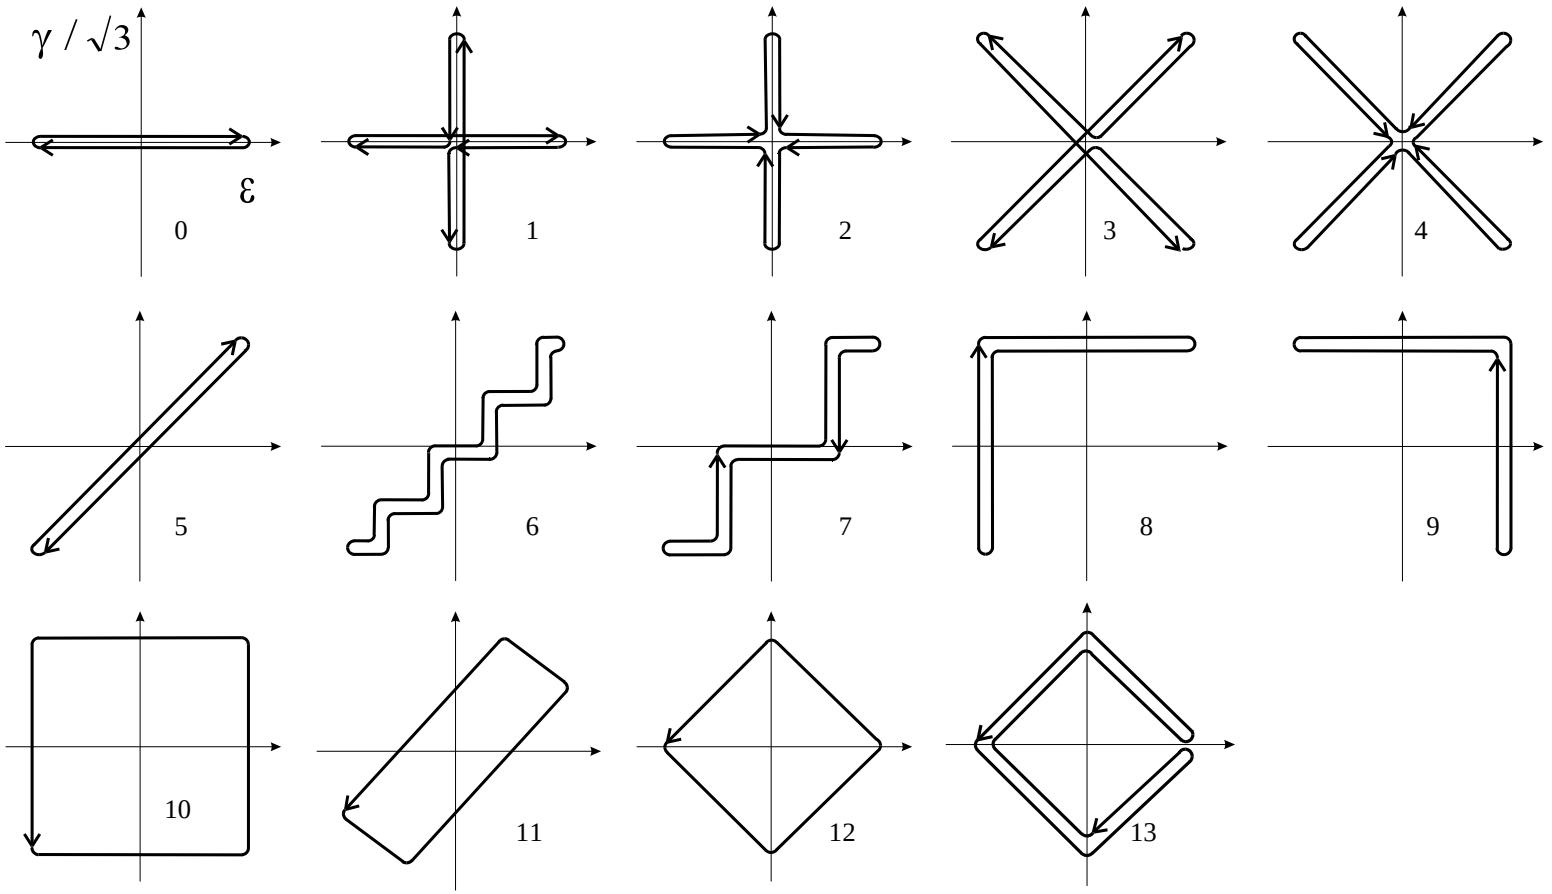

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress-Strain Response

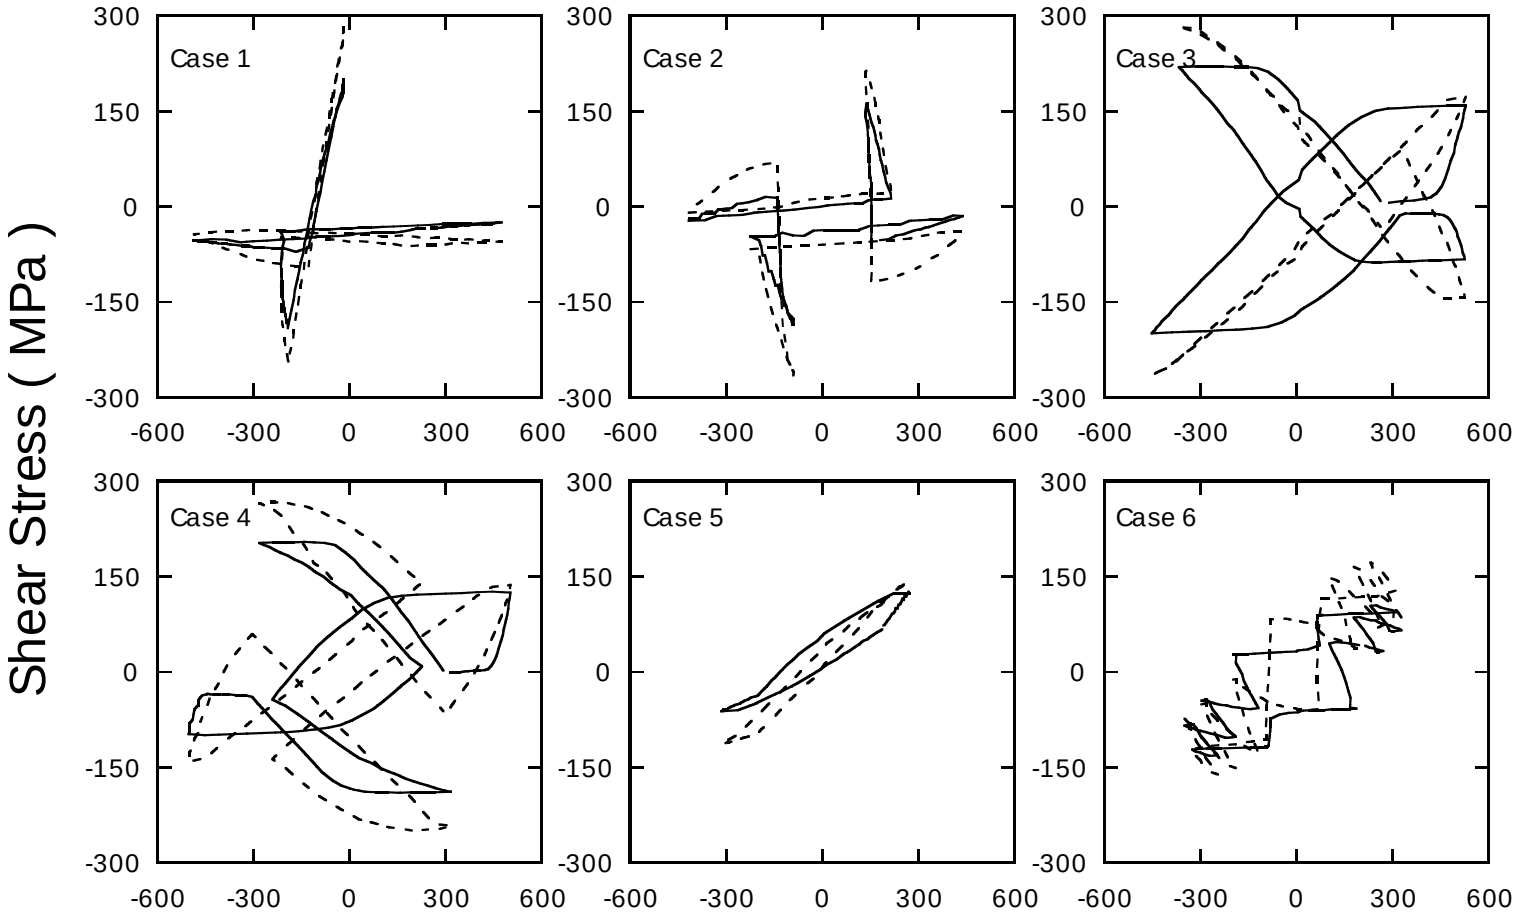

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress-Strain Response (continued)

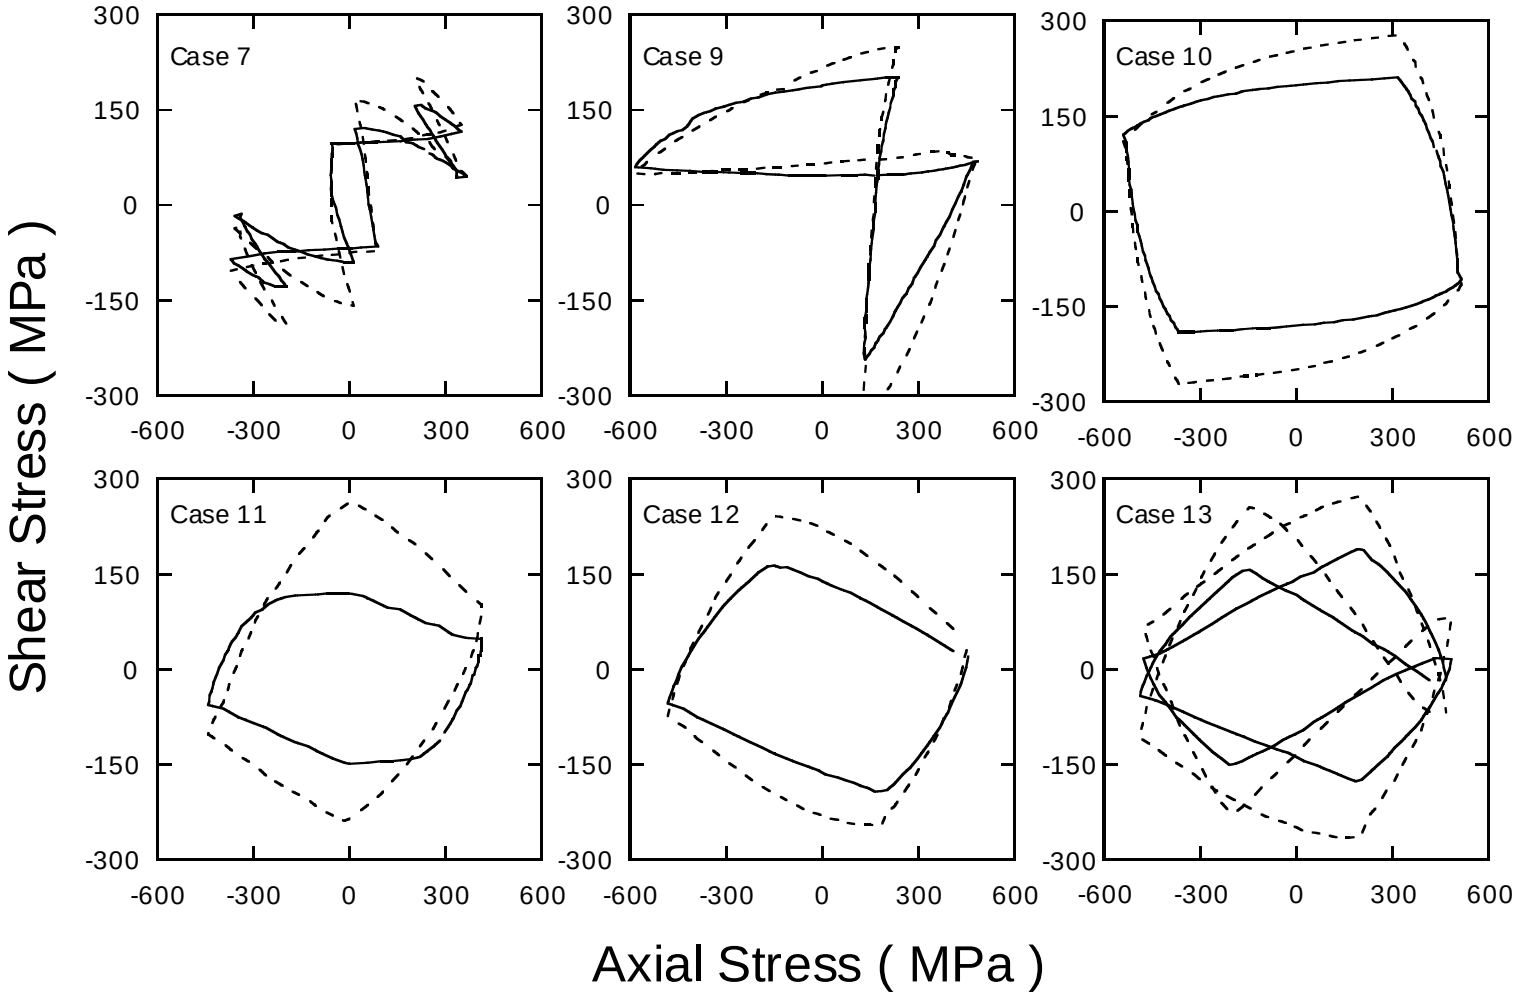

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Maximum Stress

All tests have the same strain ranges

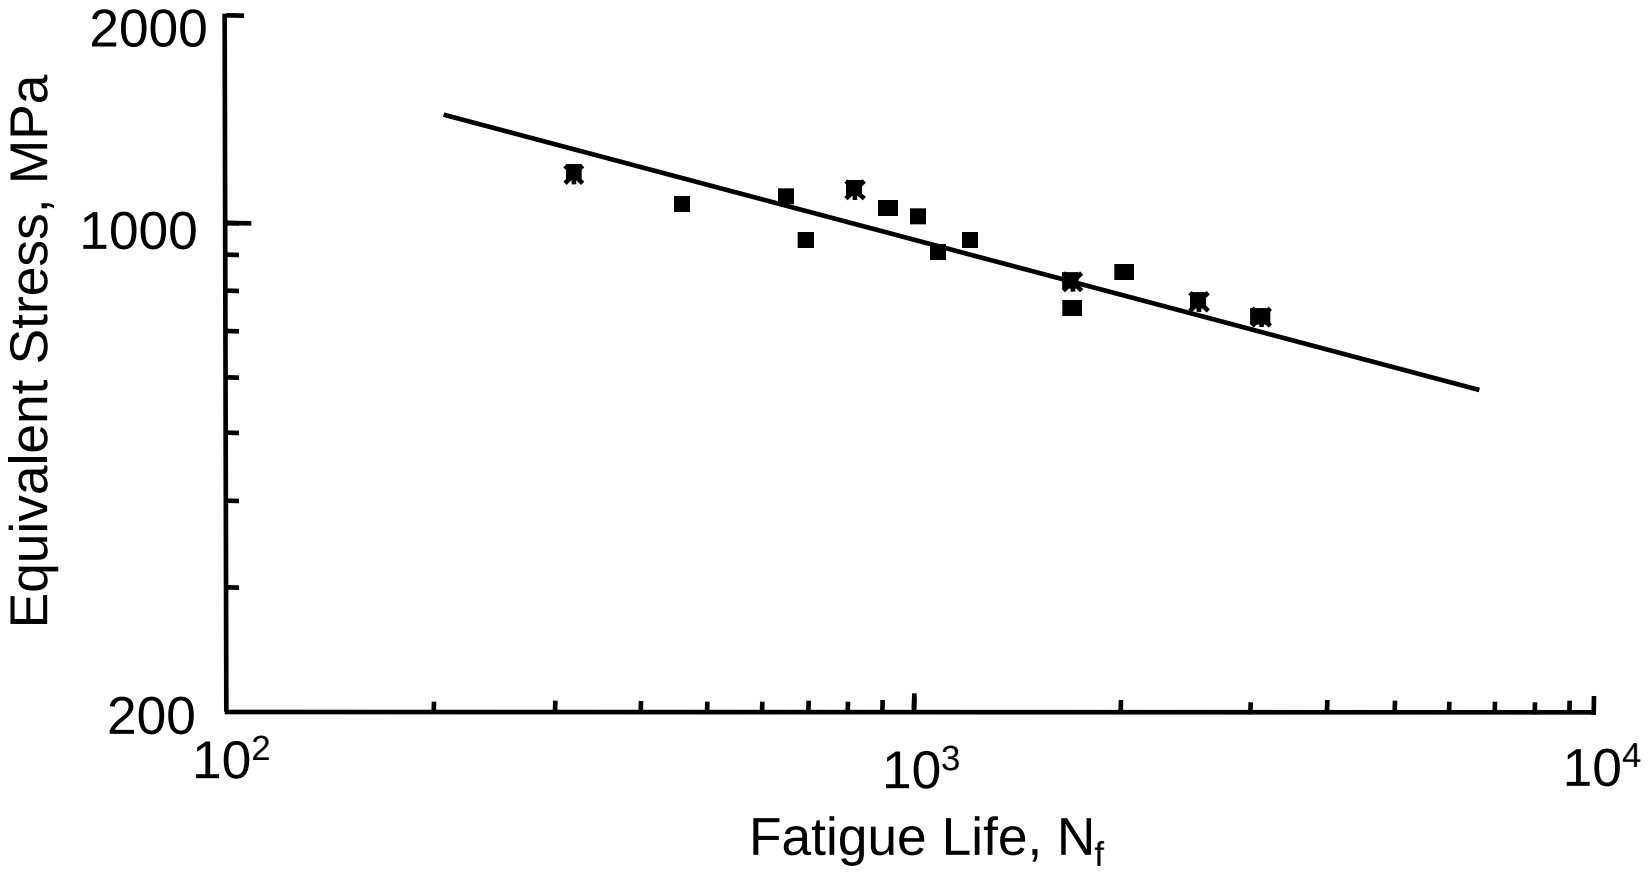

Nonproportional hardening results in lower fatigue lives

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Nonproportional Example

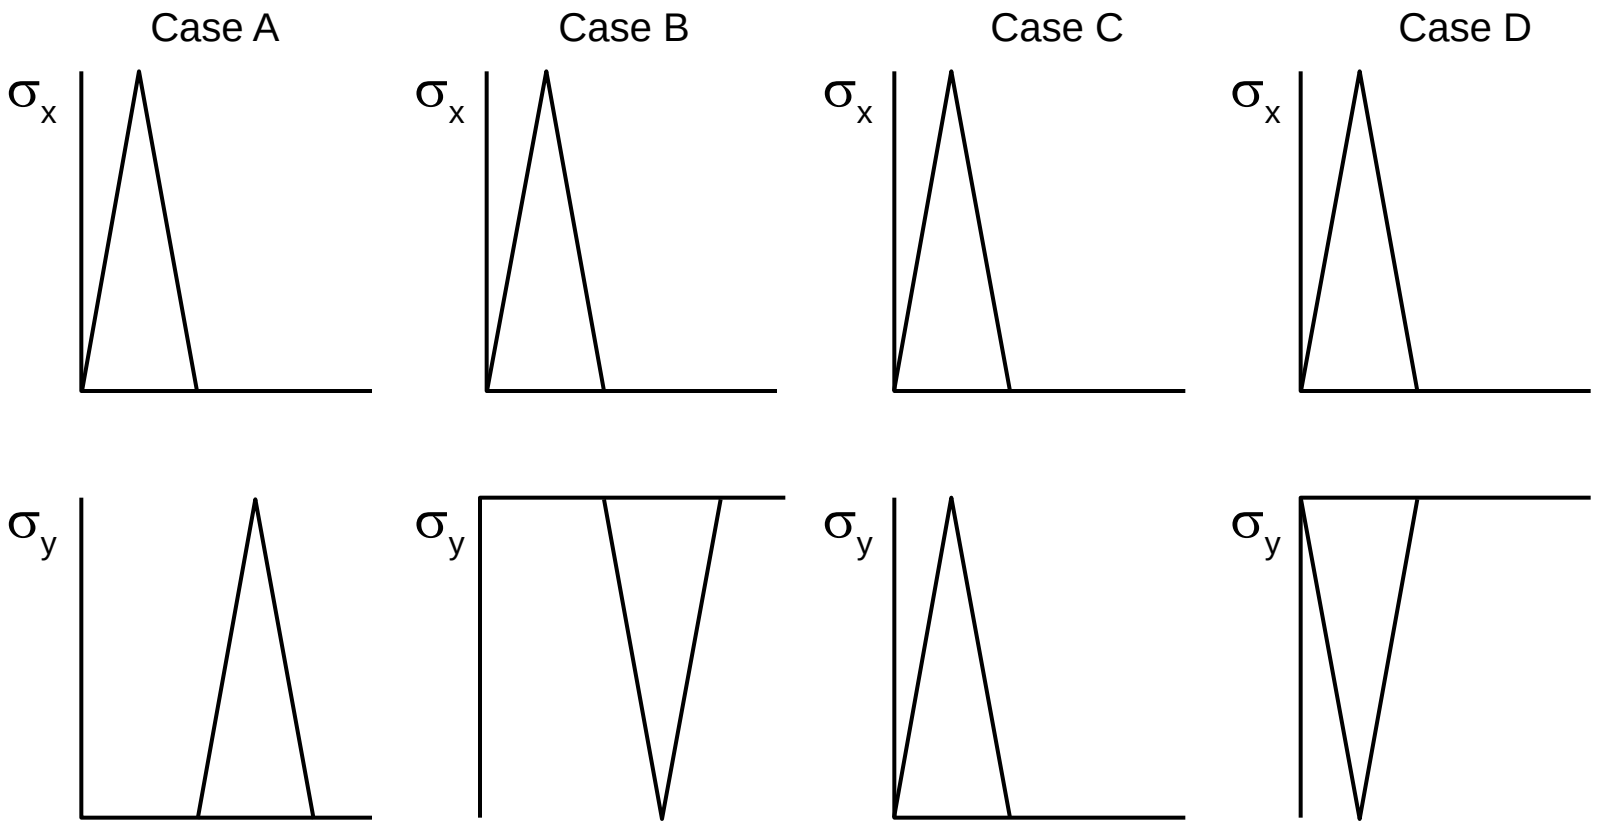

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Shear Stresses

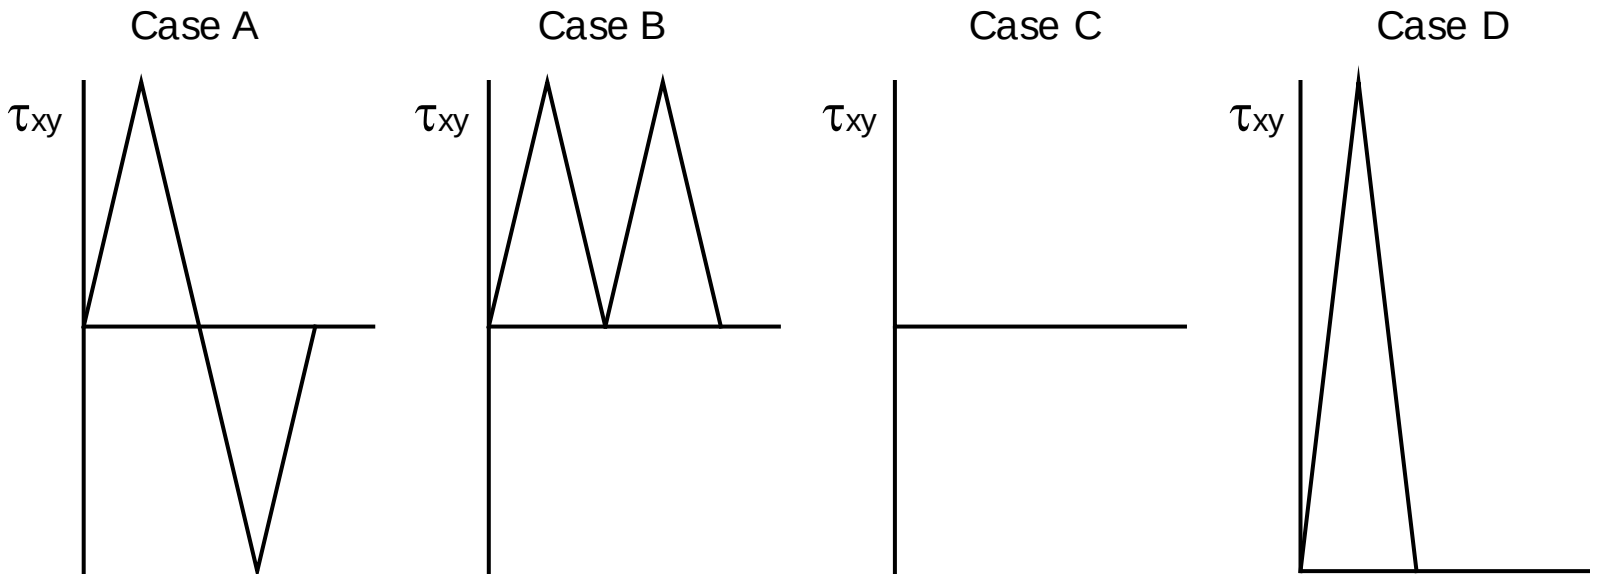

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Simple Variable Amplitude History

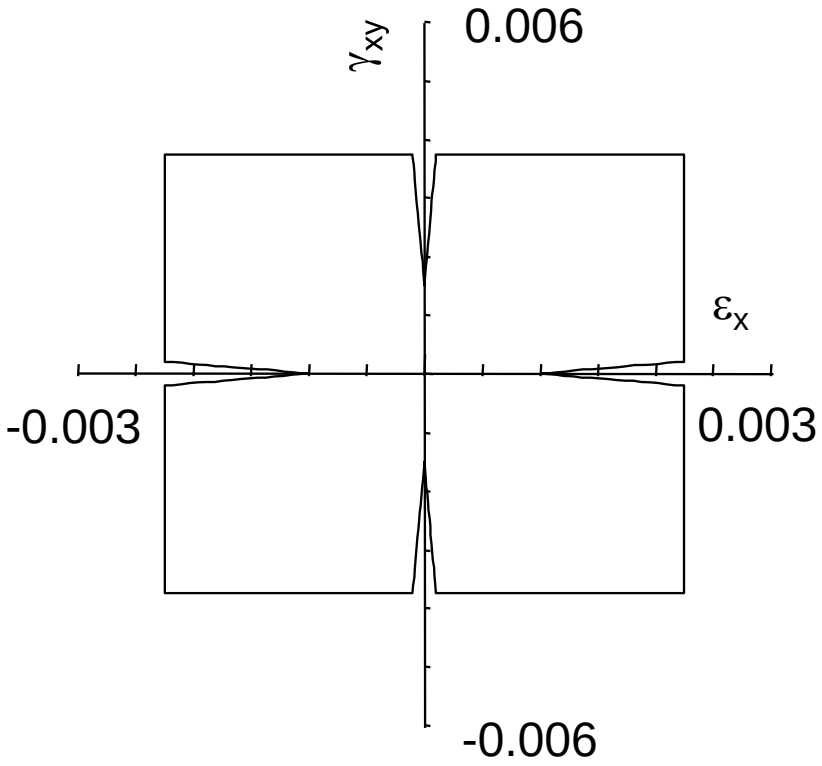

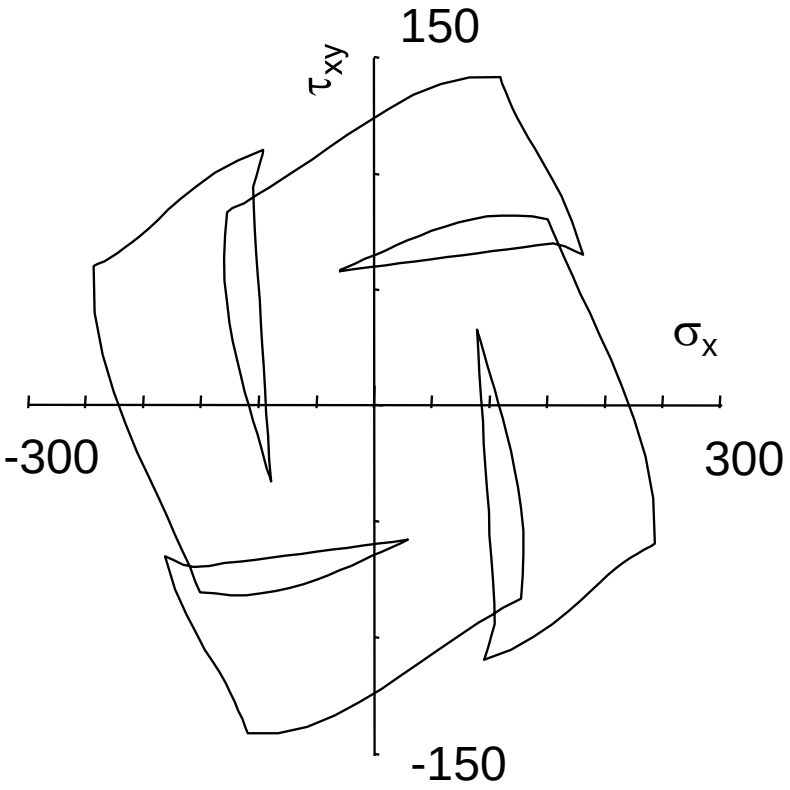

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress-Strain on 0° Plane

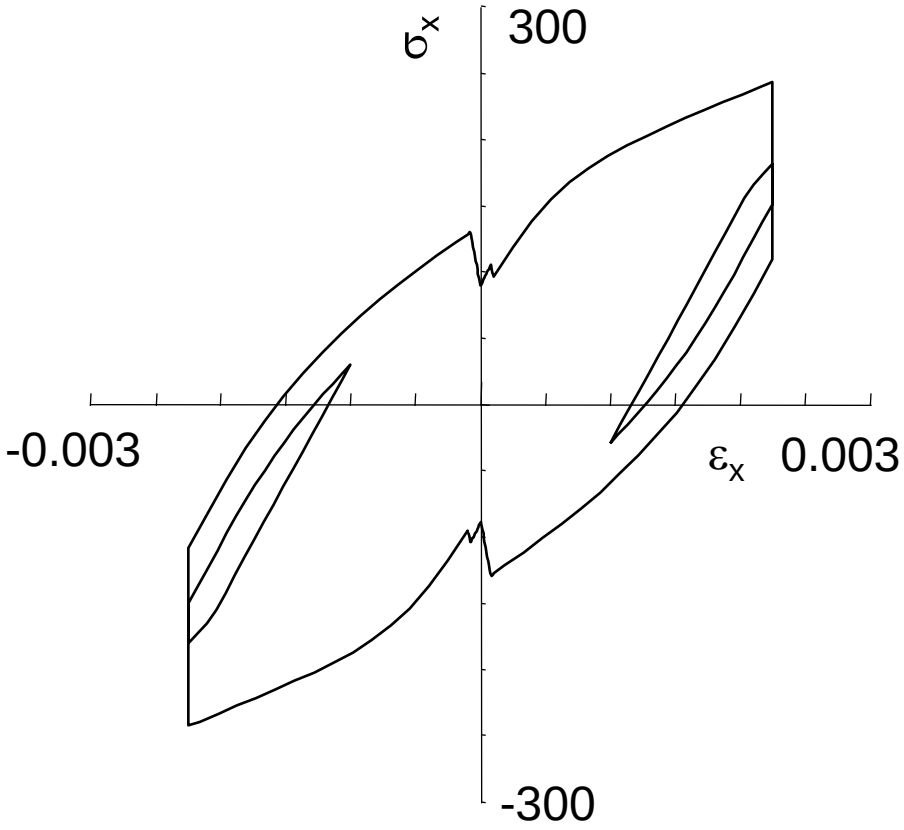

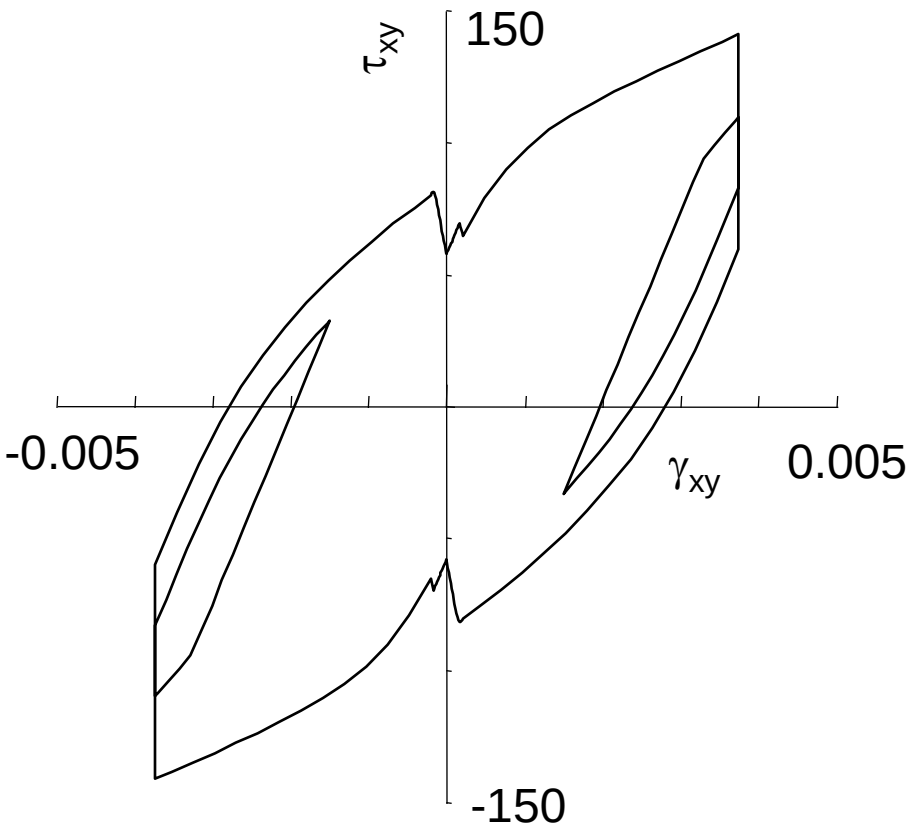

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress-Strain on 30° and 60° Planes

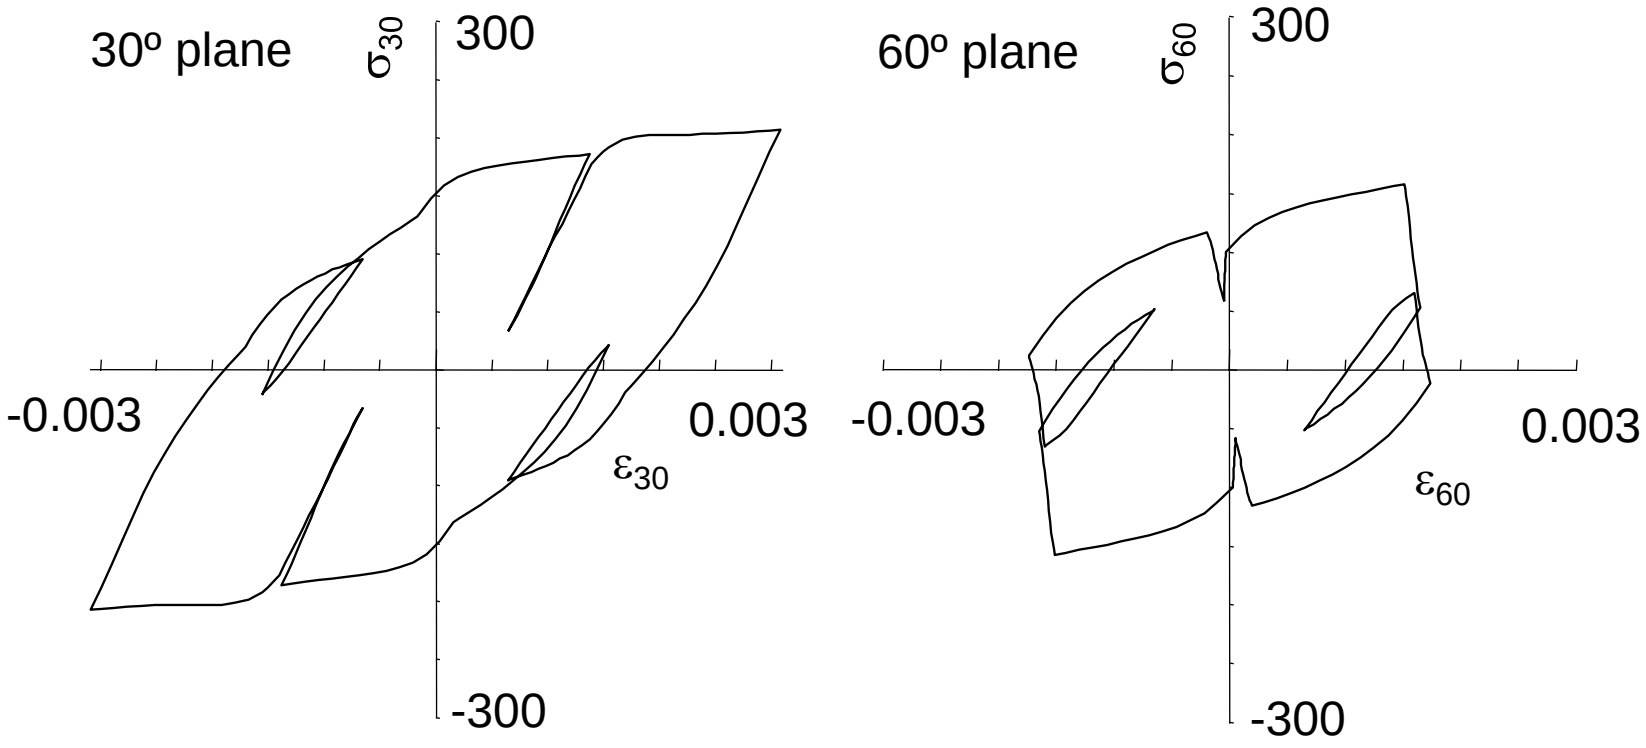

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress-Strain on 120° and 150° Planes

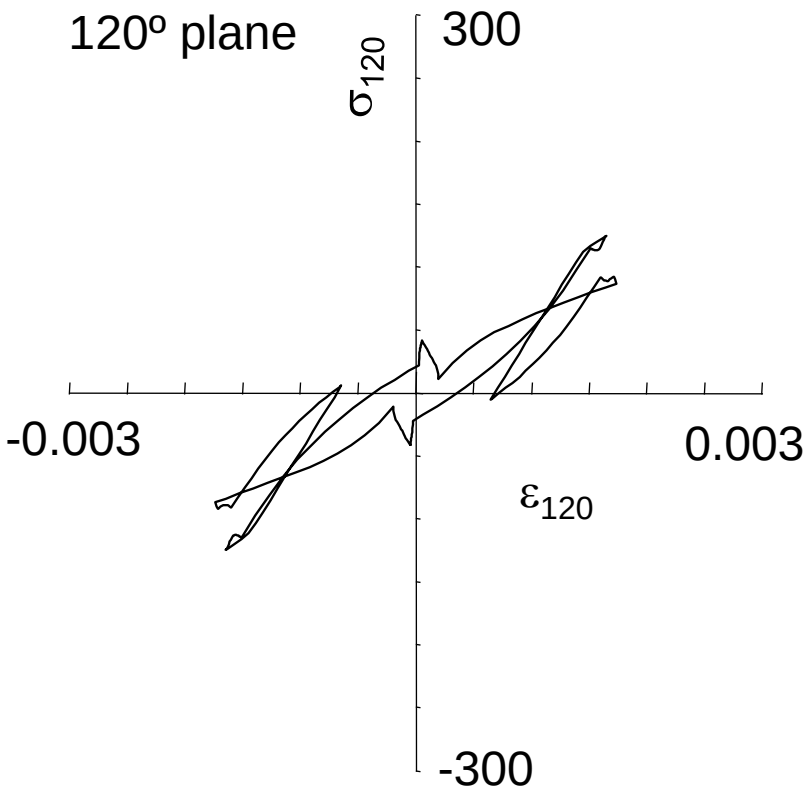

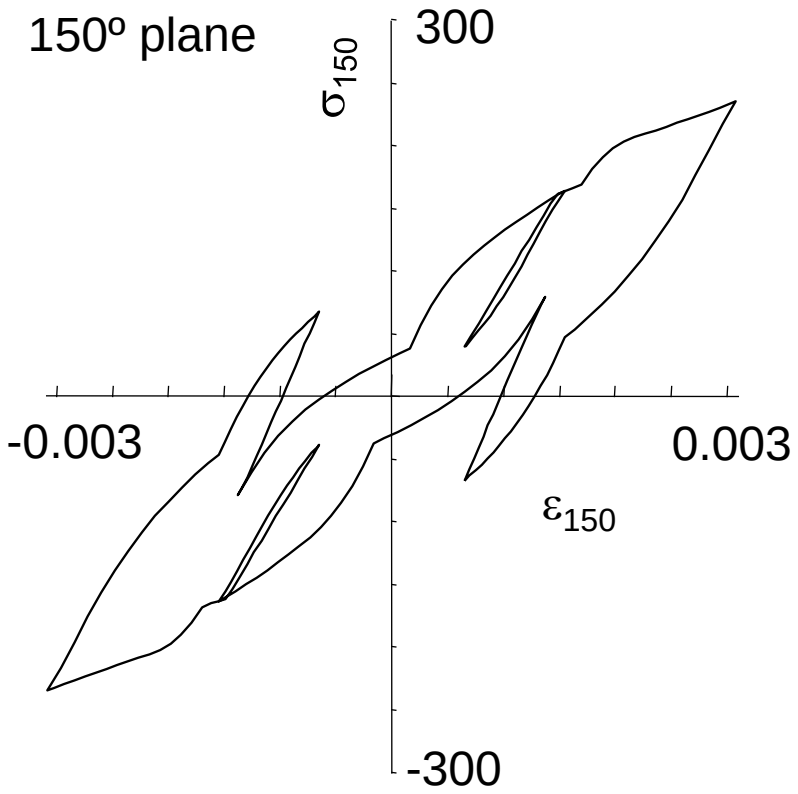

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Shear Strain History on Critical Plane

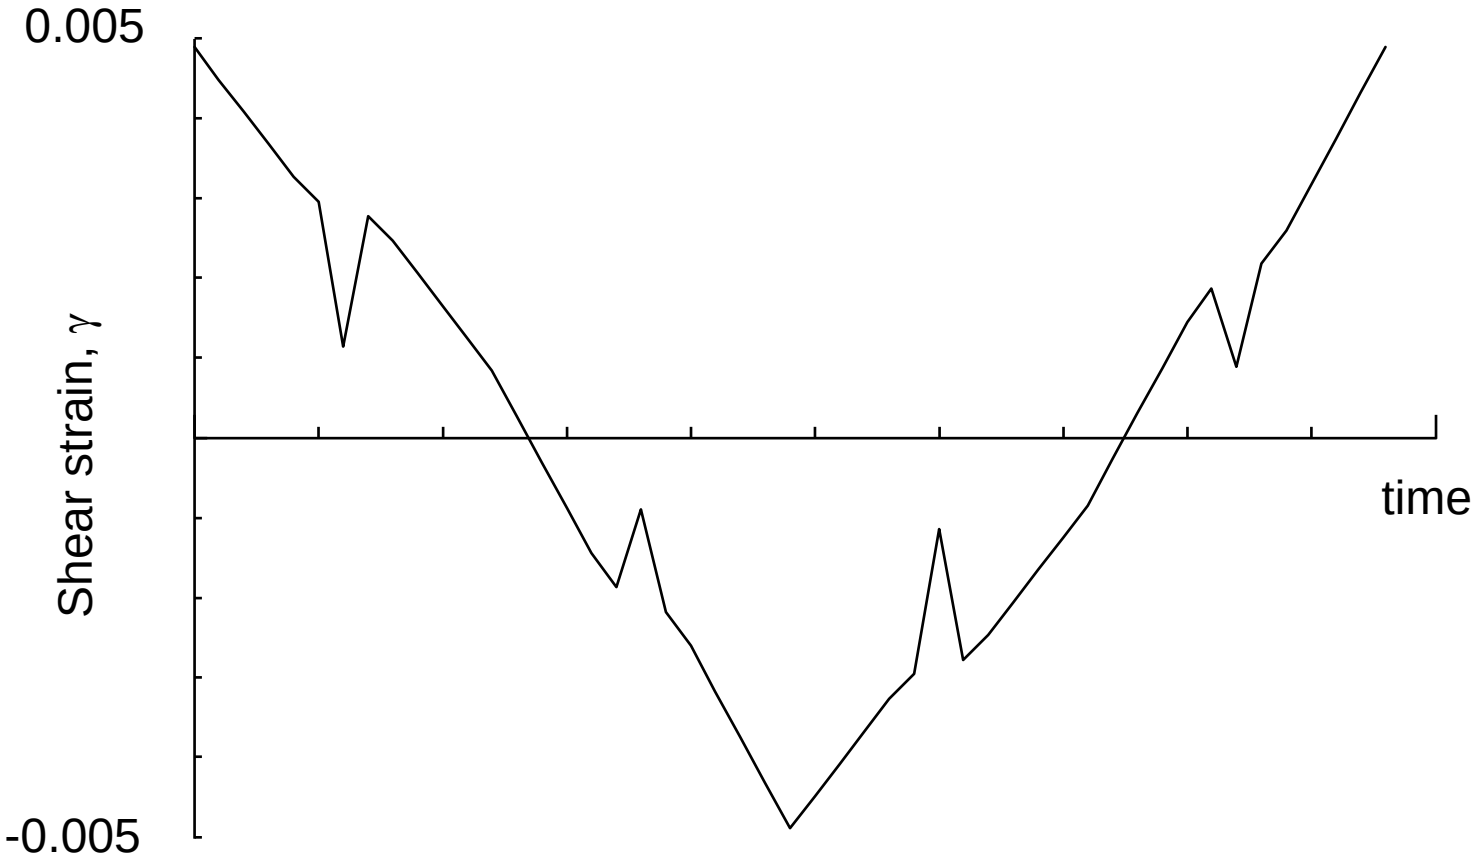

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatigue Calculations

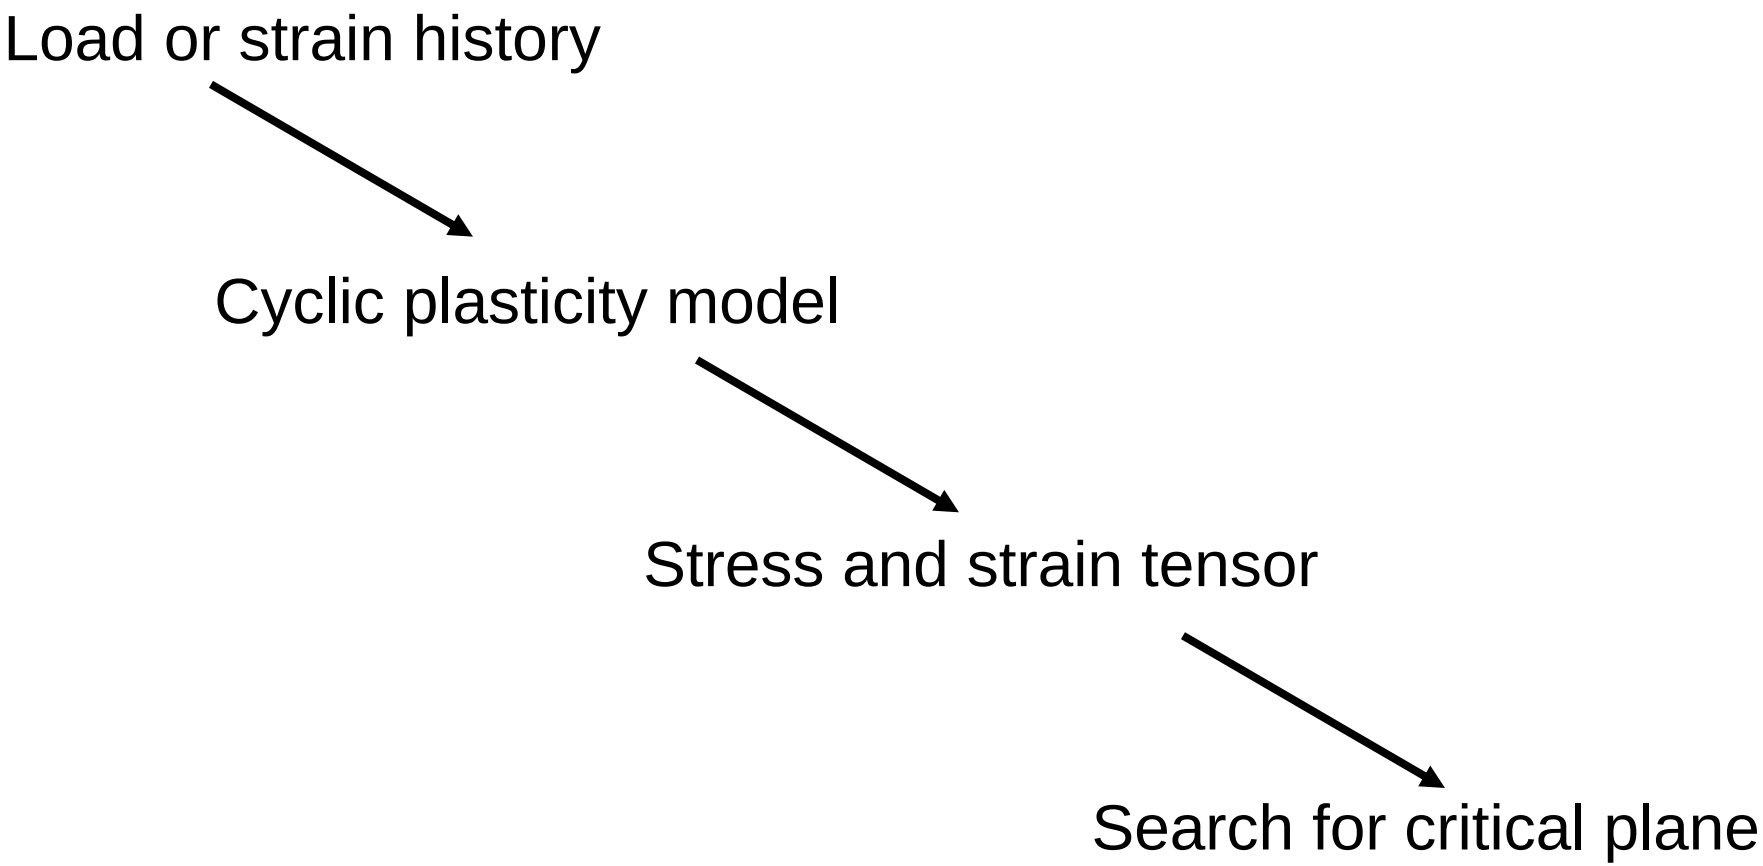

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Nonproportional Loading Summary

- Nonproportional cyclic hardening increases stress levels
- Critical plane models are used to assess fatigue damage

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Notches

- Stress and strain concentrations
- Nonproportional loading and stressing
- Fatigue notch factors
- Cracks at notches

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Notched Shaft Loading

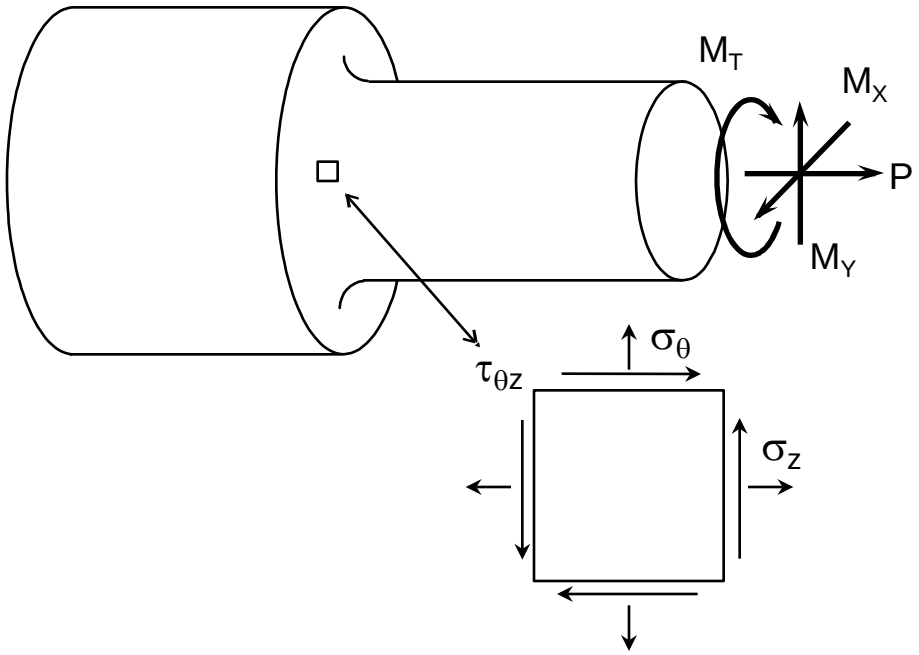

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress Concentration Factors

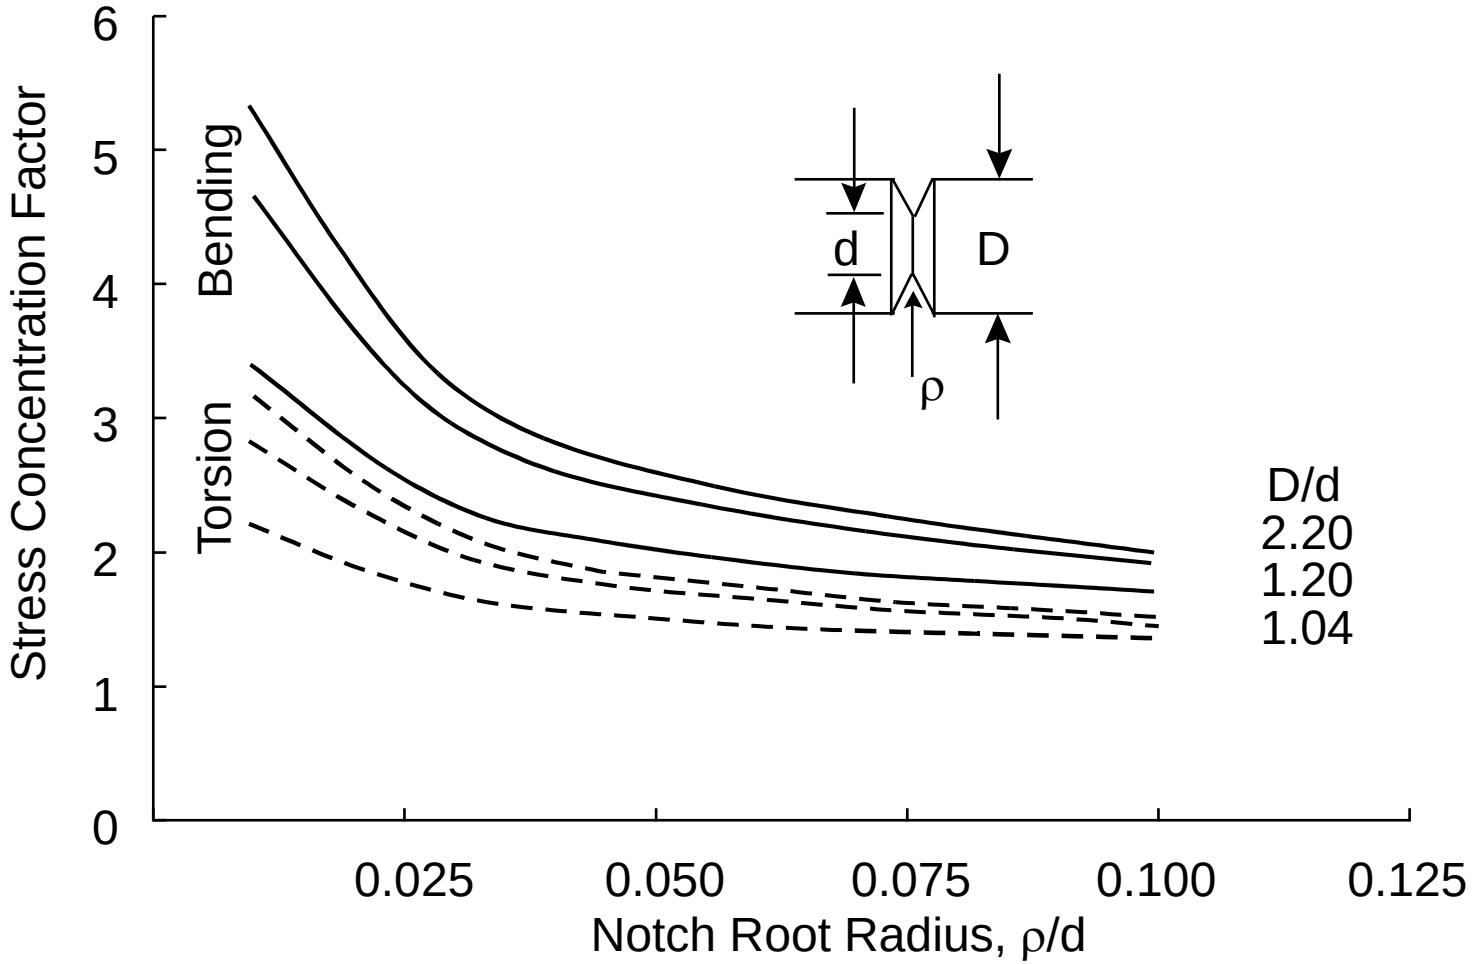

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Hole in a Plate

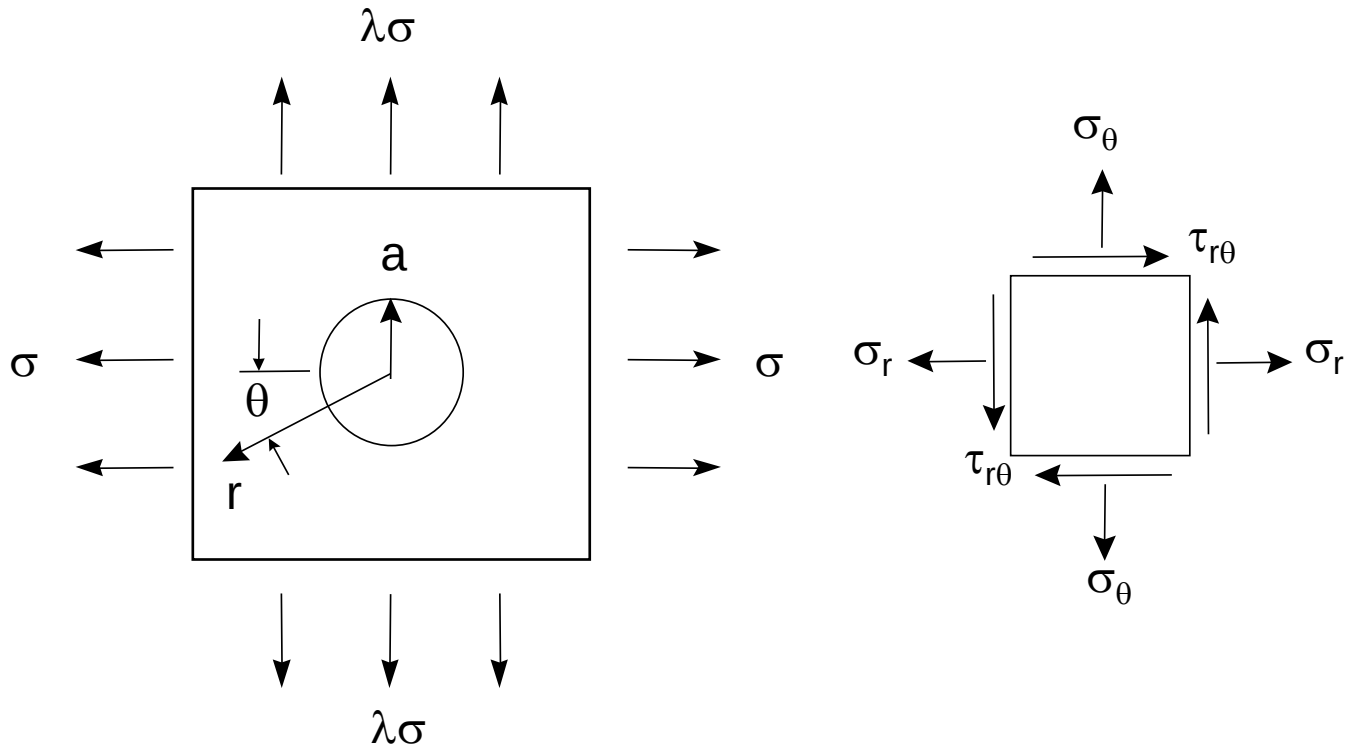

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stresses at the Hole

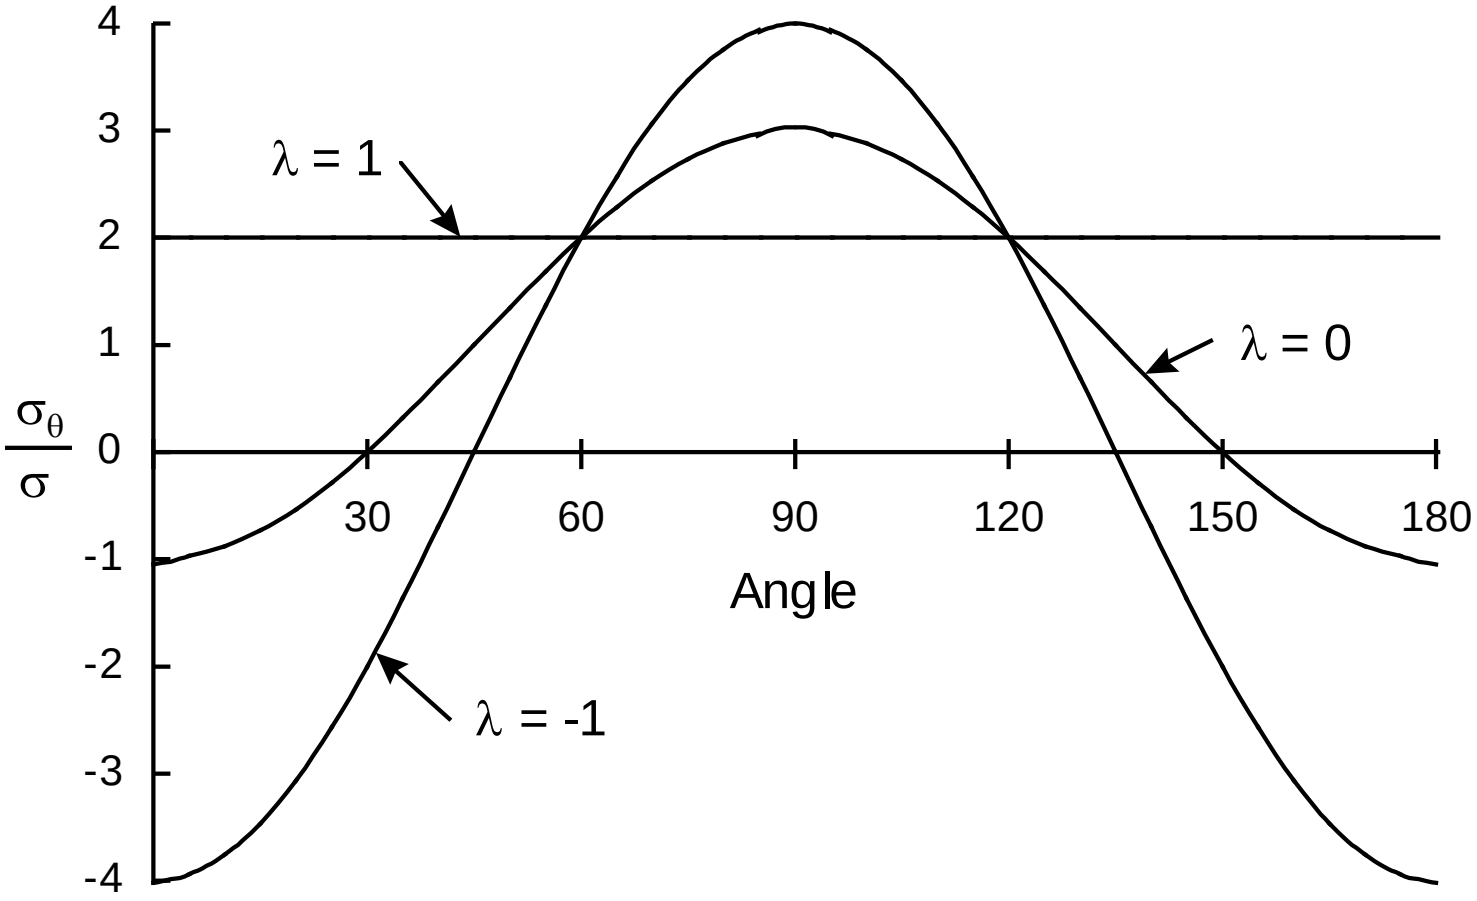

Stress concentration factor depends on type of loading

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Shear Stresses during Torsion

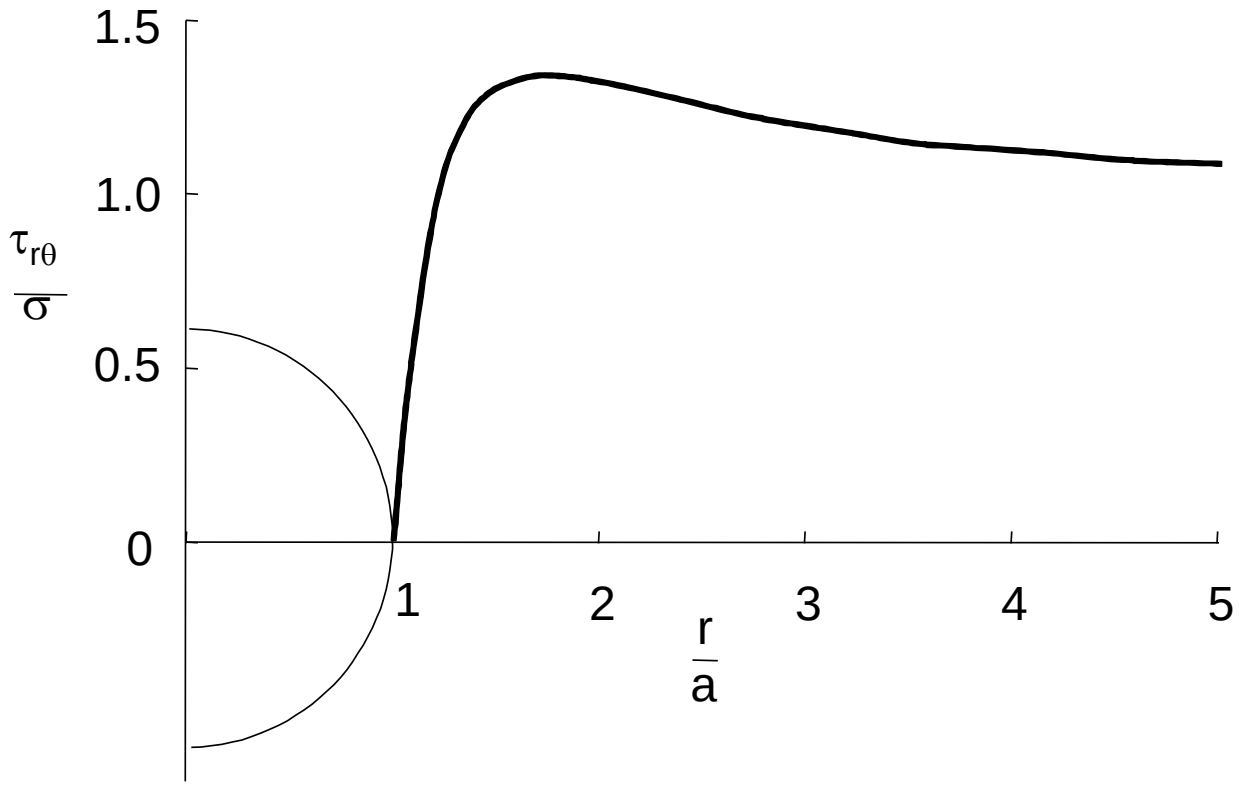

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Torsion Experiments

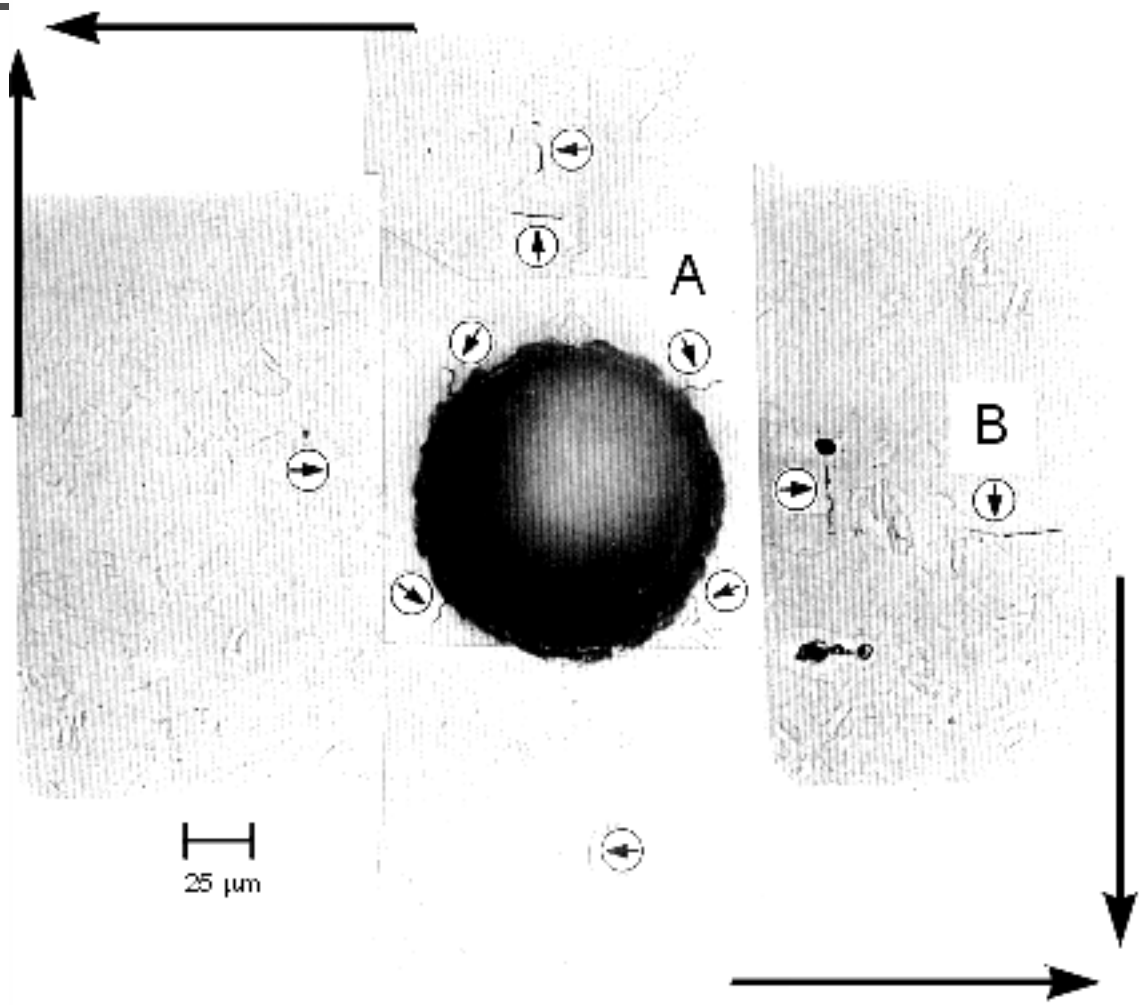

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Multiaxial Loading

- Uniaxial loading that produces multiaxial stresses at notches
- Multiaxial loading that produces uniaxial stresses at notches
- Multiaxial loading that produces multiaxial stresses at notches

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Thickness Effects

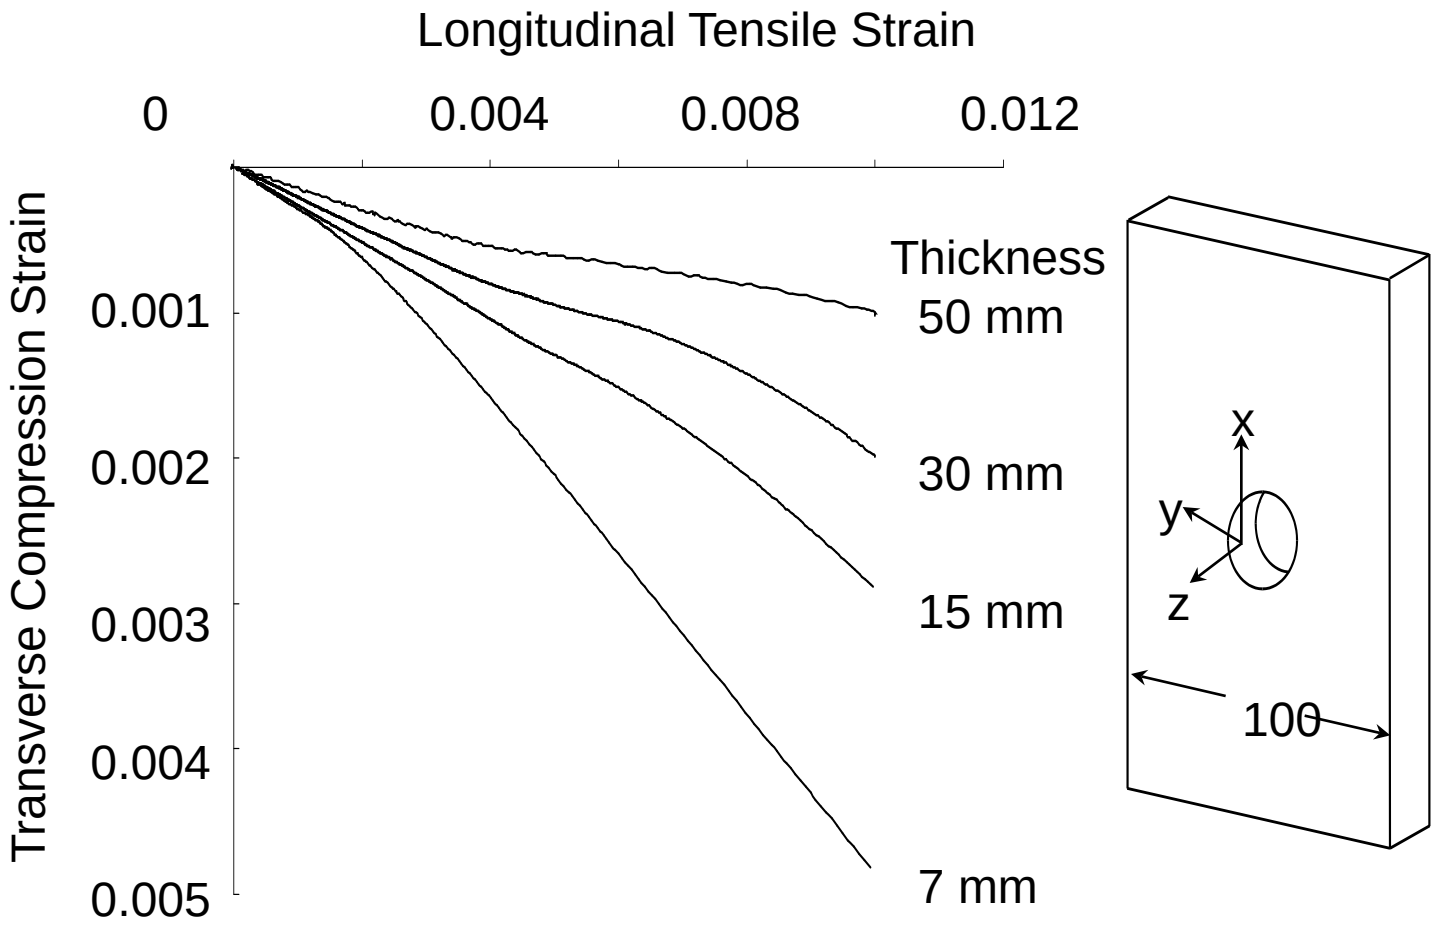

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Applied Bending Moments

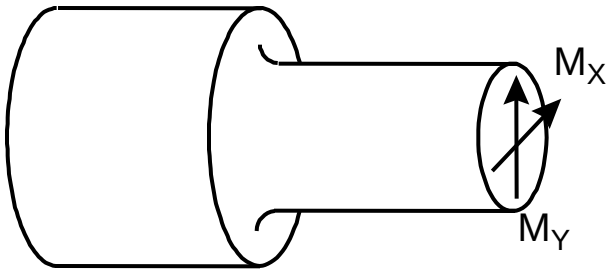

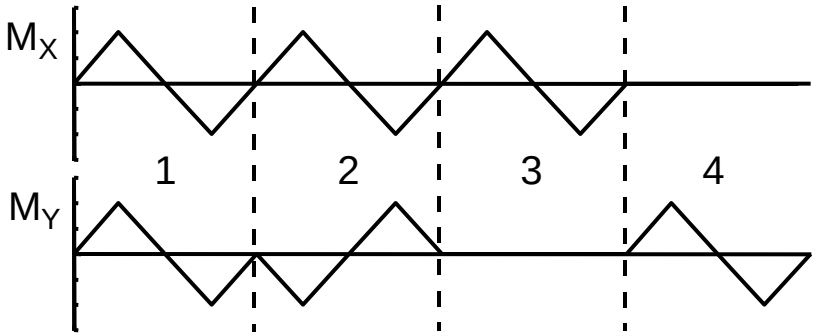

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Bending Moments on the Shaft

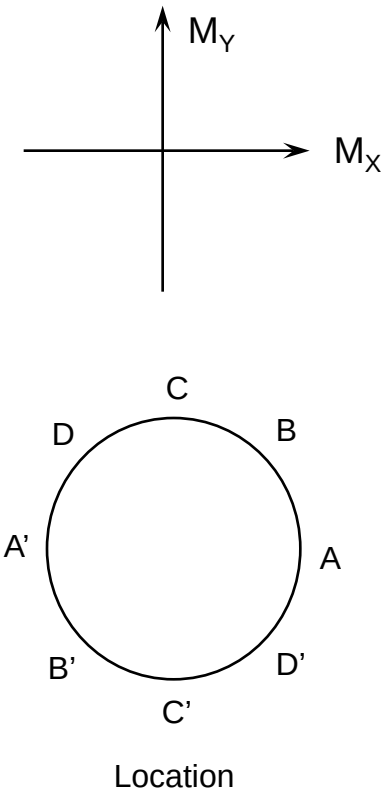

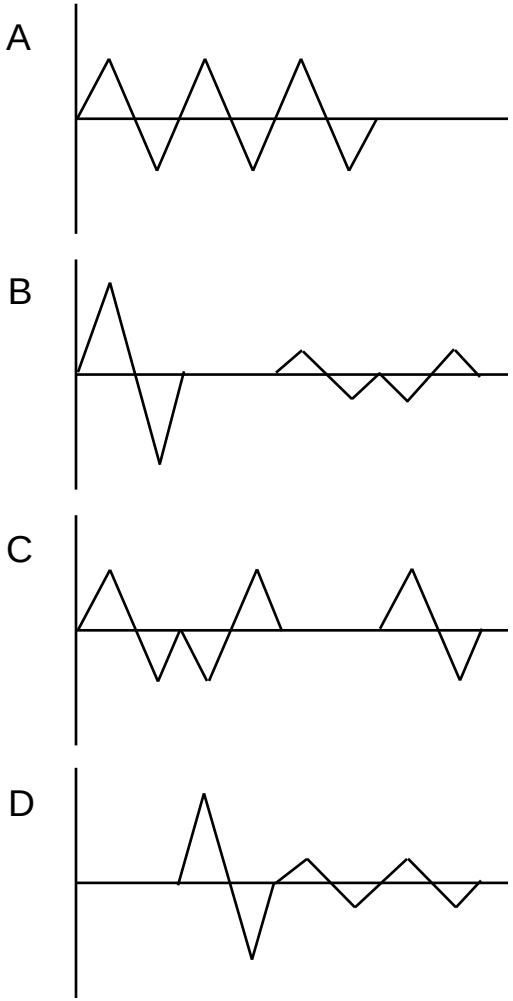

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Bending Moments

ΔM	A	B	C	D
2.82		1		1
2.00	3		2	
1.41		2		1
1.00			2	
0.71				2

$$\Delta\overline{M} = \sqrt[5]{\sum \Delta M^5}$$

	A	B	C	D
$\Delta\overline{M}$	2.49	2.85	2.31	2.84

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Torsion Loading

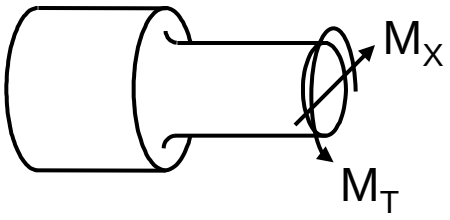

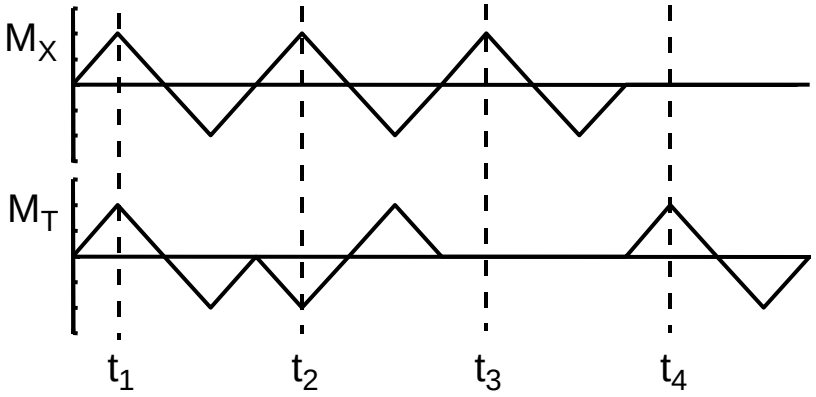

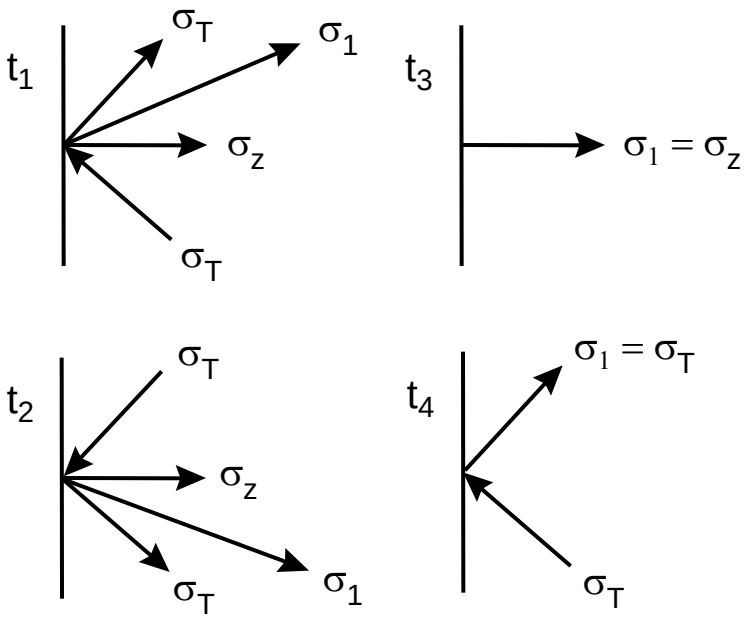

Out-of-phase shear loading is needed to produce nonproportional stressing

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Plate and Shell Structures

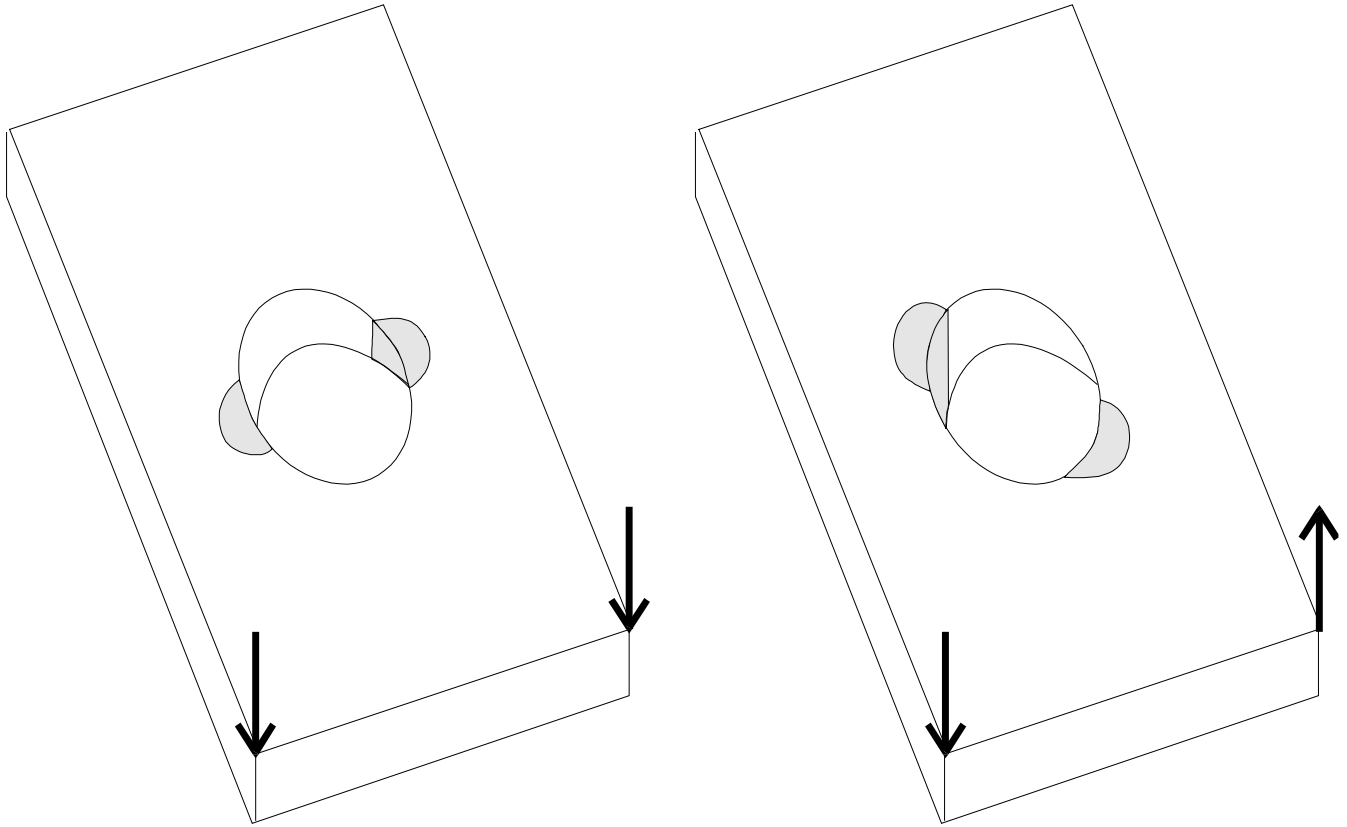

$K_t = 3$

$K_t = 4$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatigue Notch Factors

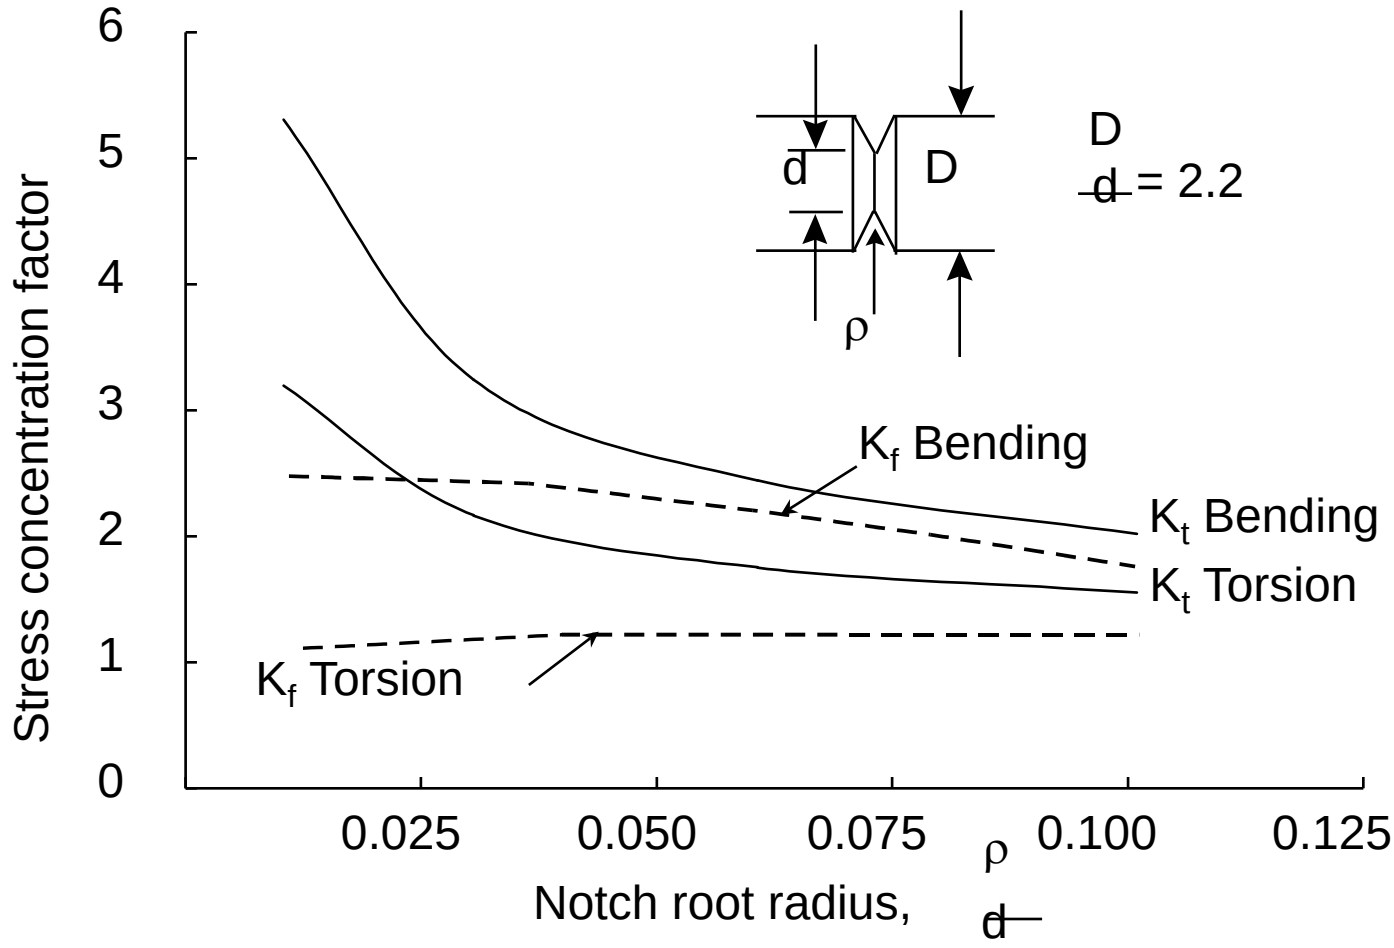

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fatigue Notch Factors (continued)

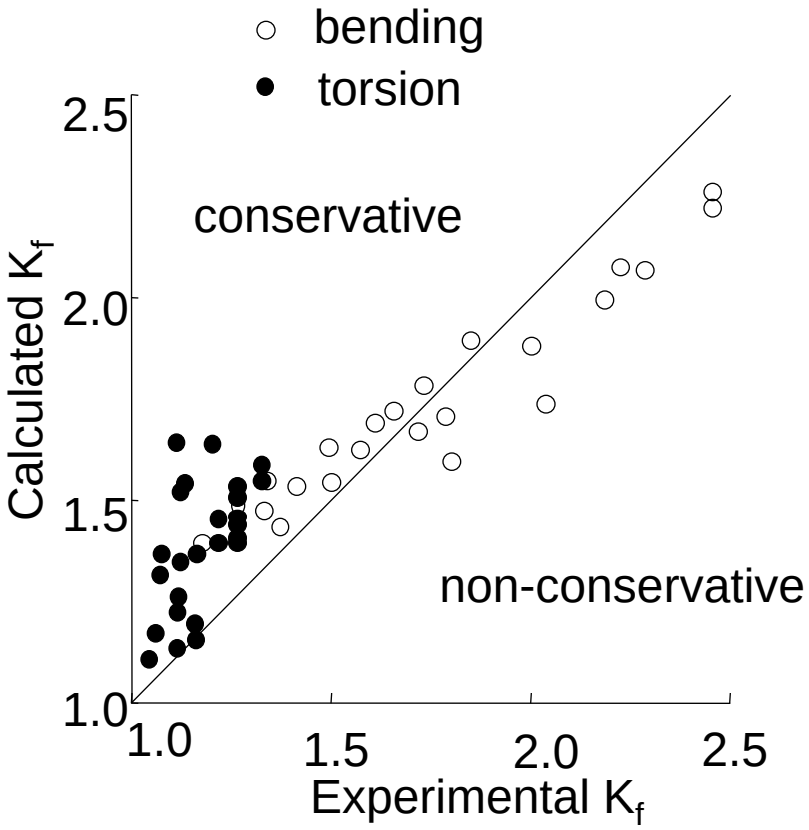

Peterson's Equation

$$K_f = 1 + \frac{K_T - 1}{1 + \frac{a}{r}}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Fracture Surfaces in Torsion

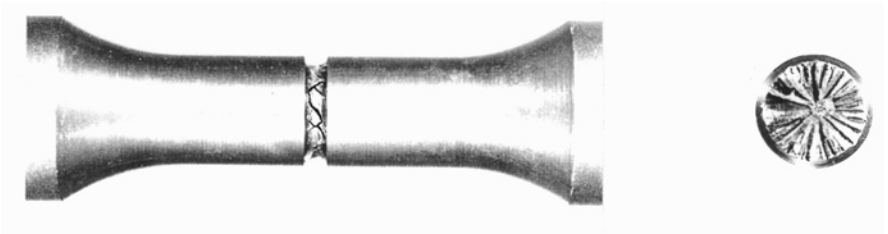

Circumferencial Notch

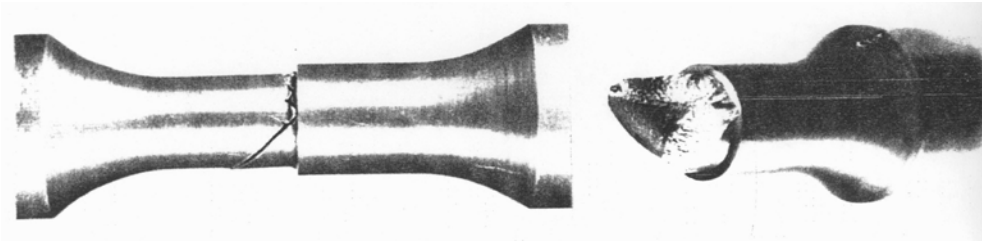

Shoulder Fillet

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Stress Intensity Factors

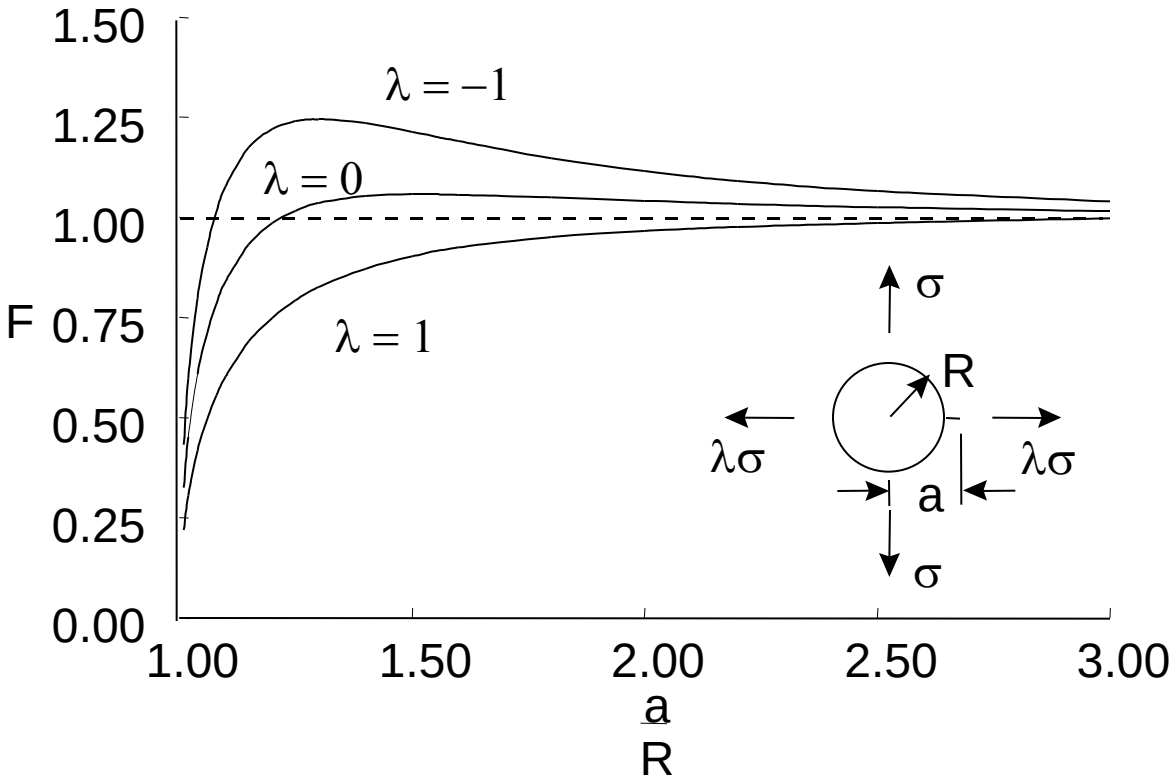

$$\frac{da}{dN} = C\left(\Delta K_{eq}\right)^m \qquad K_I = F\,\Delta\sigma\sqrt{\pi a}$$

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Crack Growth From a Hole

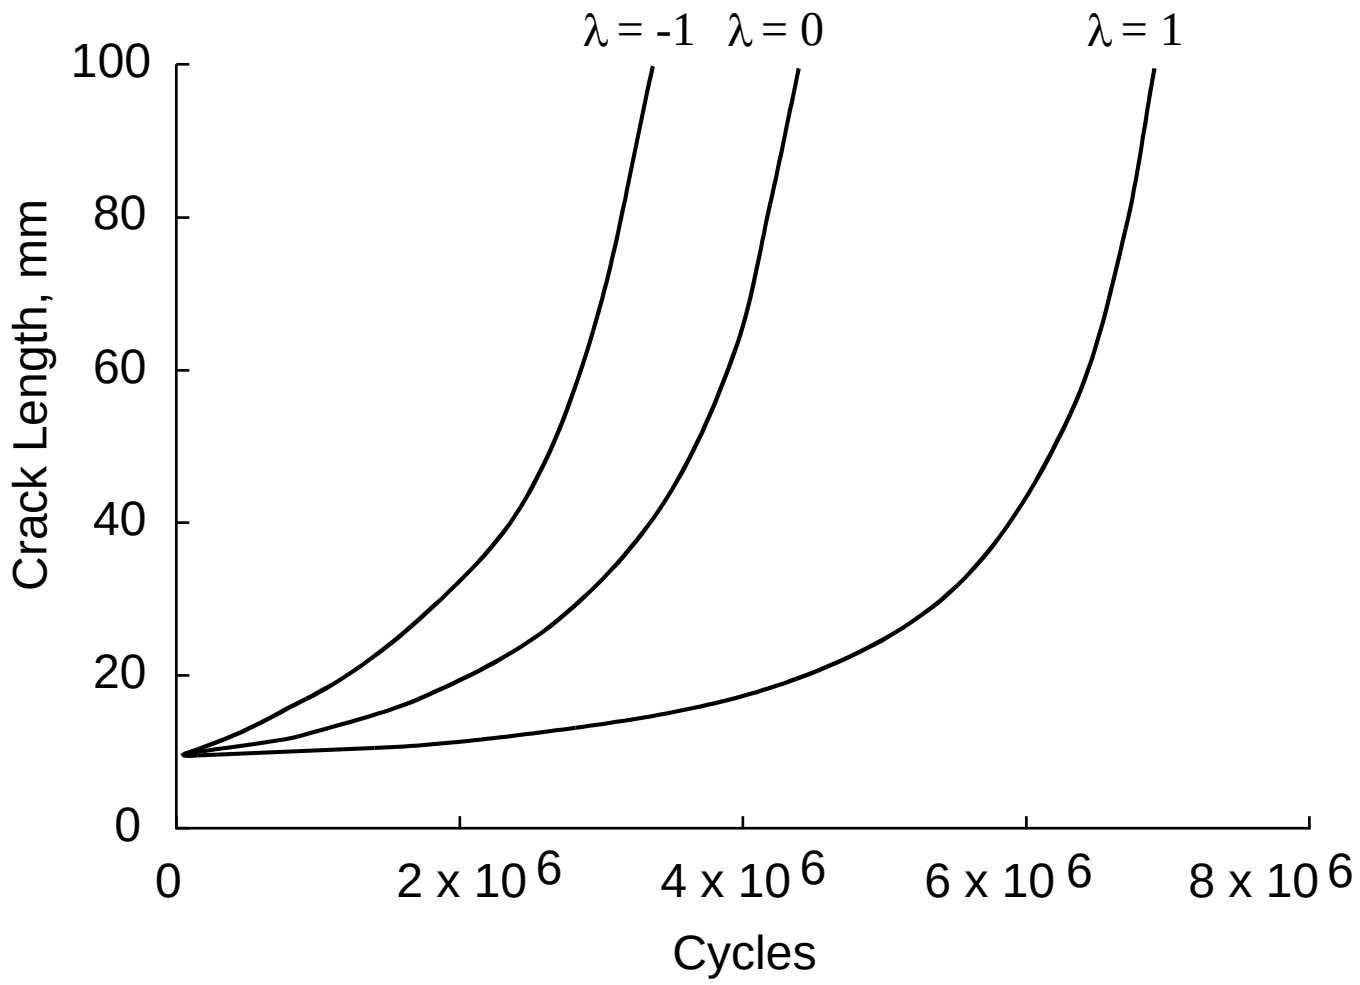

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Notches Summary

- Uniaxial loading can produce multiaxial stresses at notches
- Multiaxial loading can produce uniaxial stresses at notches
- Multiaxial stresses are not very important in thin plate and shell structures
- Multiaxial stresses are not very important in crack growth

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

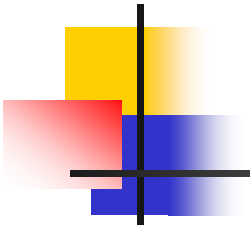

Final Summary

- Fatigue is a planar process involving the growth of cracks on many size scales
- Critical plane models provide reasonable estimates of fatigue damage

© 2001-2011 Darrell Socie, University of Illinois at Urbana-Champaign, All Rights Reserved

Multiaxial Fatigue

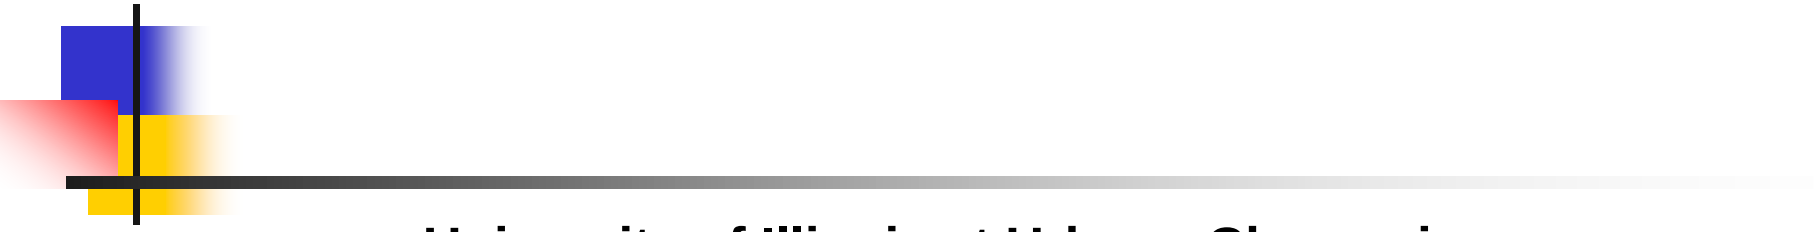

University of Illinois at Urbana-Champaign